

Product Data Sheet – Titanium Alloys

Titanium Grade 2 UNS-R50400

Titanium grade 2 is commercially pure titanium. It has outstanding corrosion resistance and useful strength (similar to austenitic stainless steels) at low density. It has good weldability and is easily formable. It is the most commonly used grade of titanium.

Typical Applications

Most of the applications of this grade are in the chemical industries. The most common uses are reactor autoclaves, piping and fittings, valves, heat exchangers and condensers.

Chemical Composition

ASTM B338 – Seamless & welded titanium & titanium alloy tubes for condensers & heat exchangers

Element	Titanium	Nitrogen	Carbon	Hydrogen	Iron	Oxygen	Residuals (each)	Residuals (total)
%	Balance	0.03 max	0.08 max	0.015 max	0.30 max	0.25 max	0.1 max	0.4 max

Specified Minimum Mechanical Properties

(ASTM B338 – Seamless & welded titanium & titanium alloy tubes for condensers & heat exchangers)

	0.2% Proof Stress	Tensile Strength	Elongation
	MPa	MPa	%
Annealed	275-450	345	20

Description

Titanium grade 2 is a commercially pure grades. It has excellent corrosion resistance in oxidising conditions, and is effectively immune from stress corrosion cracking, pitting corrosion and crevice corrosion in chloride solutions below 70°C. Titanium grade 2 is widely used in heat exchangers, where despite the low thermal conductivity of titanium the efficiency of heat transfer is high due to good strength, high resistance to erosion corrosion and the fouling resistance of the hard, smooth surface.

At room temperature grade 2 is an alpha alloy. It transforms to beta phase at 913 ±15°C, and the alpha phase returns on cooling 890 ±15°C.

Titanium is reactive, with a very high affinity for oxygen, which forms a skin of very stable and highly adherent oxide. The skin gives excellent corrosion resistance, despite the reactivity of the metal. The oxide layer forms spontaneously and rapidly on exposure to the atmosphere. However, when new parent metal is exposed to anhydrous conditions or in the absence of air, rapid corrosion may occur. Care should also be taken if titanium is to operate in contact with hydrogen, as hydrogen embrittlement from hydride formation can increase strength, with loss of ductility.

Availability

Austral Wright Metals can supply this alloy as plate, sheet and strip, rod and bar, seamless and welded pipe, weld fittings, seamless and welded tube, forging billet and forgings. It is widely used as tube in condensers and heat exchangers.

Pressure Vessels

AS1210 & ASME Boiler & Pressure Vessel Code pre-qualify titanium 2 for use in pressure vessels up to 300°C. AS4041 Pressure Piping qualifies the alloy to 325°C.

Corrosion Resistance

Titanium has excellent resistance to general corrosion, with low or negligible loss rates in many media. See Austral Wright Metals data sheet “Corrosion of Titanium and alloys” for more detail. The table at the end of this data sheet illustrates the excellent erosion corrosion performance of grade 2 in sea water.

Physical Properties

Density	Melting Range	Modulus of Elasticity (Tension)	Specific Heat	Mean Coefficient of Expansion	Thermal conductivity	Electrical Resistivity
kg/m ³	°C	GPa	J/kg. °C	x10 ⁻⁶ / °C	W / m. °C	micro-ohm.m
4,507	1668± 10	103	519	8.41	11.4	0.420

Erosion Corrosion Rates of Unalloyed Titanium, Grade 2

Location	Flow Rate m/sec	Type of Test	Test Duration months	Erosion Corrosion Rate mm/year
Brixham Sea	9.8	Model Condenser	12	0.003
Kure Beach, NC	1	Ducting	54	7.5 x 10 ⁻⁷
Kure Beach, NC	8.5	Rotating Disc	2	1.3 x 10 ⁻⁴
Kure Beach, NC	9	Micarta Wheel	2	2.8 x 10 ⁻⁴
Kure Beach, NC	7.2	Jet Impingement	1	5.0 x 10 ⁻⁴
Wrightsville Beach, NC	1.3	-	6	1.0 x 10 ⁻⁴
Wrightsville Beach, NC	9	Micarta Wheel	2	1.8 x 10 ⁻⁴
Mediterranean Sea	7.2	Jet Impingement	0.5	0.5mg/day
Dead Sea	7.2	Jet Impingement	0.5	0.5mg/day

Fabrication

Titanium grade 2 is forged by conventional processes within the narrow temperature range 815 – 900°C. Titanium and its alloys generally are more difficult to forge than both aluminium and alloy steels, due to the narrow temperature range, and high strain rate and temperature dependence of strength. Hot forging leaves a thick, extremely hard layer of titanium oxide on the surface, called “alpha case”. It is usually removed by pickling in a mixture of nitric and hydrofluoric acids. As supplied, titanium alloys are usually annealed, and can be readily cold formed in conventional machines using standard methods. When cold formed the alpha case does not form and pickling is not needed, except to remove embedded carbon steel pickup, which can cause pitting corrosion.

Machinability

Titanium grade 2 is readily machinable by conventional methods. It is similar to austenitic stainless steels for machinability. Like stainless steel, titanium has a low thermal conductivity and heat dissipation is poor, so generous use of coolant is recommended. Sharp tools are essential. Cuts should be deep and continuous, with low cutting speeds.

Weldability



Titanium grade 2 is readily weldable by GMAW and GTAW processes. Preheat or post weld heat treatment are not needed. The area immediately surrounding the welds must be CLEAN, free from all grease and shop dirt, including pencil marks. Abrasive cleaning can be used, or solvent cleaning or pickling with a mixture of nitric and hydrofluoric acids. A trailing gas shield must be applied to all areas above 450°C in addition to the normal welding torch gas shield, to prevent heavy oxidation during cooling. Matching filler metal to AWS ERTi-2 is used. The gas shield must be low in hydrogen, oxygen and nitrogen, all of which readily dissolve in titanium and cause embrittlement.

Heat Treatment

Titanium grade 7 is annealed at 650 – 760°C, still air cooled. Pickling to remove the alpha case may be needed before further fabrication or machining. Stress relief at 480 – 595°C, air cooled, may be required to improve dimensional stability for critical components.

Effects of Interstitial Elements

on the strength and ductility of unalloyed aluminium

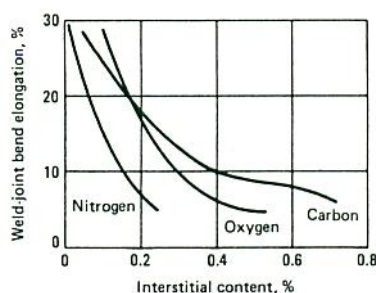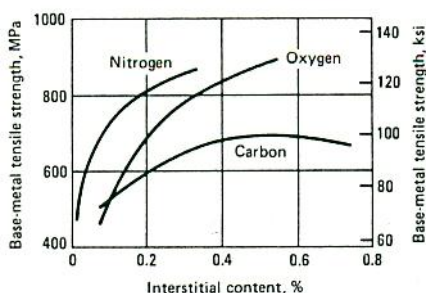

ASTM Product Specifications

Specification	Title
B265	Titanium and Titanium Alloy Strip, Sheet & Plate
B381	Titanium and Titanium Alloy Forgings
B348	Titanium and Titanium Alloy Bars and Billets
B337	Seamless and Welded Titanium and Titanium Alloy Pipe
B338	Seamless and Welded Titanium and Titanium Alloy Tubes for Condensers and Heat Exchangers
B363	Seamless and Welded Unalloyed Titanium and Titanium Alloy Welding Fittings
B367	Titanium and Titanium Alloy Castings

The technical advice and recommendations made in this Product Data Sheet should not be relied or acted upon without conducting your own further investigations, including corrosion exposure tests where needed. Please consult current editions of standards for design properties. Austral Wright Metals assumes no liability in connection with the information in this Product Data Sheet. Austral Wright Metals supplies a comprehensive range of stainless steels, copper alloys, nickel alloys and other high performance metals for challenging service conditions. Our engineers and metallurgists will be pleased to provide further data and applications advice.