



Standard Specification for High Conductivity Tough-Pitch Copper Refinery Shapes¹

This standard is issued under the fixed designation B5; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reappraisal. A superscript epsilon (ε) indicates an editorial change since the last revision or reappraisal.

This standard has been approved for use by agencies of the U.S. Department of Defense.

1. Scope*

1.1 This specification establishes the requirements for high conductivity, tough-pitch, copper wire bars, cakes, slabs, billets, ingots, and ingot bars.

1.2 Copper under this specification corresponds to the designations “ETP” (UNS C11000) and “FRHC” (UNS C11020) as shown in Classification **B224**. These coppers may also be used to produce coppers corresponding to the following:

Copper UNS No.	Classification B224 Designation
C11300, C11400, C11500, and C11600	STP
C12000	DLP
C12200	DHP
C12300	DHPS
C14520	DPTE

1.3 Although this specification includes certain UNS designations as described in Practice **E527**, these designations are for cross reference only and are not specification requirements. Therefore, in case of conflict, this ASTM specification shall govern.

1.4 *Units*—The values stated in inch-pound units are to be regarded as standard. The values given in parentheses are mathematical conversions to SI units that are provided for information only and are not considered standard.

1.4.1 *Exception*—Electrical resistivity is expressed in SI units.

2. Referenced Documents

2.1 *ASTM Standards*:²

B193 Test Method for Resistivity of Electrical Conductor Materials

B224 Classification of Coppers

¹ This specification is under the jurisdiction of ASTM Committee **B05** on Copper and Copper Alloys and is the direct responsibility of Subcommittee **B05.07** on Refined Copper.

Current edition approved April 1, 2011. Published May 2011. Originally approved in 1911. Last previous edition approved in 2005 as B5 – 00 (2005). DOI: 10.1520/B0005-11.

² For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

B846 Terminology for Copper and Copper Alloys

E29 Practice for Using Significant Digits in Test Data to Determine Conformance with Specifications

E53 Test Method for Determination of Copper in Unalloyed Copper by Gravimetry

E255 Practice for Sampling Copper and Copper Alloys for the Determination of Chemical Composition

E478 Test Methods for Chemical Analysis of Copper Alloys

E527 Practice for Numbering Metals and Alloys in the Unified Numbering System (UNS)

3. Terminology

3.1 For definitions of terms related to copper and copper alloys, refer to Terminology **B846**. For definitions of terms related to standard classification of coppers, refer to Classification **B224**.

4. Ordering Information

4.1 Include the following information, as applicable:

4.1.1 ASTM Specification Designation and year of issue,

4.1.2 Copper UNS No. Designation,

4.1.3 Quantity, shape, and dimension of each piece, and weight,

4.1.4 Should cakes, slabs, or billets be ordered for electrical use, it must be stated in the contract or purchase order, and

4.1.5 Silver content in silver-bearing shapes when required, in troy oz per short ton.

5. Chemical Composition

5.1 The copper in all shapes shall meet the minimum requirement for copper, including silver, of 99.90 %.

5.1.1 These composition limits do not preclude the presence of other elements. Limits for unnamed elements may be established, and analysis required, by agreement between the supplier and the purchaser.

5.2 For the STP (silver-bearing) coppers, the addition of silver up to an average of 30 troy oz per short ton (0.10 %) will be considered within the specification, with no individual silver analysis to exceed 35 troy oz per short ton (0.12 %).

6. Physical Property Requirements

6.1 *Electrical Resistivity*:

*A Summary of Changes section appears at the end of this standard

6.1.1 The maximum mass resistivity for wire bars, cakes, slabs, and billets for electrical use shall be $0.153\ 28\ \Omega\cdot\text{g}/\text{m}^2$ (conductivity 100.00 % minimum, International Annealed Copper Standard, (IACS)), at 68°F (20°C), annealed.

6.1.2 The maximum mass resistivity for other uses shall be $0.156\ 94\ \Omega\cdot\text{g}/\text{m}^2$ (conductivity 97.66 % minimum IACS), at 68°F (20°C), annealed.

6.1.3 The maximum mass resistivity for ingots and ingot bars shall be $0.156\ 94\ \Omega\cdot\text{g}/\text{m}^2$ (conductivity 97.66 % minimum IACS), at 68°F (20°C), annealed.

7. Dimensions, Mass, and Permissible Variations

7.1 Standard Sizes and Shapes of Wire Bars:

7.1.1 One size of mold shall be used for casting 200- to 230-lb (91- to 104-kg) wire bars, the bottom width of these bars to be $3\frac{1}{2}$ in. (89 mm), the listed weights being 200 and 225 lbs (91 to 102 kg) (Fig. 1).

7.1.2 One size of mold shall be used for casting 240- to 300-lb (109- to 136-kg) wire bars, the bottom width of these bars to be 4 in. (102 mm), the listed weights being 250, 265, 275, and 300 lbs (113, 120, 125, and 136 kg) (Fig. 2).

7.1.3 All bars shall be 54 in. (1.372 m) in length. The side draft or taper shall be $\frac{3}{8}$ in. (9.5 mm) in 4 in. ($\frac{3}{16}$ in. (4.8 mm) in 4 in. on each side of the bar). The radius of the corners at the bottom of the bars shall be $\frac{5}{8}$ in. (15.9 mm). The end taper at the bottom shall be 6 in. (152.4 mm) in overall length and


approximately 2 in. (50.8 mm)/ft (304.8 mm). The end taper of the side shall be approximately $2\frac{1}{4}$ in. (57.1 mm)/ft and the end of the bar shall be approximately $3\frac{3}{8}$ in. (85.7 mm) in depth at the point.

7.1.4 Wire bars not conforming to the requirements of Fig. 1 or Fig. 2, but otherwise meeting the requirements of this specification, may be supplied by agreement between manufacturer and the purchaser.

7.2 Permissible Variations in Weight and Dimensions—A permissible variation of $\pm 5\%$ in weight or $\pm \frac{1}{4}$ in. (6.3 mm) in any dimension from the manufacturer's published list or the purchaser's specified size shall be considered good delivery; provided, however, that wire bars may vary in length $\pm 1\%$ from the listed or specified length, and cakes may vary $\pm 3\%$ from the listed or specified size in any dimension greater than 8 in. (203.2 mm). The weight of copper in ingots and ingot bars shall not exceed that specified by more than 10 %, but otherwise its variation is not important.

8. Workmanship, Finish, and Appearance

8.1 Wire bars, cakes, slabs, and billets shall be substantially free of shrink holes, cold sets, pits, sloppy edges, concave tops, and similar defects in set or casting. This requirement shall not apply to ingots or ingot bars, in which physical defects are of no consequence.

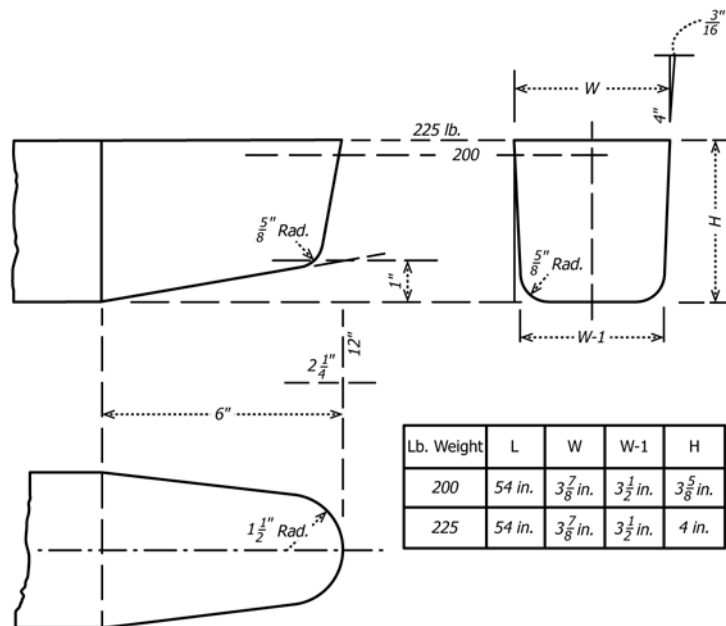

Inch-Pound Units	SI Units	Inch-Pound Units	SI Units
$\frac{3}{16}$ in.	4.763 mm	$\frac{3}{8}$ in.	9.5 mm
$\frac{5}{8}$ in.	15.875 mm	4 in.	102 mm
1 in.	25.4 mm	6 in.	152.4 mm
$1\frac{1}{2}$ in.	38.1 mm	12 in.	304.8 mm
$2\frac{1}{4}$ in.	57.15 mm	54 in.	1.372 m
$3\frac{1}{2}$ in.	89 mm	200 lbs	91 kg
$3\frac{5}{8}$ in.	92 mm	225 lbs	102 kg

FIG. 1 Copper Wire Bars, 200 and 225 lbs

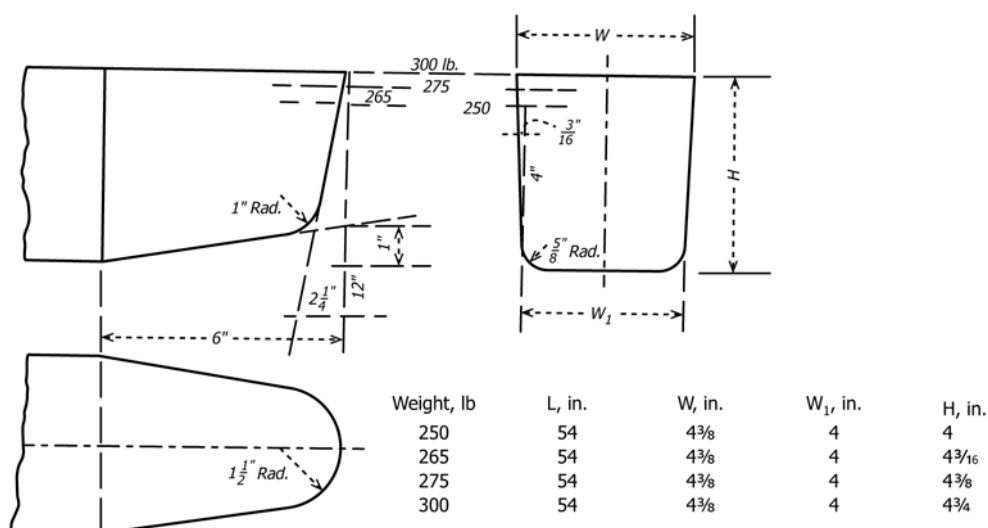


FIG. 2 Copper Wire Bars, 250, 265, 275, and 300 lbs

8.2 Blemishes of a nature that do not interfere with the intended application are acceptable.

9. Sampling

9.1 For routine sampling, the sampling practice shall be at the discretion of the sampler.

9.2 In case of dispute, a lot shall consist of all pieces the same shape and size bearing a common single identifying number.

9.3 *Chemical Composition*—In case of dispute concerning chemical composition, sampling shall be in accordance with Practice E255.

9.4 *Electrical Resistivity*—In case of dispute concerning the electrical resistivity, each party shall select two pieces from the lot. In the presence of both parties, and by means mutually agreeable, a single sample of adequate size shall be cut from each of the four pieces. See section 11.2 for subsequent specimen preparation.

10. Number of Tests and Retest

10.1 Tests:

10.1.1 *Chemical Analysis*—Chemical composition shall be determined as per the element mean of the results from at least three replicate analyses of the sample(s).

10.2 Other Tests:

10.2.1 *Electrical Resistivity*—The mass resistivity shall be determined as the mean of the observations from the test on the four wires.

10.3 *Retest*—In case of dispute, one retest may be made for chemical composition determined as the mean of the results from replicate analyses. In case of dispute concerning electrical resistivity, 9.4 and 11.2 shall apply.

10.4 Umpire Test:

10.4.1 In the case in which the retest does not settle the dispute, further retest may be made by a qualified third-party laboratory agreeable to the producer and the purchaser. The retest shall be made on the sample set aside for that purpose.

10.4.2 The umpire provision does not preclude other contractual agreements.

11. Specimen Preparation

11.1 *Chemical Analysis*—The analytical specimen preparation shall be the responsibility of the reporting laboratory.

11.2 Electrical Resistivity:

11.2.1 Each test sample for electrical resistivity shall be fabricated into a rod.

11.2.2 The external oxide shall be removed and the rod cold drawn into a wire approximately 0.080 in. (2.00 mm) in diameter.

11.2.3 Each wire coil shall be cut into four wires of approximately the same length, and the sixteen wires thus obtained shall be individually identified. The sixteen wires shall be divided into four groups of four wires each, one wire from each of the four originally selected pieces; one group each for the producer, the purchaser, contingencies, and the umpire.

11.2.4 The resulting specimen shall be annealed in an inert atmosphere at approximately 932°F (500°C) for 30 min and quickly cooled to ambient temperature in the same inert atmosphere.

12. Test Methods

12.1 The test method used for routine chemical analysis for specification compliance and preparation of certifications and test report, when required, shall be at the discretion of the reporting laboratory.

12.1.1 The test method(s) to be followed for determination of element(s) resulting from contractual or purchase-order agreement shall be as agreed upon between the supplier and purchaser.

12.2 In case of dispute concerning the minimum copper content, the method of analysis shall be in accordance with Test Method E53.

12.3 In case of dispute concerning silver content of silver-bearing shapes, the method of analysis shall be in accordance with Test Methods E478.

12.4 In case of dispute concerning the electrical resistivity, the method of test shall be in accordance with Test Method B193.

13. Significance of Numerical Limits

13.1 Calculated values shall be rounded to the specified number of places in accordance with Practice E29.

14. Inspection

14.1 The manufacturer or supplier shall inspect and make tests necessary to verify the product furnished conforms to specification requirements.

15. Rejection and Rehearing

15.1 Rejection:

15.1.1 Product that fails to conform to the specification requirements when tested by the purchaser or purchaser's agent shall be subject to rejection.

15.1.2 Rejection shall be considered as follows:

15.1.2.1 Chemical composition and electrical resistivity by lots. See section 9.2 for the definition of a lot as it pertains to this specification.

15.1.2.2 Physical defects by individual pieces.

15.1.2.3 Variations in weight or dimension by individual pieces.

15.1.3 Rejection shall be reported to the manufacturer or supplier promptly. In addition, a written notification of rejection shall follow.

15.1.4 In case of dissatisfaction with the results of the test upon which rejection is based, the manufacturer or supplier shall have the option to make claim for a rehearing.

15.2 *Rehearing*—As a result of product rejection, the manufacturer or supplier shall have the option to make claim for a retest to be conducted by the manufacturer, or supplier and the purchaser. Samples of the rejected product shall be taken in accordance with this specification, and subjected to test by both parties using the test method(s) specified, or alternately, upon agreement of both parties, an independent laboratory may be selected for the test(s) using the test method(s) specified in the product specification.

16. Product Marking

16.1 Each wire bar, cake, slab, and billet shall be stamped, or otherwise identified, with the producer's brand and lot.

16.2 Ingots and ingot bars shall have the producer's brand stamped, or cast in, but need have no other number.

17. Packaging and Package Marking

17.1 The manufacturer shall arrange rail-car loads, truck loads, or other shipping units so that, as far as possible, each shipping unit shall contain pieces bearing a single identifying lot number.

17.2 In case of dispute, a lot shall consist of all pieces of the same shape and size bearing the same identifying number.

18. Keywords

18.1 billets; cakes; electrolytic copper; electrorefined copper; electrowon copper; fire-refined copper; high-conductivity copper; ingots; ingot bars; refinery shapes; slabs; tough-pitch copper; wire bars

SUMMARY OF CHANGES

Committee B05 has identified the location of selected changes to this standard since the last issue (B5 – 00 (2005)) that may impact the use of this standard. (Approved April 1, 2011.)

(1) In section 1.2 C14500 has been changed to C14520, the correct designation for DPTE.

(2) In 6.1.1 100.0% minimum conductivity has been changed to 100.00%.

(3) In 11.2.2, 2 mm has been changed to 2.00 mm to be consistent with other specifications where this sample preparation is cited.

(4) Sections 3.1, 9.4, 10, 11, 12, and 15 have been modified to provide additional clarity.

ASTM International takes no position respecting the validity of any patent rights asserted in connection with any item mentioned in this standard. Users of this standard are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, are entirely their own responsibility.

This standard is subject to revision at any time by the responsible technical committee and must be reviewed every five years and if not revised, either reapproved or withdrawn. Your comments are invited either for revision of this standard or for additional standards and should be addressed to ASTM International Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee, which you may attend. If you feel that your comments have not received a fair hearing you should make your views known to the ASTM Committee on Standards, at the address shown below.

This standard is copyrighted by ASTM International, 100 Barr Harbor Drive, PO Box C700, West Conshohocken, PA 19428-2959, United States. Individual reprints (single or multiple copies) of this standard may be obtained by contacting ASTM at the above address or at 610-832-9585 (phone), 610-832-9555 (fax), or service@astm.org (e-mail); or through the ASTM website (www.astm.org). Permission rights to photocopy the standard may also be secured from the Copyright Clearance Center, 222 Rosewood Drive, Danvers, MA 01923, Tel: (978) 646-2600; <http://www.copyright.com/>