



Standard Test Method for Determination of Tap Density of Metallic Powders and Compounds¹

This standard is issued under the fixed designation B 527; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ε) indicates an editorial change since the last revision or reapproval.

1. Scope*

1.1 This test method specifies a method for the determination of tap density (packed density) of metallic powders and compounds, that is, the density of a powder that has been tapped, to settle contents, in a container under specified conditions.

1.2 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

2. Referenced Documents

2.1 *ASTM Standards:*²

B 215 Practices for Sampling Metal Powders

3. Significance and Use

3.1 This test method covers the evaluation of the tapped density physical characteristic of metallic powders and compounds. The degree of correlation between the results of this test method and the quality of powders in use will vary with each particular application and has not been fully determined.

4. Apparatus

4.1 *Balance*, of appropriate capacity and accuracy to satisfy the requirements shown in **Table 1**.

4.2 *Graduated Glass Cylinder*, calibrated to contain 100 cm³ at 20°C, the height of the graduated portion being approximately 175 mm. The graduations shall be at 1 cm³ intervals, thus allowing a measuring accuracy of ± 0.5 cm³. For apparent densities over 4 g/cm³, do not use the 100 cm³ cylinder.

4.2.1 Alternatively, the following may be used:

¹ This specification is under the jurisdiction of ASTM Committee B09 on Metal Powders and Metal Powder Products and is the direct responsibility of Subcommittee B09.03 on Refractory Metal Powders.

Current edition approved Oct. 1, 2006. Published October 2006. Originally approved in 1970. Last previous edition approved in 2000 as B 527 – 93 (2000)^{ε1}.

² For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

TABLE 1 Accuracy and Capacity of Balance

Cylinder Capacity, cm ³	Apparent Density, g/cm ³	Mass of Test Portion, g
100	>1	100 ± 0.5
100	≤1	50 ± 0.2
25	>7	100 ± 0.5
25	2 to 7	50 ± 0.2
25	<2	20 ± 0.1

4.2.1.1 *Graduated Glass Cylinder*, calibrated to contain 25 cm³ at 20°C, the height of the graduated portion being approximately 135 mm. The graduations shall be at 0.2 cm³ intervals.

4.2.1.2 A 25-cm³ cylinder shall be used for powders of apparent density higher than 4 g/cm³, in particular for refractory metal powders, but may also be used for powder of lower apparent density.

4.3 *Tapping Apparatus*, which permits the tapping of the graduated cylinder against a firm base. The tapping shall be such that a densification of the powder can take place without any loosening of its surface layers. The stroke shall be 3 mm (0.118 in.) and the tapping frequency shall be between 100 and 300 taps/min. An example of a tapping apparatus is shown in **Fig. 1**.

5. Test Specimen

5.1 For the quantities of powder required for each test, see **Table 1**. Obtain test powder samples according to Practices **B 215**.

5.2 In general, the powder should be tested in the as-received condition. In certain instances the powder may be dried. However, if the powder is susceptible to oxidation, the drying shall take place in a vacuum or in inert gas. If the powder contains volatile substances, it shall not be dried.

5.3 The test shall be carried out on three test samples, if possible.

6. Procedure

6.1 Clean the inside wall of the graduated cylinder (see **4.2**) with a suitable clean brush or, if necessary, by rinsing with a solvent, such as acetone. If a solvent is used, thoroughly dry the cylinder before reuse.

*A Summary of Changes section appears at the end of this standard.

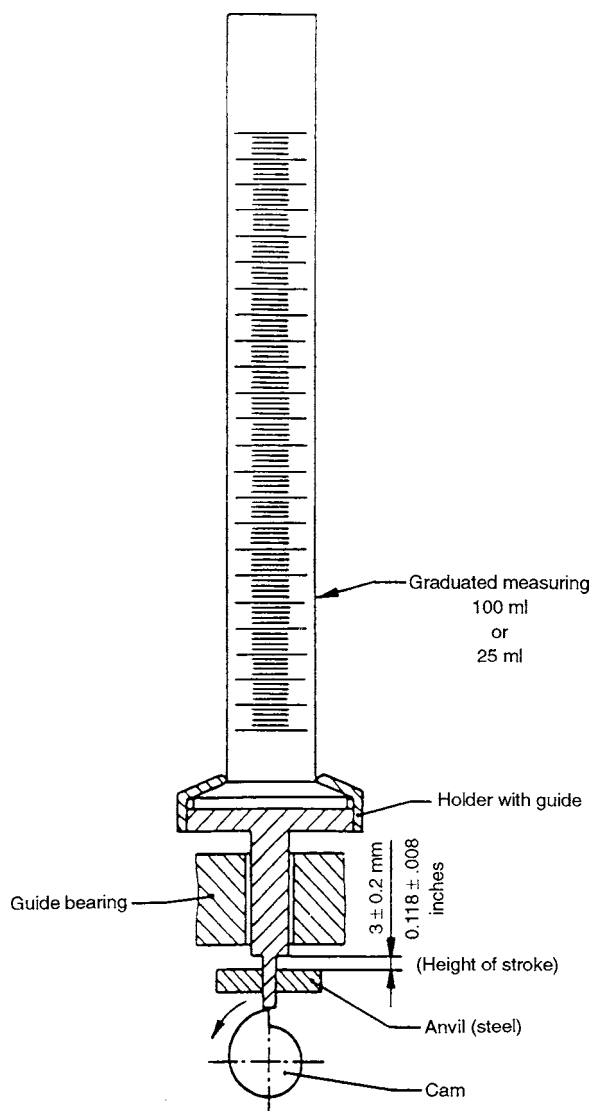


FIG. 1 Example of Tapping Apparatus

6.2 Weigh, to the nearest 0.1 g, the mass of the test portion as indicated in Table 1, using a balance (see 4.1).

6.3 Pour the test portion into the graduated cylinder. Take care that a level surface of the powder is formed. Place the cylinder in the tapping apparatus (see 4.3). Tap the cylinder until no further decrease in the volume of the powder takes place (see Note 1).

NOTE 1—In practice, the minimum number of taps, N , such that no further change in volume takes place would be determined. For all further tests on the same type of powder, the cylinder would be subjected to $2N$ taps, except where general experience and acceptance have established a specific number of taps (no less than N taps) as being satisfactory. For fine refractory metal powders, 3000 taps has been found to be satisfactory for all sizes.

6.4 If the tapped surface is level, read the volume directly. If the tapped surface is not level, determine the tap volume by calculating the mean value between the highest and the lowest reading of the tapped surface. Read the final volume to the nearest 0.5 cm^3 when using a 100 cm^3 cylinder and to the nearest 0.2 cm^3 when using a 25 cm^3 cylinder.

7. Calculation

7.1 The tap density is given in the following equation

$$P_t = \frac{M}{V} \quad (1)$$

where:

P_t = tap density, g/cm^3 ,

M = mass of powder, g, and

V = volume of tapped powder, cm^3 .

8. Report

8.1 Report the following information:

8.1.1 Reference to this test method,

8.1.2 All details necessary for identification of the test sample,

8.1.3 The drying procedure, if the powder has been dried,

8.1.4 Cylinder capacity, mass of test portion and method used,

8.1.5 All results obtained,

8.1.6 All operations not specified in this test method or regarded as optional,

8.1.7 Details of any occurrence that may have affected the result.

9. Precision and Bias

9.1 *Precision*—It is not possible at present to specify the precision and bias of the procedure in Test Method B 527 for measuring the tap density of metal powders and compounds. An interlaboratory study is currently in process.

10. Keywords

10.1 apparent density; bulk density; density; density ratio; metal powders; packed density; powder metallurgy; tap density



SUMMARY OF CHANGES

Committee B09 has identified the location of selected changes to this standard since the last issue (B 527 – 93 (2000)^{e1}) that may impact the use of this standard. (Approved Oct. 1, 2006.)

- | | |
|--|---|
| <p>(1) Edit changes were made throughout.</p> <p>(2) Removed references to equipment suppliers because the equipment is available from more than one source.</p> <p>(3) In 5.3, added “if possible” since often there is not a sufficient quantity of powder available for three independent</p> | <p>tests without reusing the materials.</p> <p>(4) In 8.1.5, changed “the” to “all”.</p> <p>(5) In Section 9, replaced precision and bias statement with standard statement from the <i>ASTM Form and Style Manual</i>.</p> <p>(6) In Table 1, changed “<1” to “≤1”.</p> |
|--|---|

ASTM International takes no position respecting the validity of any patent rights asserted in connection with any item mentioned in this standard. Users of this standard are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, are entirely their own responsibility.

This standard is subject to revision at any time by the responsible technical committee and must be reviewed every five years and if not revised, either reapproved or withdrawn. Your comments are invited either for revision of this standard or for additional standards and should be addressed to ASTM International Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee, which you may attend. If you feel that your comments have not received a fair hearing you should make your views known to the ASTM Committee on Standards, at the address shown below.

This standard is copyrighted by ASTM International, 100 Barr Harbor Drive, PO Box C700, West Conshohocken, PA 19428-2959, United States. Individual reprints (single or multiple copies) of this standard may be obtained by contacting ASTM at the above address or at 610-832-9585 (phone), 610-832-9555 (fax), or service@astm.org (e-mail); or through the ASTM website (www.astm.org).