



Standard Test Method for Density of Hydraulic Cement¹

This standard is issued under the fixed designation C188; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

This standard has been approved for use by agencies of the U.S. Department of Defense.

1. Scope*

1.1 This test method covers the determination of the density of hydraulic cement. Its particular usefulness is in connection with the design and control of concrete mixtures.

1.2 The density of hydraulic cement is defined as the mass of a unit volume of the solids.

1.3 The values stated in SI units are to be regarded as standard. No other units of measurement are included in this standard.

1.4 **Warning**—Fresh hydraulic cementitious mixtures are caustic and may cause chemical burns to skin and tissue upon prolonged exposure.²

1.5 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

2. Referenced Documents

2.1 *ASTM Standards*:³

C114 Test Methods for Chemical Analysis of Hydraulic Cement

C125 Terminology Relating to Concrete and Concrete Aggregates

C670 Practice for Preparing Precision and Bias Statements for Test Methods for Construction Materials

3. Terminology

3.1 **Definitions**—For definitions of terms used in this test method, refer to Terminology **C125**.

¹ This test method is under the jurisdiction of ASTM Committee **C01** on Cement and is the direct responsibility of Subcommittee **C01.25** on Fineness.

Current edition approved July 1, 2014. Published July 2014. Originally approved in 1944. Last previous edition approved in 2009 as C188 – 09. DOI: 10.1520/C0188-14.

² Section on Safety, Manual of Cement Testing, *Annual Book of ASTM Standards*, Vol. 04.01.

³ For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

4. Significance and Use

4.1 This test method provides a procedure for the determination of density of hydraulic cement samples using non-instrumental techniques.

5. Apparatus

5.1 *Le Chatelier flask*—The standard flask, which is circular in cross section, with shape and dimensions conforming essentially to **Fig. 1** (Note). The requirements in regard to tolerance, inscription and length, spacing, and uniformity of graduation will be rigidly observed. There shall be a space of at least 10 mm between the highest graduation mark and the lowest point of grinding for the glass stopper.

5.1.1 The material of construction shall be excellent quality glass, transparent and free of striae. The glass shall be chemically resistant and shall have small thermal hysteresis. The flasks shall be thoroughly annealed before being graduated. They shall be of sufficient thickness to ensure reasonable resistance to breakage.

5.1.2 The neck shall be graduated from 0 to 1 mL and from 18 to 24 mL in 0.1-mL graduations. The error of any indicated capacity shall not be greater than 0.05 mL.


5.1.3 Each flask shall bear a permanent identification number and the stopper, if not interchangeably ground, shall bear the same number. Interchangeable ground-glass parts shall be marked on both members with the standard-taper symbol, followed by the size designation. The standard temperature shall be indicated, and the unit of capacity shall be shown by the letters “mL” placed above the highest graduation mark.

5.2 Kerosine, free of water, or naphtha, having a density greater than 0.73 g/mL at 23 ± 2 °C shall be used in the density determination.

5.3 The use of alternative equipment or methods for determining density is permitted provided that a single operator can obtain results within ± 0.03 g/cm³ of the results obtained using the flask method.

NOTE 1—The design is intended to ensure complete drainage of the flask when emptied, and stability of standing on a level surface, as well as accuracy and precision of reading.

*A Summary of Changes section appears at the end of this standard

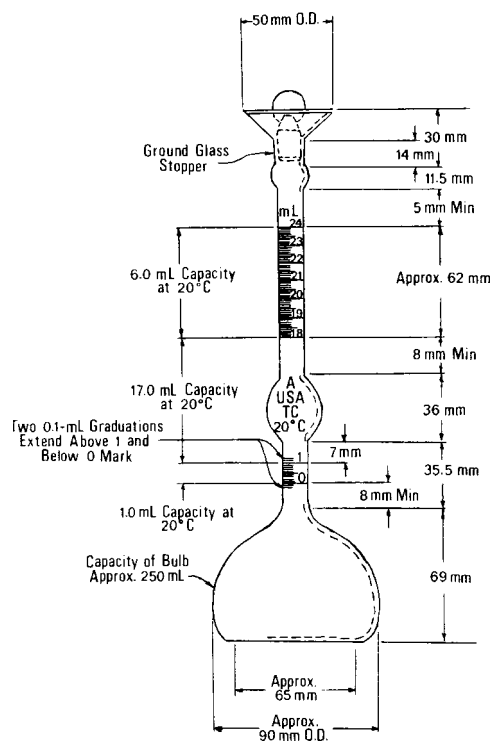

Note—Variations of a few millimeters in such dimensions as total height of flask, diameter of base, and so forth, are to be expected and will not be considered sufficient cause for rejection. The dimensions of the flask shown in Fig. 1 apply only to new flasks and not to flasks in use which meet the other requirements of this test method.

FIG. 1 Le Chatelier Flask for Density Test

6. Procedure

6.1 Determine the density of cement on the material as received, unless otherwise specified. If the density determination on a loss-free sample is required, first ignite the sample as described in the loss on ignition section on Portland Cement of Test Methods C114.

6.2 Fill the flask (Note 2) with either of the liquids specified in 5.2 to a point on the stem between the 0 and the 1-mL mark. Dry the inside of the flask above the level of the liquid, if necessary, after pouring. Record the first reading after the flask has been immersed in the water bath (Note 3) in accordance with 6.4.

NOTE 2—It is advisable to use a rubber pad on the table top when filling or rolling the flask.

NOTE 3—Before the cement has been added to the flask, a loose-fitting, lead-ring weight around the stem of the flask will be helpful in holding the flask in an upright position in the water bath, or the flask may be held in the water bath by a buret clamp.

6.3 Introduce a quantity of cement, weighed to the nearest 0.05 g, (about 64 g for portland cement) in small increments at the same temperature as the liquid (Note 2). Take care to avoid splashing and see that the cement does not adhere to the inside of the flask above the liquid. A vibrating apparatus may be used to accelerate the introduction of the cement into the flask and to prevent the cement from sticking to the neck. After all the

cement has been introduced, place the stopper in the flask and roll the flask in an inclined position (Note 2), or gently whirl it in a horizontal circle, so as to free entrapped air from the liquid. If a proper amount of cement has been added, the level of the liquid will be in its final position at some point of the upper series of graduations. Take the final reading after the flask has been immersed in the water bath in accordance with 6.4.

6.4 Immerse the flask in a constant-temperature water bath for sufficient periods of time in order to avoid flask temperature variations greater than 0.2 °C between the initial and the final readings.

7. Calculation

7.1 The difference between the first and the final readings represents the volume of liquid displaced by the mass of cement used in the test.

7.2 Calculate the cement density, ρ , as follows:

$$\rho = M/V$$

where:

ρ = density of cement, g/cm³,

M = mass of cement, g, and

V = displaced volume of liquid, cm³.

NOTE 4—The displaced volume in millilitres is numerically equal to the displaced volume in cubic centimetres.

NOTE 5—Calculate the cement density, ρ , to three decimal places and round to the nearest 0.01 g/cm³.

NOTE 6—In connection with proportioning and control of concrete mixtures, density may be more usefully expressed as specific gravity, the latter being a dimensionless number. Calculate the specific gravity (sp gr) as follows:

$$\text{sp gr} = \text{cement density/water density at } 4^\circ\text{C}$$

where the density of water at 4 °C is 1 g/cm³.

8. Precision and Bias

8.1 The single-operator standard deviation for portland cements has been found to be 0.012.⁴ Therefore, the results of two properly conducted tests by the same operator on the same material should not differ by more than 0.03.

8.2 The multilaboratory standard deviation for portland cements has been found to be 0.037.⁴ Therefore, the results of two properly conducted tests from two different laboratories on samples of the same cement should not differ by more than 0.10.⁴

8.3 Since there is no accepted reference material suitable for determining any bias that might be associated with this test method, no statement on bias is being made.

9. Keywords

9.1 density; hydraulic cement; specific gravity

⁴ These numbers represent the 1s and d2s limits described in Practice C670.



SUMMARY OF CHANGES

Committee C01 has identified the location of selected changes to this standard since the last issue (C188–09) that may impact the use of this standard. (Approved July 1, 2014.)

(1) Added 1.5, Sections 3 and 4.

(2) Revised 5.3, 7.2, and Note 6.

ASTM International takes no position respecting the validity of any patent rights asserted in connection with any item mentioned in this standard. Users of this standard are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, are entirely their own responsibility.

This standard is subject to revision at any time by the responsible technical committee and must be reviewed every five years and if not revised, either reapproved or withdrawn. Your comments are invited either for revision of this standard or for additional standards and should be addressed to ASTM International Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee, which you may attend. If you feel that your comments have not received a fair hearing you should make your views known to the ASTM Committee on Standards, at the address shown below.

This standard is copyrighted by ASTM International, 100 Barr Harbor Drive, PO Box C700, West Conshohocken, PA 19428-2959, United States. Individual reprints (single or multiple copies) of this standard may be obtained by contacting ASTM at the above address or at 610-832-9585 (phone), 610-832-9555 (fax), or service@astm.org (e-mail); or through the ASTM website (www.astm.org). Permission rights to photocopy the standard may also be secured from the Copyright Clearance Center, 222 Rosewood Drive, Danvers, MA 01923, Tel: (978) 646-2600; <http://www.copyright.com/>