



Standard Practice for Calculating Thermal Endurance of Materials from Thermogravimetric Decomposition Data¹

This standard is issued under the fixed designation E1877; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

1. Scope

1.1 This practice covers additional treatment of the Arrhenius activation energy data determined by Test Method E1641 to develop a thermal endurance curve and derive a relative thermal index for materials.

1.2 This practice is generally applicable to materials with a well-defined decomposition profile, namely a smooth, continuous mass change with a single maximum rate.

1.3 The values stated in SI units are to be regarded as standard. No other units of measurement are included in this standard.

1.4 There is no ISO standard equivalent to this practice.

1.5 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

2. Referenced Documents

2.1 *ASTM Standards:*²

E1641 Test Method for Decomposition Kinetics by Thermogravimetry

3. Terminology

3.1 *Definitions of Terms Specific to This Standard:*

3.1.1 *failure, n*—change in some chemical, physical, mechanical, electrical or other property of sufficient magnitude to make it unsuitable for a particular use.

3.1.2 *failure temperature (T_f), n*—the temperature at which a material fails after a selected time.

3.1.3 *relative thermal index (RTI), n*—a measure of the thermal endurance of a material when compared with that of a control with proven thermal endurance characteristics.

¹ This practice is under the jurisdiction of Committee E37 on Thermal Measurements and is the direct responsibility of Subcommittee E37.10 on Fundamental, Statistical and Mechanical Properties.

Current edition approved Aug. 1, 2011. Published September 2011. Originally approved in 1997. Last previous edition approved in 2010 as E1877 – 00 (2010). DOI: 10.1520/E1877-11.

² For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

3.1.3.1 *Discussion*—The RTI is also considered to be the maximum temperature below which the material resists changes in its properties over a defined period of time. In the absence of comparison data for a control material, a time-to-failure of 60 000 h has been arbitrarily selected for measuring RTI. The RTI is therefore, the failure temperature, T_f , obtained from the thermal endurance curve.

4. Summary of Practice

4.1 The Arrhenius activation energy obtained from Test Method E1641 is used to construct the thermal endurance curve of a material from which an estimate of lifetime at certain temperatures may be obtained.

5. Significance and Use

5.1 Thermogravimetry provides a rapid method for the determination of the temperature-decomposition profile of a material.

5.2 This practice is useful for quality control, specification acceptance, and research.

5.3 This practice shall not be used for product lifetime predictions unless a correlation between test results and actual lifetime has been demonstrated. In many cases, multiple mechanisms occur during the decomposition of a material, with one mechanism dominating over one temperature range, and a different mechanism dominating in a different temperature range. Users of this practice are cautioned to demonstrate for their system that any temperature extrapolations are technically sound.

6. Calculation

6.1 The following values obtained by Test Method E1641 are used to calculate thermal endurance, estimated thermal life and failure temperature.

6.1.1 The following definitions apply to 6.1 and 6.3:

6.1.1.1 E = Arrhenius activation energy (J/mol),

6.1.1.2 R = Universal gas constant (= 8.314 510 J/(mol K)),

6.1.1.3 β = Heating rate (K/min),

6.1.1.4 β' = Heating rate nearest the mid-point of the experimental heating rates (K/min),

6.1.1.5 a = Approximation integral taken from Table 1,

6.1.1.6 α = Constant conversion value,

TABLE 1 Numerical Integration Constants

E/RT	a
8	5.3699
9	5.8980
10	6.4157
11	6.9276
12	7.4327
13	7.9323
14	8.4273
15	8.9182
16	9.4056
17	9.8900
18	10.3716
19	10.8507
20	11.3277
21	11.8026
22	12.2757
23	12.7471
24	13.2170
25	13.6855
26	14.1527
27	14.6187
28	15.0836
29	15.5474
30	16.0103
31	16.4722
32	16.9333
33	17.3936
34	17.8532
35	18.3120
36	18.7701
37	19.2276
38	19.6845
39	20.1408
40	20.5966
41	21.0519
42	21.5066
43	21.9609
44	22.4148
45	22.8682
46	23.3212
47	23.7738
48	24.2260
49	24.6779
50	25.1294
51	25.5806
52	26.0314
53	26.4820
54	26.9323
55	27.3823
56	27.8319
57	28.2814
58	28.7305
59	29.1794
60	29.6281

6.1.1.7 t_f = Estimated thermal life for a given value of conversion (α) (min) (see Test Method E1641),

6.1.1.8 T_c = Temperature for the point of constant conversion for β (K), and

6.1.1.9 T_f = Failure Temperature for a give value of conversion (α) (K) (see Test Method E1641).

NOTE 1—The precision of the calculation in this practice are exponentially dependent on the uncertainty of activation energy value used. Care should be taken to use only the most precise values of E .

6.2 Use Eq 1 or Eq 2³ and trial values of T_f to plot the logarithm of estimated thermal life (t_f) versus reciprocal of T_f as, by example, shown in Fig. 1.

³ Krizanovsky, L., and Mentlik, V., *Journal of Thermal Analysis*, Vol 13, 1978.

$$\log t_f = E / (2.303 R T_f) + \log [E / (R \beta)] - a \quad (1)$$

$$T_f = E / (2.303 R [\log t_f - \log \{E / (R \beta)\} + a]) \quad (2)$$

6.2.1 To calculate t_f , select the value for the temperature at the constant conversion point (T_c) for a heating rate (β) nearest the mid-point of the experimental heating rates. Use this value, along with the Arrhenius activation energy (E) to calculate the quantity $E/(R T_c)$ to select the value in Table 1.^{4, 5, 6} Arbitrarily select a number of temperatures in the region of the chosen percent mass loss, indicative of failure, in the mass change curve at the midpoint heating rate. Calculate the logarithm of the thermal life from Eq 1. Plot the thermal endurance curve, as shown in Fig. 1, with thermal life on the ordinate and reciprocal of absolute temperature on the abscissa.

NOTE 2—The values for E and β may be obtained by the procedure described in Test Method E1641.

6.3 The thermal endurance of two or more materials may be compared by calculating the RTI for each material. To compute RTI for each material; select some common thermal life for comparison, a typical value may be 60 000 h (6.8 years), insert that value (in minutes) and the appropriate activation energy for each material into Eq 2 to obtain T_f . This value of temperature is called the “relative thermal index (RTI) at the specified time”. Materials with greater resistance to thermal decomposition will have a larger RTI.

7. Report

7.1 Report the following information:

7.1.1 If data other than that generated by Test Method E1641 is used in these calculations, then include a description of the data source in the report,

7.1.2 Designation of the material under test, including the name of the manufacturer, the lot number, and supposed chemical composition when known, and

7.1.3 The calculated thermal life (t_f) and RTI values.

7.1.4 The specific dated version of this practice that is used.

8. Precision and Bias⁷

8.1 The precision and bias of these calculations depend on the precision and bias of the kinetic data used in them. To provide an example of the precision expected, thermal life was calculated by the procedure in this practice using data for poly(tetrafluoroethylene) from the interlaboratory study conducted to develop the precision and bias statement for Test Method E1641. Extreme values of thermal life were calculated using an arbitrarily chosen value for temperature of 600 K and the extreme values of E corresponding to the 95 % confidence level from that interlaboratory study. The resulting calculated extreme values were 9 years and 3700 years for this material.

⁴ Flynn, J.H., and Wall, L.A., *Polymer Letters*, Vol 4, 1966 pp. 323–328.

⁵ Flynn, J.H., *Journal of Thermal Analysis*, Vol 27, 1983, pp. 95–102.

⁶ Toop, D.J., *IEEE Transactions on Electrical Insulation*, Vol EI-6, 1971, pp. 2–12.

⁷ Supporting data have been filed at ASTM International Headquarters and may be obtained by requesting Research Report RR:E37-1024.

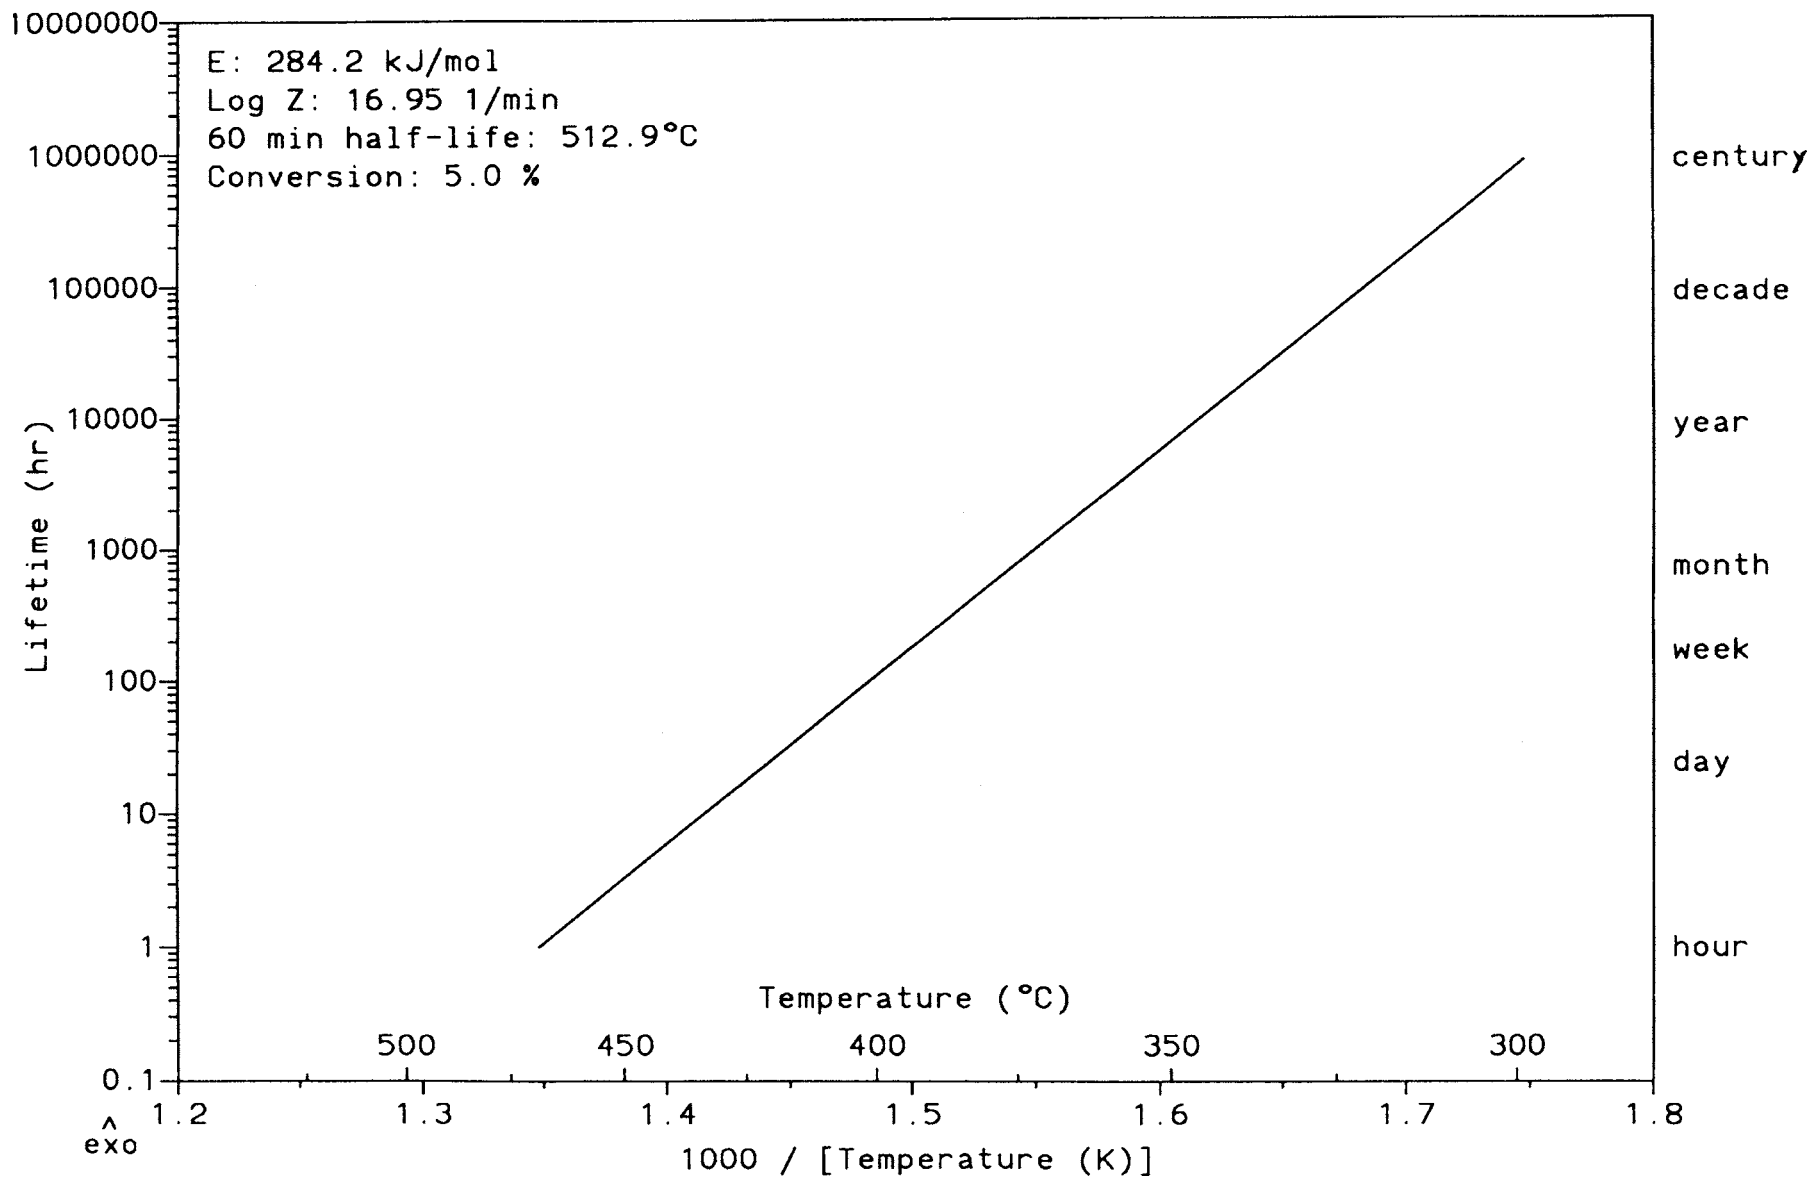


FIG. 1 Thermal Endurance Curve

9. Keywords

9.1 Arrhenius activation energy; Arrhenius pre-exponential factor; kinetic parameters; relative thermal index; thermal decomposition; thermal endurance; thermal life; thermogravimetric analysis

ASTM International takes no position respecting the validity of any patent rights asserted in connection with any item mentioned in this standard. Users of this standard are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, are entirely their own responsibility.

This standard is subject to revision at any time by the responsible technical committee and must be reviewed every five years and if not revised, either reapproved or withdrawn. Your comments are invited either for revision of this standard or for additional standards and should be addressed to ASTM International Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee, which you may attend. If you feel that your comments have not received a fair hearing you should make your views known to the ASTM Committee on Standards, at the address shown below.

This standard is copyrighted by ASTM International, 100 Barr Harbor Drive, PO Box C700, West Conshohocken, PA 19428-2959, United States. Individual reprints (single or multiple copies) of this standard may be obtained by contacting ASTM at the above address or at 610-832-9585 (phone), 610-832-9555 (fax), or service@astm.org (e-mail); or through the ASTM website (www.astm.org). Permission rights to photocopy the standard may also be secured from the ASTM website (www.astm.org/COPYRIGHT/).