



Standard Test Method for Determining Forming Limit Curves¹

This standard is issued under the fixed designation E 2218; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

1. Scope

1.1 This method gives the procedure for constructing a forming limit curve (FLC) for a metallic sheet material by using a hemispherical deformation punch test and a uniaxial tension test to quantitatively simulate biaxial stretch and deep drawing processes.

1.2 FLCs are useful in evaluating press performance by metal fabrication strain analysis.

1.3 The method applies to metallic sheet from 0.5 mm (0.020 in.) to 3.3 mm (0.130 in.).

1.4 The values stated in SI units are to be regarded as the standard. The inch-pound equivalents are approximate.

1.5 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

2. Referenced Documents

2.1 ASTM Standards:²

A 568/A 568M Specification for Steel, Sheet, Carbon, Structural, and High-Strength, Low-Alloy, Hot-Rolled and Cold-Rolled, General Requirements for

E 6 Terminology Relating to Methods of Mechanical Testing

E 8/E 8M Test Methods for Tension Testing of Metallic Materials

E 517 Test Method for Plastic Strain Ratio r for Sheet Metal

E 646 Test Method for Tensile Strain-Hardening Exponents (n -Values) of Metallic Sheet Materials

3. Terminology

3.1 Terminology **E 6** shall apply as well as the following special terms used in this method.

3.2 *forming limit diagram (FLD)*—a graph on which the measured major (e_1) and associated minor (e_2) strain combinations are plotted to develop a forming limit curve. See **Fig. 1**.

3.2.1 *Discussion*—The graduated scales on the FLD shall be in percent strain, calculated from the initial gage length.

3.2.2 *Discussion*—The distance between FLD percentage increments shall be the same for both the major strain (e_1) ordinate (parallel to the vertical y axis) and minor strain (e_2) abscissa (parallel to the horizontal x axis) unless the difference is noted in the report.

3.3 *forming limit curve (FLC)*—an empirically derived curve showing the biaxial strain levels beyond which localized through-thickness thinning (necking) and subsequent failure occur during the forming of a metallic sheet. See **Fig. 2**.

3.3.1 *Discussion*—The curve of **Fig. 2** is considered the forming limit for the material when the metal is subjected to a stamping press operation. It was obtained for a drawing quality aluminum killed steel sheet. The curve of **Fig. 2** correlates with the upper curve of **Fig. 1**, a generic curve representing a metallic sheet material with a FLD_0 of 40 %.

3.3.2 *Discussion*—The strains are given in terms of percent major and minor strain measured after forming a series of test specimen blanks by using a grid pattern. The gage lengths before and after forming the part are measured to obtain the percent strain. The curve for negative (e_2) strains will generally follow a constant surface area relationship to the associated (e_1) strain.

3.3.3 *Discussion*—The range of possible major strain (e_1) is from 0 % to over 200 %. The range of possible minor strain (e_2) is from –40 % to over +60 %, or even greater strain levels.


3.3.4 *Discussion*—For convenience, the forming limit curve (FLC) can be plotted on a reduced range of the forming limit diagram (FLD), for example, from +20 % to +80 % major (e_1) strains and from –20 % to +30 % minor (e_2) strain. If the lowest (e_1) strain increment of the FLD is not 0 % e_1 , that value shall be noted in the report.

3.4 *grid pattern*—a pattern applied to the surface of a metal sheet to provide an array of precisely spaced gage points prior to forming the metal into a final shape by the application of a force.

¹ This method is under the jurisdiction of ASTM Committee E28 on Mechanical Testing and is the direct responsibility of Subcommittee E28.02 on Ductility and Formability.

Current edition approved May 1, 2008. Published October 2008. Originally published in 2002. Last previous edition approved in 2002 as E2218–02.

² For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

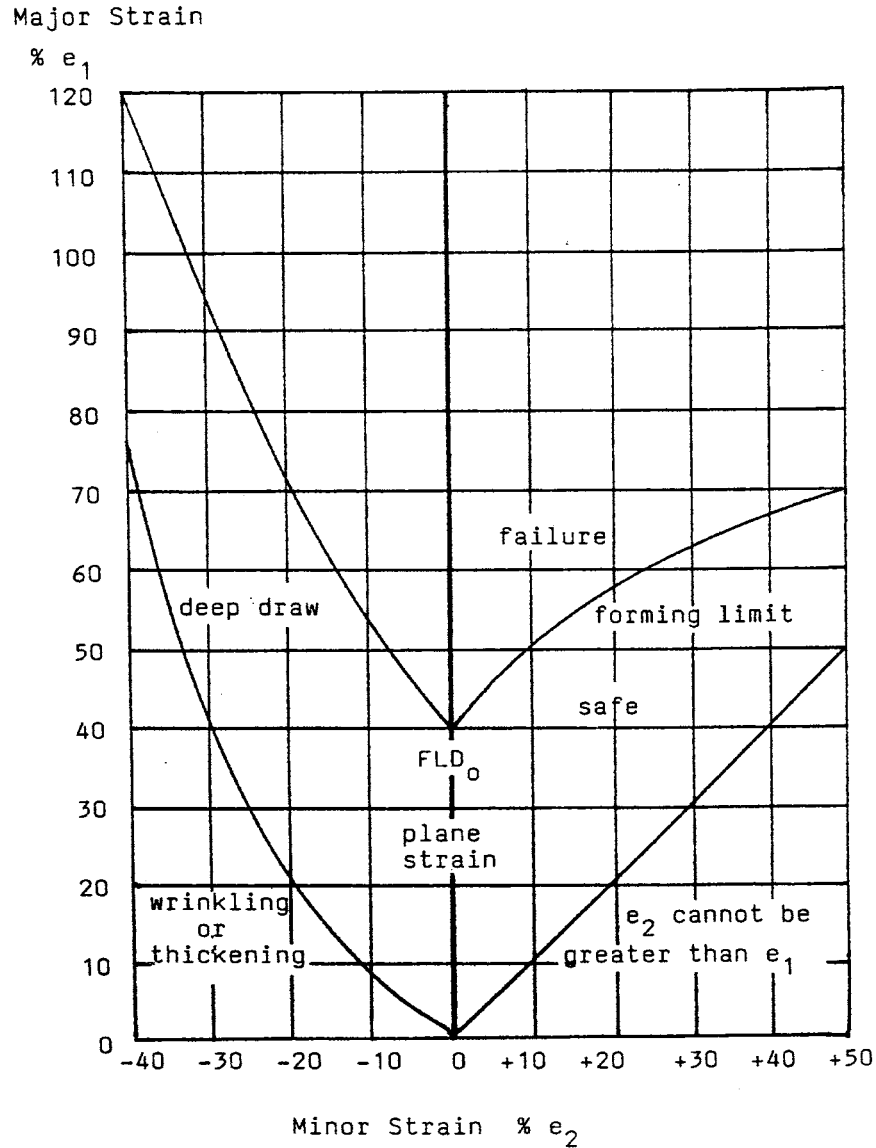

NOTE—The upper curve is representative of the forming limit. Strains below the lower curve do not occur during forming metallic sheet products in the most stamping press operations. Curves to the left of $\% e_2 = 0$ are for constant area of the sheet surface.


FIG. 1 Forming Limit Diagram

3.4.1 *Discussion*—An array of squares, or circles, or both, is printed on the surface of the specimen. Suggested patterns are shown in Fig. 3. The pattern shall adhere to the metal so that it will not be moved on the surface or rubbed off by the forming operation. Refer to Specification A 568/A 568M, Appendix X4—Procedures for Determining the Extent of Plastic Deformation Encountered in Forming or Drawing, for procedures to apply photographic and electrochemically printed grid patterns and a review of strain analysis.

3.4.2 *Discussion*—Suggested dimensions for the gage lengths are 2.5 mm (0.100 in.) for the sides of a square pattern,

or diameter of a circle pattern. After the part has been formed, critical areas are measured for the resulting gage length changes in the long dimension from (L_o) to (L_f) of the pattern, and in the width dimension (W_o) to (W_f) at 90° to the long dimension as shown in Fig. 4. The major strain (e_1) and associated minor strain (e_2) at 90° to (e_1) are calculated from these gage length changes. The strains can be either engineering strain based on the original gage length, or true strain.

Major Strain

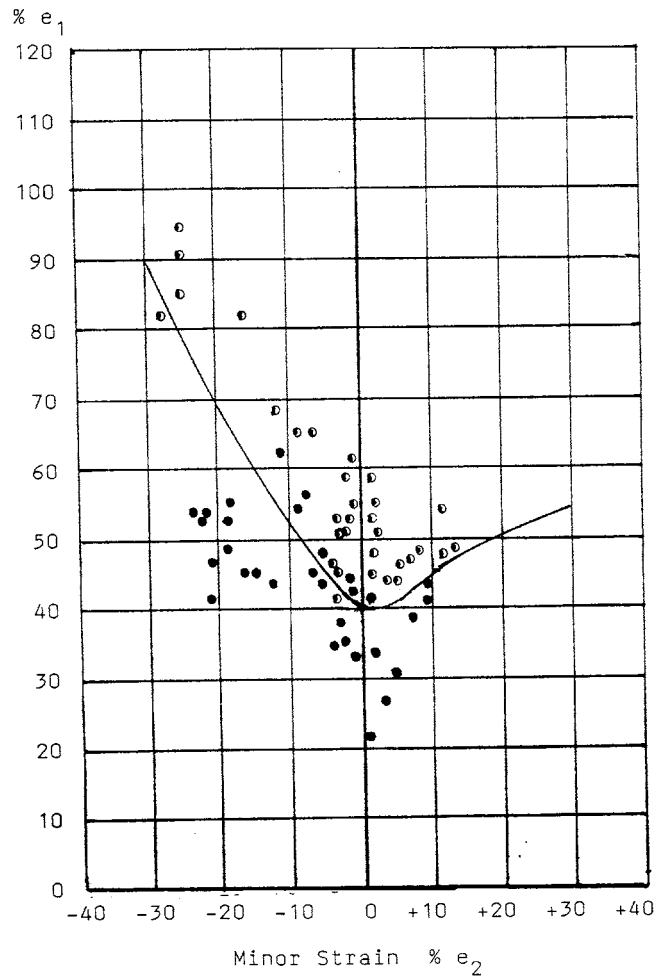

Code: ● good ○ Marginal (necked)

Material properties:


Thickness 0.866 mm (0.034 in.)
Strain hardening (n) 0.230
Plastic Strain (r) 1.710

Cold Rolled Drawing Quality Aluminum Killed Steel
Longitudinal Mechanical Properties

Thickness		Yield Strength		Tensile Strength		% El in 50 mm	n Value	r Value
mm	(in.)	MPa	(ksi)	MPa	(ksi)			
0.866	(0.034)	163.4	(23.7)	304.7	(44.2)	43.5	0.230	1.71

Chemical Composition							
Element Percent	C	S	N	Mn	Al	P	Si
	0.035	0.006	0.006	0.19	0.29	0.006	0.004

FIG. 2 Forming Limit Curve (FLC) for a Cold Rolled Drawing Quality Aluminum Killed Steel Sheet.

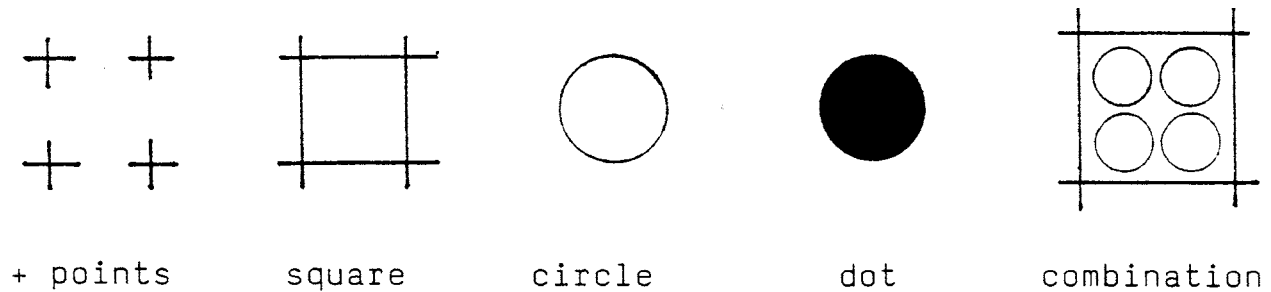

NOTE—The basic pattern is repeated over the area of the part to be studied on a flat specimen blank.

FIG. 3 Examples of patterns for Gage Length measurement units used in Determining Forming Limit Curves (FLC)

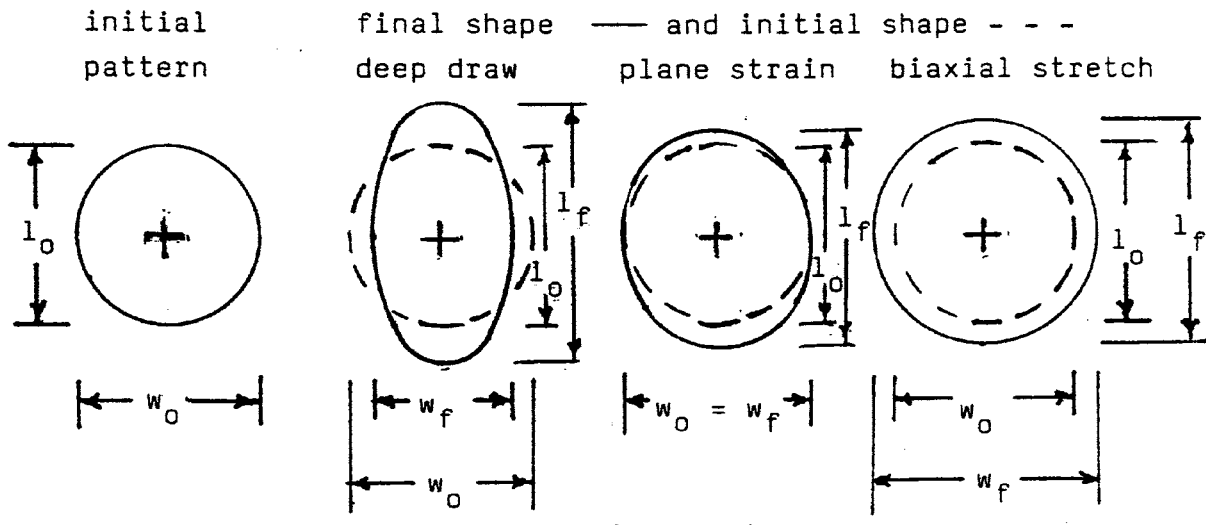


FIG. 4 Possible Changes in Shape of the Grid Pattern Caused by Forming Operations on Metallic Sheet Products

3.4.3 *Discussion*—Larger patterns, of 6 mm (0.25 in.) up to 125 mm (5 in.), can be used to measure low strain levels on formed parts, but are not used in determining the FLC.

3.4.4 *Discussion*—Circles are suggested for deformations where the major strain (e_1) does not align with the lines of a square pattern. This condition is less likely in the process of determining the FLC than in production stamping evaluations. These circles commonly have diameters of 2.5 mm (0.100 in.) and can be spaced up to 2.5 mm (0.100 in.) apart. They are measured across the diameter of the circle when the line width is minimal. For wider lines, the enclosed area of the etched circle should be consistent from one circle to another and the measurement made across the inside diameter. This is more critical with wider line width patterns and at high e_1 strains when the line spreads as the metal surface stretches.

3.4.5 *Discussion*—An alternate to circles is a pattern of solid dots of precise diameter, which are measured across the diameter of the dot.

3.5 *deep drawing*—a metal sheet forming operation in which strains on the sheet surface are positive in the direction of the punch travel (e_1) and negative at 90° to that direction. See Fig. 4.

3.5.1 *Discussion*—Deep drawing occurs in the walls of a drawn cylinder or the corner walls of a deep drawn part when the flange clamping force is sufficient to restrain metal movement and wrinkling, while permitting the punch to push the center area of the blank into the cavity of the die. Strain conditions that can cause wrinkling or thickening are shown in Fig. 1.

3.5.2 *Discussion*—In forming a square pan shape, metal from an area of the flange under a reduced clamping force is pulled into the die to form the side wall of the part.

3.6 *major strain*—the largest strain (e_1) developed at a given location in the sheet specimen surface.

3.6.1 *Discussion*—The major strain (e_1) is measured along the stretched line of a square pattern, or along the major axis of the ellipse resulting from deformation of a circular grid pattern.

3.7 *minor strain*—the strain (e_2) in the sheet surface in a direction perpendicular to the major strain.

3.7.1 *Discussion*—The minor strain (e_2) is measured at 90° to the major strain, along the shorter dimension of the final rectangular shape of a part formed using a square pattern, or the shorter axis of the ellipse resulting from deformation of a circular grid pattern. If a square pattern becomes skewed into a parallelogram shape, it shall not be used to measure strain.

3.8 *plane strain*—the condition in metal sheet forming that maintains a near zero (0 to +5 %) minor strain (e_2) while the major strain (e_1) is positive (in tension). It is sometimes referred to as FLD_0 . See Fig. 1 and Fig. 4.

3.8.1 *Discussion*—Plane strain is the most severe deformation mode and causes a low point in the forming limit curve (FLC). For convenience, many FLCs are shown with the low point at 0 % (e_2), however, such an abrupt reversal of (e_1) strain does not occur. See Fig. 2 and Figs. X2.1-X2.3.

3.9 *biaxial stretching*—a mode of metal sheet forming in which positive strains are observed in all directions at a given location. See Fig. 4.

3.10 *limiting dome height (LDH)*—an evaluative test for metal sheet deformation capability employing a 200 mm (4 in.) hemispherical punch and a circumferential clamping force sufficient to prevent metal from the surrounding flange being pulled into the die cavity.

3.10.1 *Discussion*—The LDH test was designed to give a repeatable measure of punch movement among specimens of a specific metal sheet sample, thus the only measured value would be the punch height at incipient fracture. Problems with maintaining a secure clamp result in variation of the measured LDH value. A modification of the LDH test using a strip in the range of 200 mm (4 in.) wide was found to give (e_1) values near 0 % (e_2), when the surface strains were measured using a grid pattern. On this basis, a test was developed to use a sheared strip of metal sheet 200 mm (4 in.) wide and sufficiently long to be securely clamped in the LDH test fixture. The height at incipient fracture was to correlate with FLD_0 . The test was not sufficiently repeatable to be employed for evaluation of metal sheet samples. The equipment is used to stretch specimens, with grid patterns, that have been sheared to various widths and is one method to obtain a range of (e_2) and associated (e_1) values for plotting a FLC on a FLD.

4. Summary of Test Method

4.1 The procedure for determining a forming limit curve (FLC) involves the following:

4.1.1 Using a hemispherical punch testing machine (LDH tester). Sometimes called a bulge tester. The LDH test employs a 100 mm (4 in.) diameter machined surface punch.

4.1.1.1 A universal testing machine for tension load application and a sub-press for against the metal sheet surface loading with a ball punch of 75 mm (3 in.), 100 mm (4 in.), or larger diameter can be used in place of the LDH test equipment.

4.1.2 Preparing a series of grid pattern blanks with different widths and a common length suitable for being securely gripped in the test apparatus.

4.1.2.1 All specimens for a series shall have their long dimension in the same orientation, relative to the original process rolling direction of the sample and that direction noted in the report.

4.1.3 Lubricating the contact surfaces of the blank and punch for the hemispherical punch test.

4.1.3.1 Mineral oil and a thin polyethylene sheet is an excellent lubricant.

4.1.3.2 Drawing lubricants, or greases containing graphite, are acceptable.

4.1.3.3 Kerosene is not a good lubricant, as it cleans the surfaces under pressure and the metal sheet will not slide over the punch.

4.1.4 Securely clamping the flanges of a blank in the serrated, or lock bead, blank-holder dies of the hemispherical punch test.

4.1.4.1 For a tension test specimen, the standard procedure for testing sheet type specimens, as shown in Fig. 1 of E 8/E 8M, shall be followed.

4.1.5 Stretching the central area of the blank biaxially over the nose of the hemispherical punch, or pulling in the tension test, without interrupting the force.

4.1.5.1 Negative (e_2) strains can be obtained using sheared narrow strips stretched over the punch of the LDH tester.

4.1.6 Stopping the punch advance or the force when a localized through thickness neck (localized necking) is observed, if possible, or as soon as the specimen fractures.

4.1.7 Removing the specimen from the testing machine grips and then proceeding with another, different width, blank in the test series of the same material.

4.1.8 Measuring and recording the (e_1) and the (e_2) strains of the grid pattern on the surface area near the neck of all the test specimens for the series.

4.1.8.1 These measurements can include good (no localized necking), marginal (localized necking), and fracture areas.

4.1.8.2 If other than good (no localized necking) locations are included, each measured point shall be visually evaluated and noted as illustrated in Fig. 2.

4.1.9 Plotting the measured strain combinations on a FLD. See Fig. 2.

4.1.10 Establishing the forming limit curve (FLC) by connecting the uppermost good (no localized necking) (e_1) strains over the associated (e_2) strain range used in the study.

4.1.10.1 For practical purposes, the specimens that have been strained to a localized neck-down, or through thickness fracture, condition can be measured at a location on the opposite side of the hemispherical bulge from the fracture, in a good (no localized necking) location, to obtain values to establish the FLC.

4.1.10.2 Another acceptable procedure is to measure the grid near the necked, or fracture, location and identify these data points in determining the forming limit curve. This procedure was used in locating the FLC of Fig. 2.

4.1.10.3 Establishing the FLC depends on judgement. Note that in Fig. 2 there are several good (no localized necking) data points above the FLC and two marginal points below the FLC.

4.1.10.4 The FLC curve shall not include an area where there is a preponderance of marginal data points at an (e_1) strain level below the measured good (no localized necking) data points.

5. Significance and Use

5.1 A forming limit curve (FLC) defines the maximum (limiting) strain that a given sample of a metallic sheet can undergo for a range of forming conditions, such as deep drawing, stretching and bending over a radius in a press and die drawing operation, without developing a localized zone of thinning (localized necking) that would indicate incipient failure.

5.1.1 FLCs can be obtained empirically by using a laboratory hemispherical punch biaxial stretch test and also a tension test to strain metal sheet specimens from a material sample beyond their elastic limit, just prior to localized necking and fracture.

5.1.1.1 Since this cannot be predetermined, one or both surfaces of specimens are covered with a grid pattern of gage lengths usually as squares or small diameter circles, by a suitable method such as scribing, photo-grid, or electro-etching, and then each specimen is formed to the point of localized necking, or fracture.

5.1.2 Strains in the major (e_1) and minor (e_2) directions are measured using points on the grid pattern in the area of the localized necking or fracture.

5.1.2.1 Blanks of varied widths are used to produce a wide range of strain states in the minor (e_2) direction.

5.1.2.2 The major (e_1) strain is determined by the capacity of the material to be stretched in one direction as simultaneous surface forces either stretch, do not change, or compress, the metal in the (e_2) direction.

5.1.2.3 In the tension test deformation process, the (e_2) strains are negative and the metal is narrowed both through the thickness and across its width.

5.1.3 These strains are plotted on a forming limit diagram (FLD) and the forming limit curve (FLC) is drawn to connect the highest measured (e_1 and e_2) strain combinations that include good data points.

5.1.3.1 When there is intermixing and no clear distinction between good and necked data points, a best fit curve is established to follow the maximum good data points as the FLC.

5.1.4 The forming limit is established at the maximum (e_1) strain attained prior to necking.

5.1.5 The FLC defines the limit of useful deformation in forming metallic sheet products.

5.1.6 FLCs are known to change with material (specifically with the mechanical or formability properties developed during the processing operations used in making the material), and the thickness of the sheet sample.

5.1.6.1 The strain hardening exponent (n value), defined in Test Method E 646, affects the forming limit. A high n value will raise the limiting major strain (e_1), allowing more stretch under positive ($+e_2$) strain conditions.

5.1.6.2 The plastic strain ratio (r value), defined in Test Method E 517, affects the capacity of a material to be deep drawn. A high r value will move the minor ($-e_2$) strain into a less severe area to the left of the FLD₀, thus permitting deeper draws for a given major (e_1) strain.

5.1.6.3 The thickness of the material will affect the FLC since a thicker specimen has more volume to respond to the forming process.

5.1.6.4 The properties of the steel sheet product used in determining the FLC of Fig. 2 included the n value and the r value.

5.1.7 FLCs serve as a diagnostic tool for material strain analysis and have been used for evaluations of stamping operations and material selection.

5.1.8 The FLC provides a graphical basis for comparison with strain distributions on parts formed by sequential press operations.

5.1.9 The FLC obtained by this method follows a constant proportional strain path where there is a fixed ratio of major (e_1) to minor (e_2) strain.

5.1.9.1 There is no interrupted loading, or reversal of straining, but the rate of straining may be slowed as the specimen approaches neck-down, or fracture.

5.1.9.2 The FLC can be used for conservatively predicting the performance of an entire class of material provided the n value, r value and thickness of the material used are representative of that class.

5.1.10 Complex forming operations, in which the strain path changes, or the strain is not homogeneous through the metal sheet thickness, may produce limiting strains that do not agree with the forming limit obtained by this method.

5.1.11 Characterization of a material's response to plastic deformation can involve strain to fracture as well as to the onset of necking. These strains are above the FLC.

5.1.12 The FLC is not suitable for lot-to-lot quality assurance testing because it is specific to that sample of a material which is tested to establish the forming limit.

6. Apparatus

6.1 Data points for minor strains (e_2) near 0 % and for positive strains ($+e_2$) associated with major strains (e_1) can be obtained using a hemispherical punch testing machine such as a LDH tester, a sub press in a universal testing machine, or a hydraulic bulge testing machine.

6.1.1 The hydraulic bulge can employ a liquid or a soft elastic material as the forming force.

6.2 Data points for the negative minor ($-e_2$) strain associated with a major (e_1) strain can be obtained using various width strips in a LDH tester and also a universal testing machine and Test Method E 8/E 8M for a tension test of a specimen that has a grid pattern on the surface.

6.2.1 A series of specimens having different widths of reduced parallel sections or a series of sheared full length strips with grid patterns is used to obtain a range of (e_2) strains.

6.3 The press apparatus must be capable of securely clamping the test blank to prevent, or minimize, draw-in of flange metal.

6.3.1 Serrated dies work well with equipment using 75 mm (3 in.), or 100 mm (4 in.) diameter punches. If an interlocking ring bead is used, the fit between the two clamping parts shall be such that no area of the specimen flange is pulled-in by the forming force.

6.3.2 Restriction of the pull-in of flange metal is not critical in obtaining strips for measuring (e_1) and associated (e_2) strains to establish the forming limit.

6.3.3 Secure clamping of the flange is critical for the LDH test in which only the punch height is recorded.

6.4 The test system must have sufficient force and stroke to ensure the hemispherical punch can be driven until the metal sheet ruptures.

6.5 The apparatus must produce sufficient force to both hold down the flanges and advance the punch to complete the deformation of the blank.

6.6 Although no punch displacement or load measuring capabilities are required for determining data, such devices are helpful in conducting the test.

6.7 The hemispherical punch is advanced against the center of the clamped specimen at a constant rate until the material exhibits localized necking (through thickness thinning) and a fracture appears in the surface of the specimen.

6.7.1 The punch advance may be slowed at the end of the forming process to aid in stopping at the start of localized necking, or when fracture begins.

6.7.2 The nominal punch speed shall be measured and reported.

6.7.3 Unless there is a defect in the material, it should not split across the nose of the punch. Instead, when the punch is advanced beyond the forming limit of the material, necking or fracturing, or both, will occur in a ring encircling the round cap of the formed region.

6.8 Lubrication improves sliding of the material over the surface of the punch and causes rupture to occur closer to the top. This does not change the forming limit, as the minor (e_2) strain adjusts to the increased major (e_1) strain.

6.9 The punch shall have a hemispherical nose with a nominal diameter of at least 75 mm (3 in.). Diameters of 100 mm (4 in.) and 200 mm (8 in.) have been used.

6.9.1 The 100 mm (4 in.) diameter limiting dome height (LDH) testing equipment is well suited to straining narrow strips and full size (square, or round) specimen blanks to obtain data for determining the forming limit curve (FLC).

6.9.2 A 75 mm (3 in.) round ball seated in a spherical mount can be used as a hemispherical nose punch.

6.10 Clearance between the forming punch and hold down dies shall be large enough to prevent pinching of the metal if the punch advances to full penetration of the die.

6.11 The draw approach radius of the hold down die shall be sufficient to avoid fracture of the test blank in that area during stretching.

6.11.1 Wide blanks may wrinkle or produce an edge tear in the periphery near the hold down bead areas. This is not considered a failure.

6.12 The punch nose and hold down dies shall have a hardness of 50.0 HRC $\pm$ 5.0.

7. Materials

7.1 Prepared stencils of suitable size and accurate dimensions may be used with electrochemical etching equipment, photo grid, or other transfer method to produce grid patterns of squares, circles, or dots, or combination thereof.

7.1.1 The dimensions of the grid pattern shall be checked for each stencil at the start and periodically during use to ensure that dimensions are not changing due to stretching or shrinking.

7.1.2 Wrinkling of the stencil shall be prevented to insure precise gage lengths over the pattern area.

7.1.3 Dimensions of transferred patterns on the metal sheet blank shall be confirmed by measuring at random locations on the specimen.

7.2 Techniques for applying grids are explained in [Appendix X1](#) of this method.

7.2.1 Refer to Specification [A 568/A 568M](#), Appendix X4, for the photographic and electrochemical etching techniques. Improper application of the electric current and time can affect the line appearance so that establishing the line edge becomes difficult when the pattern is magnified for measurement.

7.2.2 A grid pattern with a dark thin line maximizes the precision of readings.

7.3 Rectangular and circle grid patterns made with a metal scribing tool can be used.

7.3.1 It is necessary to measure each scribed circle and rectangle prior to forming the test blank to establish the initial gage length in the final measured directions.

7.4 A grid pattern with precise gage lengths can be printed on one or both surfaces of the test specimen.

7.4.1 This is sometimes necessary when studying a production formed part, but not for the specimens used in establishing the FLC.

7.5 The preferred grid consists of 2.50 mm (0.100 in.) squares, or circle diameters, as the gage length.

7.5.1 Examples of patterns are shown in [Fig. 3](#).

7.6 The length of each side of the square pattern and the diameters of all circles shall be within ± 0.025 mm (0.001 in.) of the established gage length.

7.6.1 Due to possible line width variations within a printed pattern, the measurements shall be from the inside of the line on one side of the square, or circle, to the inside of the opposite line.

7.6.1.1 This is important when measuring high strains where the line width has increased.

7.7 The grid pattern shall cover an area of the specimen blank sufficient to encompass the critically strained areas.

7.8 Solid dots can be used in place of square or open circle patterns. These are preferred for some electronic measuring devices employing a camera and a programmed computer. See [3.4.5](#) for the measuring procedure of solid dots.

8. Sampling

8.1 Blanks to be tested shall be representative of the properties of the material, as specified in the applicable product specification, and shall be from a common known source, such as a single sample.

8.1.1 For coil processed materials, the rolling direction shall be identified on the sample and the specimens.

8.2 The forming limit curve (FLC) is specific to the tested sample of a material.

8.3 It is possible for the forming limit curve (FLC) to be different for separate samples of a given grade of metal.

8.3.1 Some causes of this are differences in the strain hardening exponent (n value), material non-homogeneity, specimen thickness, and the cold rolling and annealing processing methods used in producing the material.

9. Sample Preparation

9.1 Several specimen blanks are required to establish the forming limit curve (FLC).

9.1.1 For example, the 64 data points of [Fig. 2](#) are from 32 specimens of different widths that were formed by several methods.

9.1.2 Specimens over a range of widths are used to obtain different (e_2) strains.

9.2 The blanks shall be sufficiently long in the major strain direction of the forming operation to allow secure clamping in the holding grips and allow a free span over which stretching occurs.

9.2.1 For the tension strain applied in a universal testing machine, either standard reduced-section 50 mm (2 in.) sheet specimens, or sheared parallel strips of various widths, can be used.

9.2.2 For hemispherical punch tests, the blanks must be sufficiently long to be securely clamped in the holding die without excessive pull-in.

9.2.2.1 This secure clamping condition for the flange is not critical for the FLC determination, but it is necessary for the limiting dome height (LDH) test.

9.2.3 Example lengths are 180 to 225 mm (7 to 9 in.) for a test using a hemispherical punch diameter of 100 mm (4 in.) and also for the tension test specimen.

9.3 The width of each set of specimen blanks is different in order to produce a range of minor strain (e_2) values.

9.3.1 Several sets of specimens may be needed to provide sufficient data.

9.3.2 Rectangular strips are cut to various widths, typically ranging from 12 mm (0.50 in.) up to 180 or 200 mm (7 to 8 in.) in increments of 12 mm (0.50 in.), or 25 mm (1 in.).

9.4 Test blanks from a given sample shall all be sheared to width in the same direction, either across the rolling direction or along the rolling direction, of the sheet product.

9.4.1 The rolling direction relative to the specimen length dimension shall be included in the report.

9.5 The width cut shall be made using a shear with sharp blades and a blade clearance of approximately 10 % of sheet thickness to minimize double shear and edge burr effects that could be a safety hazard when handling test specimens.

9.5.1 A moderate amount of shear burr will not affect the test results.

9.5.2 The rake angle of the upper shear blade should be less than 3° to prevent curling of the narrow specimens.

9.6 Edges of the specimen blanks may be polished to remove excessive edge burr.

9.7 Specimens shall have edges that are parallel within 1 % of their length.

10. Calibration

10.1 Tests for forming limit curves made in hemispherical punch forming presses and universal testing machines do not require measurements of the forces applied.

10.2 The measurements of (e_1) and (e_2) strain shall be accurate to ± 2.5 % strain.

10.3 The procedure used to make these measurements may involve one of the five following devices, or it may be a comparable technique and device that gives equivalent precision:

10.3.1 A machinist's microscope with 10 $\times$ magnification and incorporating a calibrated scale.

10.3.1.1 The surface being measured shall be held perpendicular to the microscope.

10.3.2 A steel scale with 0.25 mm (0.01 in.) divisions. The scale lines shall be read from center to center of the line widths.

10.3.3 A magnifier that incorporates a calibrated scale.

10.3.4 A tapered wedge scale on clear plastic (Mylar) that gives the strain in percent for an established gage length, which effectively magnifies the strain.

10.3.5 A circle grid analyzer employing a camera and computer imaging that makes multiple simultaneous readings.

10.4 Curvature of the surface of specimens formed over a hemispherical punch is not critical over the distance of the 2.5 mm (0.100 in.) initial gage length.

11. Conditioning of Specimens

11.1 The forming limit curve (FLC) is specific to the material sampled. It can change if the material is subjected to cold work or any annealing process. Thus, two samples from a given lot of material can produce different curves if their processing varied.

11.2 The processing history of the material must be known if the test is to be considered representative of a grade of a product.

11.3 Applying the grid pattern may require cleaning the surface of the sample. This will not affect the results. Grids have been successfully applied to metallic coated and pre-lubricated surfaces.

12. Procedure

12.1 Test blanks shall be wiped clean and dry to remove grit and soil. A lubricant of any suitable type can be used between the hemispherical punch and the specimen's surface.

12.1.1 Lubricants increase the amount of stretch before localized necking and move the location toward the nose of the punch.

12.1.1.1 Mineral oil plus a polyethylene sheet, and graphite drawing compounds are good lubricants, while kerosene is not.

12.1.2 Lubrication changes the e_1 and e_2 strains, but does not affect the FLC. Data points move along the curve due to the change of the e_2 strain becoming more positive in the stretch region and more negative in the draw region of the FLD when effective lubricants are used in press forming.

12.2 Any metal pick-up on the punch shall be removed prior to the test.

12.2.1 Cold welding can occur if there is no lubricant; heat, pressure, and coatings on the specimen can cause metal pick-up.

12.3 The punch speed (or rate at which the deformation of the specimen occurs) shall be such that the test can be stopped when localized necking or fracture occurs.

12.3.1 Initial application of the forming force shall not be abrupt.

12.3.2 Incremental loading, in which the force is removed and reapplied, shall not be used in determining the FLC.

12.4 The test blank shall be centered over the punch, especially the width for narrow strips formed over a hemispherical punch. If only one surface has an applied grid pattern, it shall be away from the punch contact surface.

12.4.1 Any metallic sheet deformation process can be used if it is continuous and not interrupted before the test conclusion. For examples, a LDH machine using a 200 mm (4 in.)

diameter hemispherical punch, other ball punch testing machines using round ball punches, and a standard tension test in a universal testing machine can apply controlled force to form the metallic sheet.

12.5 The testing machine is activated to stretch the blank continuously until the onset of localized necking, as observed visually or by monitoring for a drop in the testing machine applied force.

13. Results and Calculations

13.1 Selection of gage lengths to be measured:

13.1.1 It is not necessary to measure each gage location. With a dot pattern, all locations can be measured by using a circle grid analyzer, but this would be extremely time consuming if done by a hand held scale and a magnifier.

13.1.2 Deformed circles may appear as ellipses with widened lines at the long dimension ends. These shall be measured from the inside of one line to the inside of the opposite line.

13.1.3 All gage lengths that are to be measured shall be near the location on the specimen where localized necking initiated, no more than 2 or 3 ellipses away from the necked, or fractured, site in the radial direction relative to the nose of the punch.

13.1.4 If fracture has occurred, it will be on one side of the hemisphere pole. Suitable grids for measuring the strain levels at localized necking can be found on the opposite side of the pole.

13.2 Visual rating of the individual deformed grid areas shall be made, with each classified as being good (no localized necking), marginal (contains localized necking), or fractured, defined as follows:

13.2.1 *Good (also referred to as no localized necking, pass, or acceptable, on production parts)*—The deformed grid lies in an area entirely outside the necked region of the specimen.

13.2.2 *Marginal (also called localized necking, or borderline)*—The deformed grid lies in a region of localized thinning, or a trough in the specimen surface.

13.2.2.1 For circle grid patterns, if the ellipse is tear-drop shaped, indicating nonuniform strain, it shall not be measured. The condition can be corrected by using a smaller diameter grid.

13.2.3 *Fracture (also called fail)*—A split through the specimen separates the gage length of the grid in two and the area is beyond the forming limit. Each piece can be measured for information purposes.

13.3 *Strain Measurements:*

13.3.1 The major (e_1) and minor (e_2) strains of the selected deformed grids shall be measured to within $\pm 2.5\%$. For a 2.5 mm (0.100 in.) initial gage length, this is ± 0.075 mm (0.0025 in.).

13.3.2 Schematic diagrams of the three ways the circle grid can deform are shown in Fig. 4, representing draw, plane strain and biaxial stretch.

13.3.3 The calculations of the major strain and the associated minor strain are illustrated. The major strain (e_1) is defined to coincide with the major deformation direction and the minor strain (e_2) is at 90° to the major strain direction.

$$\text{Major strain} = \frac{L_f - L_o}{L_o} \times 100 = e_1 (\%)$$

$$\text{Minor strain} = \frac{W_f - W_o}{W_o} \times 100 = e_2 (\%)$$

where:

L = length,
 W = width,
 o = original, and
 f = final.

14. Forming Limit Curve (FLC)

14.1 The data for the (e_1) and (e_2) strains of the selected grids are plotted on a FLD as shown in Fig. 2.

14.2 Each data point is identified by the code as being good (no localized necking), or marginal (localized necking). Fractured grid areas are normally not measured.

14.3 A smooth curve is drawn above the good (no localized necking) data points.

14.3.1 In the event that some good (no localized necking) data points are intermixed with marginal (localized necking) points, the curve shall lie below these marginal points unless additional strain measurements on the same or a similar specimen show a preponderance of good data points in the area on the FLD.

14.4 The range of major (e_1) strains can be from 0 % to over 200 %.

14.5 The range of minor (e_2) strains can go from -40% to over $+60\%$.

14.6 The FLD for a material can be reduced in range. If the lower limit of the major strain (e_1) dimension is not shown as 0 %, this shall be noted in the report.

15. Report

15.1 The forming limit curve (FLC) report shall include the following information:

15.1.1 Forming limit diagram, with the lower limit of the major strain axis noted if it is different from 0 % (e_1) on the FLD.

15.1.2 Forming limit curve (FLC) drawn on a forming limit diagram (FLD).

15.1.3 Material designation, and processing if not standard for the grade.

15.1.4 Material thickness.

15.1.5 Orientation of the long dimension of the blanks relative to the coil processing direction.

15.1.6 Temperature of testing facility, if other than ambient.

15.1.7 Diameter of any hemispherical punch used to stretch form the specimen.

15.1.8 Punch speed of nominal advance during the test, exclusive of final slow down.

15.1.9 Lubricant used on the contact surfaces.

15.1.10 Blank sizes, length and widths used.

15.1.11 Quantity of a repeated specimen size tested, for example, single, duplicate, triplicate.

15.1.12 Gage length(s) of the grid used.

15.1.13 Method used for measuring the grid pattern.

15.2 The report may include the FLD₀ value.

16. Precision and Bias

16.1 This method is not believed to introduce any systematic bias.

16.2 Using calibrated scales to measure sufficiently magnified grid patterns of determined precision, the accuracy of individual readings of e_1 and associated e_2 strains of 25 mm (0.100 in.) initial gage length should be within $\pm 0.5\%$ (0.012 mm or 0.0005 in.).

16.3 Due to the subjectiveness of the method of selecting areas to measure and classify as necked, or not necked,

variations of forming limit curves (FLC) for a specific material may show disagreement among testers. For a given material the forming limit curve (FLC) should be repeatable within $\pm 5\%$.

17. Keywords

17.1 circle grid; forming limit curve (FLC); forming limit diagram (FLD); limiting dome height (LDH); major strain; minor strain; strain analysis

APPENDIXES

(Nonmandatory Information)

X1. TECHNIQUES FOR APPLYING GRID PATTERNS

INTRODUCTION

There are several methods available for applying gage marks to the surface of metallic sheets used in determining the strains for plotting data on a FLD from which to obtain a FLC. For convenience, these are usually in the form of a grid pattern consisting of squares, circles, dots, or combinations of these patterns.

X1.1 Punch Marks—A punch mark is the simplest method, with two making up a gage length for the major (e_1) strain and a third at a right angle providing the 90° minor (e_2) strain. It is necessary to measure the distances between the two before and after forming the specimen, and then calculate the percent strain based on the initial gage length in each direction. Punch marks shall be shallow and could cause premature failure in some materials. For this reason, punch marks shall only be used when evaluating highly formable materials.

X1.2 Scribed Square—A square pattern of scribed lines was used in early studies of drawn metal sheet parts to evaluate strains. For the precision required to construct a FLC, the intersection of each scribe line in the critical areas would have to be measured, as for the punch marks.

X1.3 Scribed Circles—Using a compass with a steel point to locate circles on the surface of a part to be studied for strain distribution is commonly done over areas subjected to low strain levels. These are usually 125 mm (5 in.) diameter to detect strains of less than 5 %. Similar circles of 2.5 mm (0.10) in. could be used for determining a FLC.

X1.4 Photogrid—A photographic print of a pattern can be printed on the surface using the technique described in Specification A 568/A 568M, Appendix X4. This can be used to obtain a fine lined pattern over a surface. One problem is a tendency for the pattern to become detached from the surface under high strains which can result in false readings.

X1.5 Silk Screen—A pattern of circles, squares, or any desired shape can be made by the silk screen process. This was used extensively in the early development of the circle grid

technique. One problem is resolution, in that gage lengths less than 25 mm (1 in.) cannot be established precisely using silk screen inks or paint.

X1.6 Electrochemical Etching—This is a refinement of the silk screen method. Stencils are available commercially with many different patterns for use on a variety of materials, to accommodate the needs of the user. For FLC determinations, a pattern with a fine line width on a non-stretching backing is required.

X1.6.1 This technique was first used to imprint logos and information on metal parts.

X1.6.1.1 Considerations are necessary for specific applications and it is recommended that anyone using the electrochemical etching method should first be properly trained by a knowledgeable person.

X1.6.2 Special transformers and etching solutions are available from suppliers of the stencils. Early methods of stenciling used a weight and pressure pads soaked in the chemical. Rollers and pads soaked with the chemical are now most frequently used.

X1.6.3 A rectifier unit is required, operating with 115 volt, 60 Hz, AC power input that applies up to 10 amps of output and from 0 to 26 volts. One lead from this is connected to the work and the other to the roller.

X1.6.4 The stencil is coated with the etching solution and placed on the material to be etched. A pad soaked with the same chemical, specific for the metal being etched, is placed over the stencil. It is necessary to have sufficient solution on the pad, but too much solution will create problems. Pad thickness should be about 3 mm ($\frac{1}{8}$ in.).

X1.6.5 The current is turned on at the rectifier and the roller is slowly rolled across the width of the stencil pad. It is not



advisable to roll the roller back and forth, as a double print of the pattern can result due to slippage of the stencil under the pad.

X1.6.5.1 If the print is too light, more etching solution may be needed on the pad, or if it is too dark and broad, the voltage can be adjusted to give a correct pattern.

X1.6.5.2 Caution should be exercised to not touch the metal roller and the material being etched, as a mild electric shock to the operator can result. Hold the roller by the handle and turn the current on only during the etching process.

X1.6.6 The pad and stencil are removed from the metal sheet being etched, and a uniform dark lined pattern should be on the surface. This dark pattern should dry before it is handled, as it can be rubbed off, leaving a light etched pattern that is more difficult to read.

X1.6.7 Several different solutions are available from the stencil suppliers for use on surfaces of steel, stainless steel, aluminum, brass, zinc and other metals.

X1.6.7.1 AC or DC current can be used, depending on the desired finish (black or frosty) to the pattern and the material being etched.

X1.6.8 The etching solution is mildly corrosive and if not rinsed, or neutralized with a second solution, the surface of steel sheet will rust when exposed to air for a short time. This can be minimized by not having excess solution on the pad. Some solutions contain a rust inhibitor.

X1.6.9 Wiping the etched surface with a lubricating oil will prevent excessive rusting.

X1.6.10 The gage length of the grid shall be checked at random locations over the test specimen prior to use to ensure that the gage length has not been affected by stretching the stencil pattern.

X2. SAMPLE FORMING LIMIT DIAGRAMS FOR ALUMINUM KILLED DRAWING QUALITY STEEL, ALUMINUM TYPE 3003-0, AND BRASS ALLOY C260 SHEET PRODUCTS

INTRODUCTION

Forming limit curves (FLC) were determined for three materials using the procedure described in this method.

X2.1 The first material is an aluminum killed cold rolled steel sheet similar to that used for Fig. 1 of the method. The method for establishing the forming limit involved locating the FLC above the good locations (solid circles) and below the marginal data points (half filled circles).

X2.1.1 The minimum point for this steel is around +5 % e_2 to give a FLD_o of 49 % e_1 .

X2.2 The second material is a 3003-0 aluminum sheet.


X2.2.1 The minimum point for this aluminum is around +5 % e_2 and the FLD_o is 40 % e_1 .

X2.3 The third material is a 260 brass sheet.

X2.3.1 The minimum point on the FLC curve for this brass sheet is between 0 and +5 % e_2 and the FLD_o is at 46 % e_1 .

Major Strain

% e_1

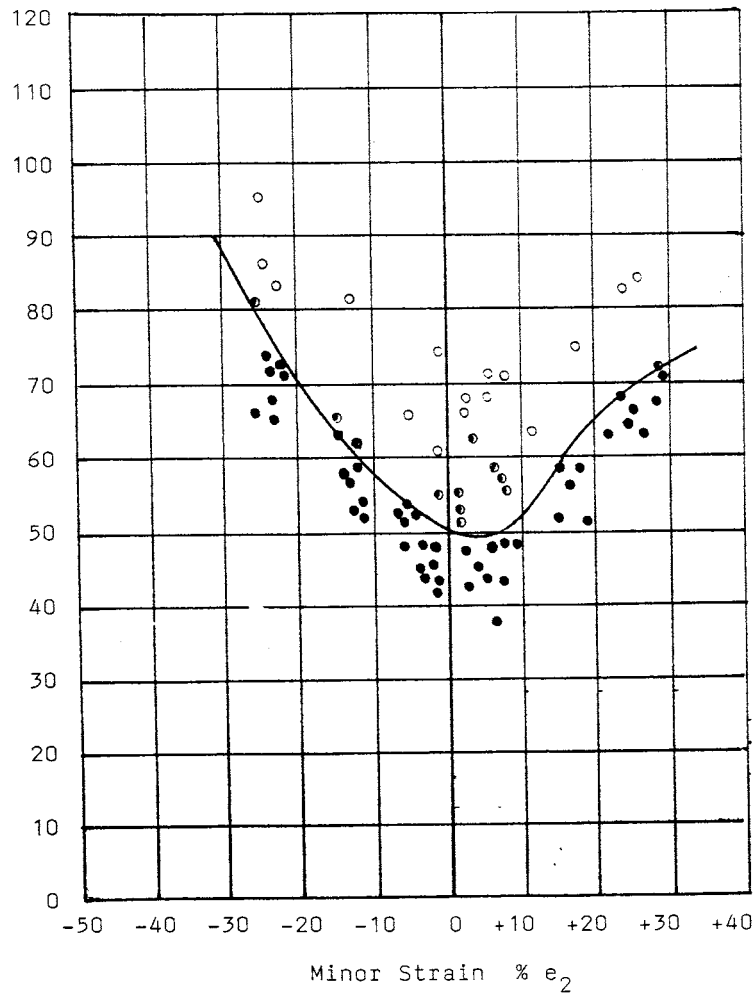

Code: ● good ◐ marginal (Necked) ○ fail

Material properties:

Thickness 0.990 mm (0.039 in.)
Strain hardening (n) 0.222

Test result: FLD₀ 49 %


Cold Rolled Drawing Quality Aluminum Killed Steel
Longitudinal Mechanical Properties

Thickness		Yield Strength		Tensile Strength		% El in 50 mm	n Value	r Value
mm	(in.)	MPa	(ksi)	MPa	(ksi)			
0.990	(0.039)	173	(25.1)	303	(44.0)	43	0.228	1.94

FIG. X2.1 Forming Limit Curve (FLC) for a Cold Rolled Drawing Quality Aluminum Killed Steel Sheet

Major Strain

% e_1

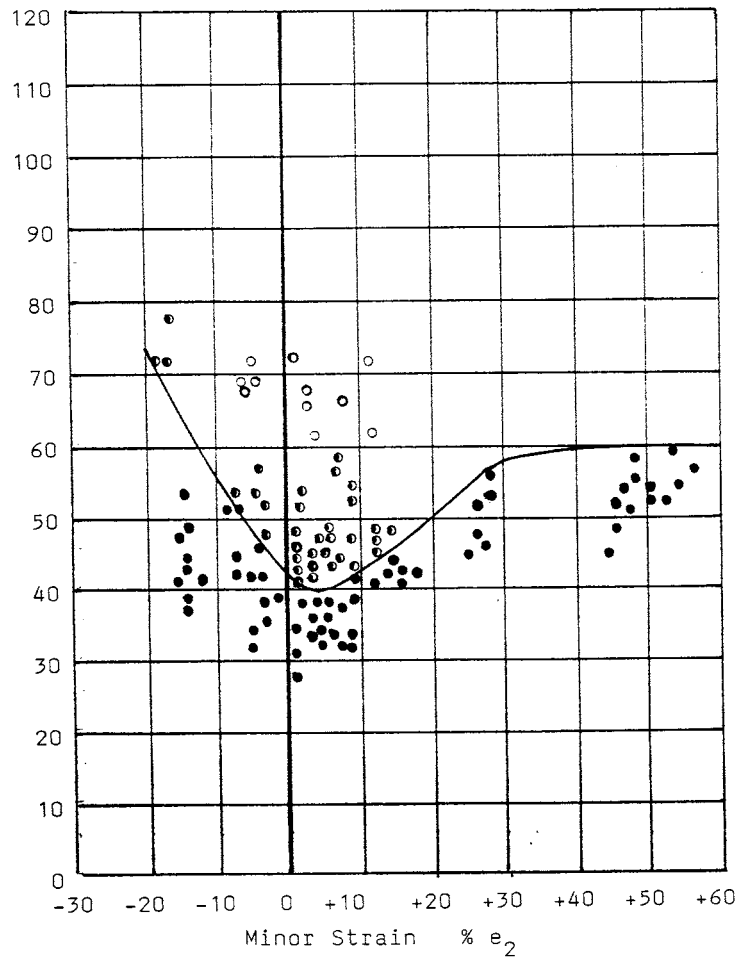

Code: ● good ◐ marginal (necked) ○ fail

Material properties:

Thickness 1.020 mm (0.040 in.)
Strain hardening (n) 0.245

Test result: FLD₀ 40 %


3003-0 Aluminum
Longitudinal Mechanical Properties

Thickness		Yield Strength		Tensile Strength		% El in 50 mm	n Value	r Value
mm	(in.)	MPa	(ksi)	MPa	(ksi)			
1.016	(0.040)	44	(6.3)	113	(16.4)	37	0.248	0.86

FIG. X2.2 Forming Limit Curve (FLC) for a 3003-0 Aluminum Alloy Sheet

Major Strain

% e_1

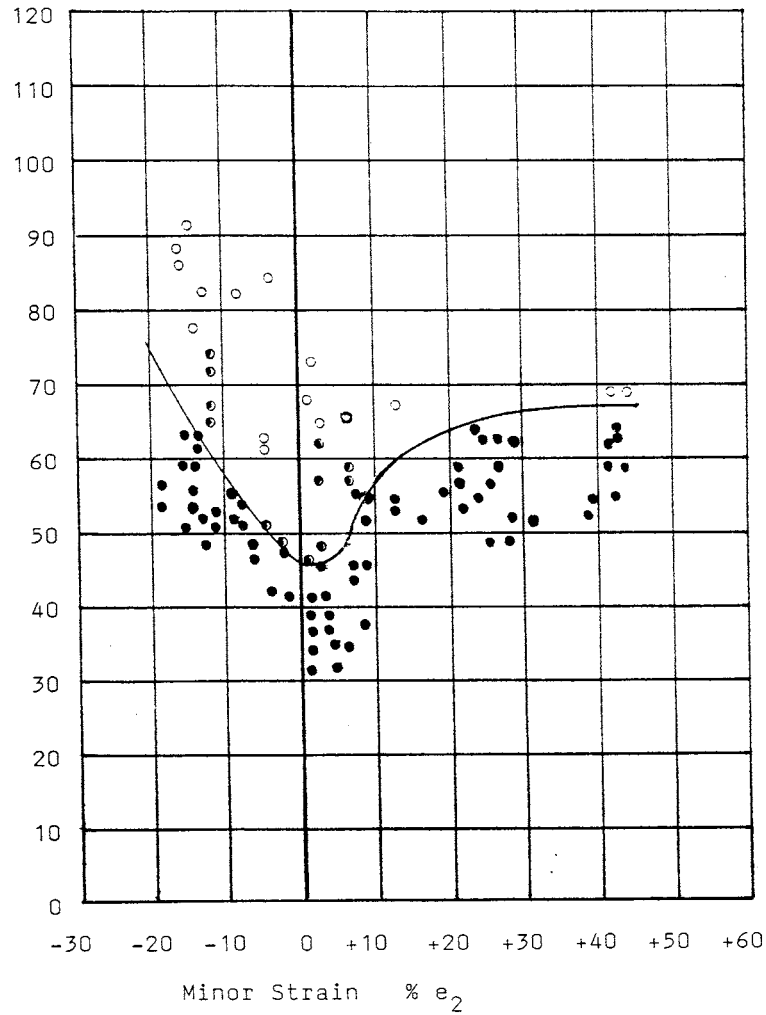

Code: ● good ◐ marginal (necked) ○ fail

Material properties:

Thickness 1.140 mm (0.045 in.)
Strain hardening (n) 0.393
Plastic strain (r) 0.950

Test result: FLD₀ 46%

260 Brass
Longitudinal Mechanical Properties

Thickness		Yield Strength		Tensile Strength		% El in 50 mm	n Value	r Value
mm	(in.)	MPa	(ksi)	MPa	(ksi)			
1.143	(0.045)	136	(19.7)	349	(50.7)	57	0.397	1.05

FIG. X2.3 Forming Limit Curve (FLC) for a C260 Brass Sheet



ASTM International takes no position respecting the validity of any patent rights asserted in connection with any item mentioned in this standard. Users of this standard are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, are entirely their own responsibility.

This standard is subject to revision at any time by the responsible technical committee and must be reviewed every five years and if not revised, either reapproved or withdrawn. Your comments are invited either for revision of this standard or for additional standards and should be addressed to ASTM International Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee, which you may attend. If you feel that your comments have not received a fair hearing you should make your views known to the ASTM Committee on Standards, at the address shown below.

This standard is copyrighted by ASTM International, 100 Barr Harbor Drive, PO Box C700, West Conshohocken, PA 19428-2959, United States. Individual reprints (single or multiple copies) of this standard may be obtained by contacting ASTM at the above address or at 610-832-9585 (phone), 610-832-9555 (fax), or service@astm.org (e-mail); or through the ASTM website (www.astm.org).