



Standard Specification for 245/70R19.5 136/134M Radial Truck Standard Reference Test Tire¹

This standard is issued under the fixed designation F2871; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

1. Scope

1.1 This specification covers the general requirements for the 245/70R19.5 136/134M radial truck standard reference test tire. The tire covered by this specification is primarily for use as a reference tire for braking traction, snow traction, and wear performance evaluations, but may also be used for other evaluations, such as pavement roughness, noise, or other tests that require a reference tire.

1.1.1 Other standard reference test tires are also used for these purposes and are referenced in Section 2.

1.2 This specification provides a 19.5 rim diameter code standard truck tire design and construction, standard dimensions, and specifies the conditions of storage.

1.3 The values stated in SI units are to be regarded as standard. The values given in parentheses are mathematical conversions to inch-pound units that are provided for information only and are not considered standard.

1.4 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

2. Referenced Documents

2.1 *ASTM Standards:*²

[D412](#) Test Methods for Vulcanized Rubber and Thermoplastic Elastomers—Tension

[D2240](#) Test Method for Rubber Property—Durometer Hardness

[D3182](#) Practice for Rubber—Materials, Equipment, and Procedures for Mixing Standard Compounds and Preparing

[Standard Vulcanized Sheets](#)

[E867](#) Terminology Relating to Vehicle-Pavement Systems

[E1136](#) Specification for P195/75R14 Radial Standard Reference Test Tire

[F538](#) Terminology Relating to the Characteristics and Performance of Tires

[F2493](#) Specification for P225/60R16 97S Radial Standard Reference Test Tire

[F2870](#) Specification for 315/70R22.5 154/150L Radial Truck Standard Reference Test Tire

[F2872](#) Specification for 225/75R16C 116/114S M+S Radial Light Truck Standard Reference Test Tire

3. Terminology

3.1 *Definitions:*

3.1.1 For definitions of terms used in this specification, refer to Terminology [F538](#).

3.1.2 *pavement characteristic, n*—physical feature or property of a pavement surface such as type, roughness, texture, and skid resistance. [E867](#)

3.1.3 *pitch, n*—unit of tread pattern elements used in various combinations to obtain optimum noise levels. [F538](#)

3.1.4 *standard reference test tire, SRTT, n*—tire that is used as a control tire or surface-monitoring tire (for example, Specifications [E1136](#), [F2493](#), [F2870](#), [F2871](#), and [F2872](#) tires). [F538](#)

4. Design and Construction

4.1 The 245/70R19.5 136/134M standard reference test tire shall feature the steel-belted radial technology, and a smooth-ribbed tread design, see [Fig. 1](#) and [Fig. 2](#), with technology as described in Sections 5-7.

4.2 The tire shall be designed to conform to the European Tyre and Rim Technical Organisation (ETRTO) dimensions and tolerances for cross section and overall diameter found in the current ETRTO Standards Manual.³

¹ This specification is under the jurisdiction of ASTM Committee [F09](#) on Tires and is the direct responsibility of Subcommittee [F09.20](#) on Vehicular Testing.

Current edition approved Jan. 1, 2011. Published March 2011. DOI: 10.1520/F2871-11.

² For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

³ Available from the European Tyre and Rim Technical Organisation 32/2, avenue Brugmann – B-1060 Brussels Belgium.

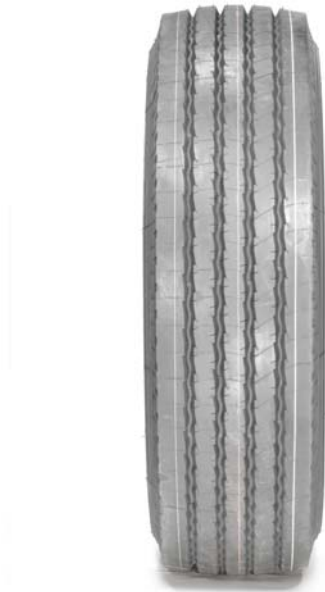


FIG. 1 Front View of the 245/70R19.5 136/134M Radial Truck Standard Reference Test Tire



FIG. 2 Side View of the 245/70R19.5 136/134M Radial Truck Standard Reference Test Tire

4.3 The tire used for this specification is produced by Manufacture Francaise des Pneumatiques Michelin.⁴ The tire is stamped on the sidewall with the words: “Standard Reference Test Tire” and “F2871”.

5. Materials and Manufacture

5.1 The individual standard reference test tires shall conform to the manufacturer’s design standards.

5.2 Tread compound, fabric processing, and all the steps in tire manufacturing shall be controlled to ensure minimum variability between tires.

5.3 The standard reference test tire shall be as originally molded without any tread grinding or repairs.

5.4 Since the formulation for tread compounds are proprietary, they shall be controlled by means of their physical properties given in Table 1.

5.5 Dimensions, weights, and permissible variations are given in Section 7.

5.6 The tire shall be of the following construction:

5.6.1 One-ply sidewall construction (steel).

5.6.2 A five-ply tread construction (one-ply steel and four steel belts).

5.6.3 Black sidewall.

6. Physical Properties

6.1 The physical properties of the tread compound are listed in Table 1.

7. Dimensions, Weights, and Permissible Variations

7.1 Details of dimensions are listed as follows and are shown in Fig. 3. When tolerances are not specified, tire dimensions are subject to manufacturer’s normal tolerances.

7.2 *Inflated Dimensions and Cured Cord Angles (at 825 kPa (120 psi)):*

7.2.1 The tread width shall be 208 mm (8.19 in.), and the cross-sectional tread radius shall be 625 mm $\pm$ 50.8 mm (24.61 in. $\pm$ 2.0 in.) on the center and 475mm $\pm$ 50.8 mm (18.70 in. $\pm$ 2.0 in.) on the shoulder.

7.2.2 The tread radius is measured using a reference radius template as shown in Fig. 4.

7.2.3 The tire shall have an overall section width of 251.6 mm (9.91 in.), and an outside diameter of 849 mm (33.43 in.) when mounted on a measuring rim (19.5 by 7.50 rim).

7.2.4 The cured cord angles shall be 90 $\pm$ 8° for the carcass and 65 $\pm$ 4° for belt 1, 26 $\pm$ 4° for belt 2, and 18 $\pm$ 4° for belts 3 and 4.

7.3 *Ribs*—The tire shall have five ribs.

7.4 *Grooves*—The tire shall have four circumferential grooves having a minimum tread depth of 12.8 mm (0.504 in.).

7.5 *Tread Design:*

7.5.1 *Groove (Void) Area Fraction*—22 %.

7.5.2 *Number of Pitches*—72.

7.5.3 *Footprint Size*—182 mm long by 205.9 mm wide (7.17 by 8.11 in.) at 2240 kg (4938 lb) at 775 kPa (112 psi).

7.6 *Tread Wear Indicators*—The tire shall have indicators in each groove, laterally across the tread width, in at least six locations spaced uniformly around the tire circumference. The

TABLE 1 Physical Properties of Tread Compound

Tensile sheet cure, min at 160°C (320°F)	15.0 min
Stress at 300 % elongation, Mpa (psi)	11.0 $\pm$ 1.0 MPa (1595 $\pm$ 145 psi)
Tensile strength, min MPa (psi)	15.5 MPa (2250 psi) min
Elongation, min %	450 % min
Durometer hardness ^A	65 $\pm$ 2 Type A

^A Measured on tire tread.

⁴ The sole source of supply of the apparatus known to the committee at this time is Manufacture Francaise des Pneumatiques Michelin CERL Ladoux, 23 place des Carnes Dechaux, 6304 Clermont-Ferrand Cedex 09, France (attn. F43 Magasin – specify 245/70R19.5 136/134L Michelin truck SRTT). If you are aware of alternative suppliers, please provide this information to ASTM International Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee,¹ which you may attend.

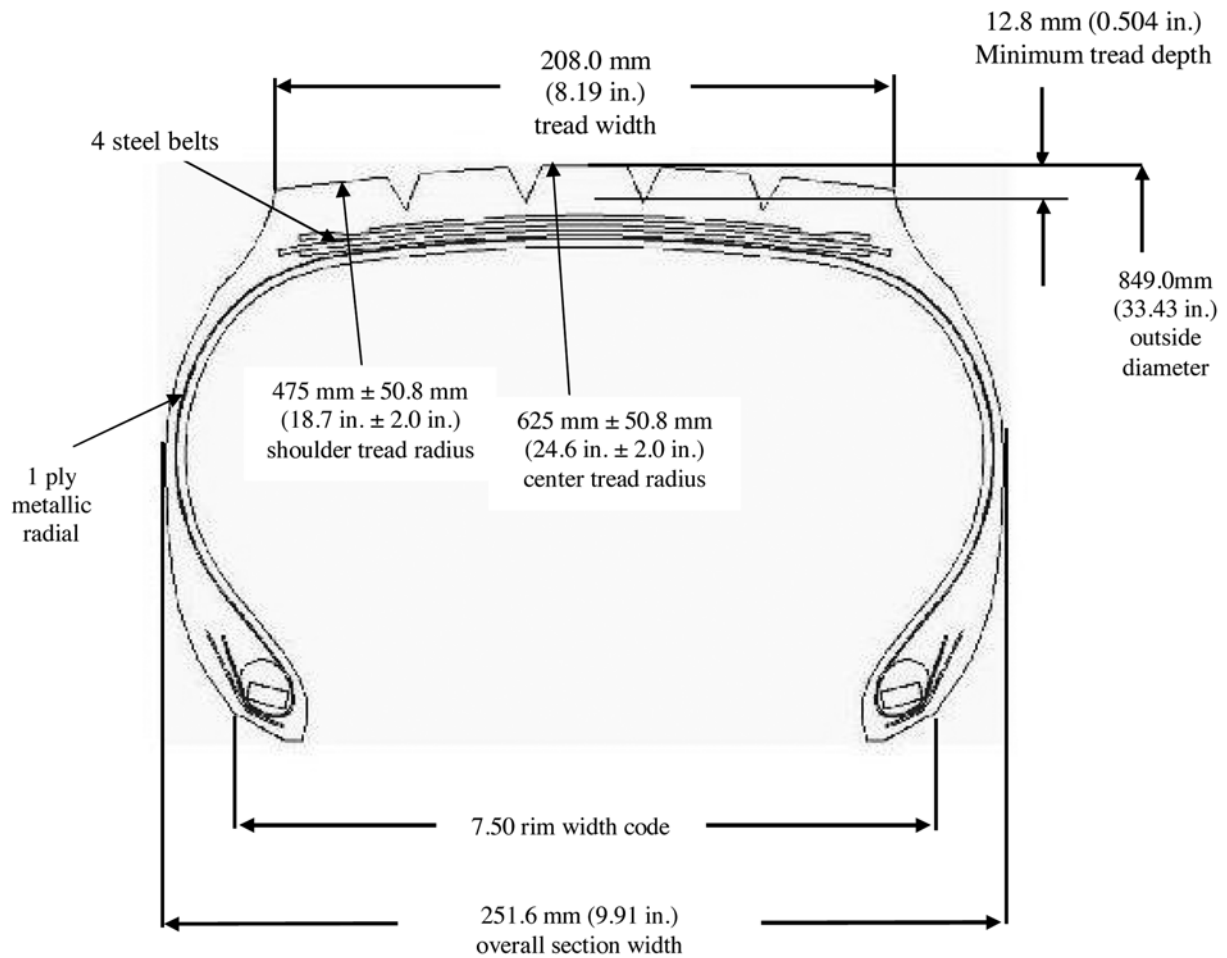


FIG. 3 Tire Cross Section – 245/70R19.5 136/134M Radial Truck SRTT



FIG. 4 Measuring a Tread Radius using a Reference Radius Template

height of the wear indicators in the grooves shall be 1.6 mm (0.0625 in.), – 0.00 mm, + 0.60 mm.

NOTE 1—Tread depth is not to be measured at these wear indicators.

8. Workmanship

8.1 Tires shall be free of defects in workmanship and material.

9. Test Methods

9.1 Preparation of tensile sheet cure shall be in accordance with Practice **D3182**.

9.2 Stress at 300 % elongation shall be in accordance with Test Methods **D412**.

9.3 Tensile strength shall be in accordance with Test Methods **D412**.

9.4 Elongation shall be in accordance with Test Methods **D412**.

9.5 Tire tread hardness shall be in accordance with Test Method **D2240** in addition to the following:

9.5.1 Use a Type A durometer that has the center of the presser foot at a minimum of 6.0 mm (0.24 in.) from any edge of the foot.

9.5.2 Check the durometer operation and the state of calibration of the durometer with the rubber reference block(s).

9.5.3 Condition the tire and the durometer to an equilibrium of $23 \pm 2^{\circ}\text{C}$ ($73.4 \pm 3.6^{\circ}\text{F}$) before determining the tread hardness.

9.5.4 Determine the tire tread hardness by averaging at least four readings. Take these readings in the center of each rib, excluding the center rib. It is recommended that additional sets of readings be taken around the tread circumference.

9.5.5 Apply the presser foot to the tire tread, as rapidly as possible without shock, keeping the foot parallel to the tread surface. Apply just enough pressure to obtain firm contact between the presser foot and the tread surface. Read the durometer scale within 1 s after the presser foot has made contact with the tread, but after the initial maximum transient needle deflection that may occur immediately after contact is made.

10. Certification

10.1 Upon request, the manufacturer shall furnish to the purchaser certification that the test tire meets this specification.

10.2 All tires under certification shall be subject to the manufacturer's normal variation.

11. Storage and Preservation

11.1 The tires shall be stored under constant relative humidity conditions at a temperature not to exceed 21°C (70°F) and above freezing. The ozone level in the storage area shall not exceed 5 parts/ 10^8 (or 5 mPa partial pressure), and no tires shall be stored within 9.1 m (30 ft) of electrical motors or other ozone-generating equipment. Storage of the tires shall be in subdued light, with the tires stacked unbundled, no more than eight tires high on a pallet.

12. Recommendations for Tire Use and Operational Requirements

12.1 It is recommended that the tire be used as a reference for braking traction, snow traction, and wear performance evaluations, and for other evaluations where a standard reference test tire is determined to be required.

12.2 The tire shall be mounted on an ETRTO measuring rim width code of 7.50 (for example, 19.5 by 7.50 rim).

12.3 When irregular wear or damage results from tests, or when wear influences the test results, the use of the tire shall be discontinued.

12.4 Test results, such as measured friction force, may be influenced by tire tread depth or tread hardness or both. The magnitude of this dependence is a function of the water depth, pavement characteristics, test speed, tire aging effects, and break-in.

13. Keywords

13.1 braking; F09; SRTT; standard reference test tire; tire pavement friction; truck; wet braking

APPENDIX

(Nonmandatory Information)

X1. RATIONALE

X1.1 This specification covers the general requirements for the 245/70R19.5 truck radial standard reference test tire. The tire covered by this specification is primarily for use as a reference tire for braking traction, snow traction, and wear performance evaluations, but may also be used for other evaluations such as pavement roughness, noise, or other tests that require a reference tire.

X1.2 Standards and regulatory initiatives in Europe on wet grip braking performance for commercial vehicle tires (or as known in Europe, Class C2 and C3 tires) have required the development of this commercial vehicle standard reference test tire. The use of the standard reference test tire is necessary to limit the variability of the testing method procedures.

ASTM International takes no position respecting the validity of any patent rights asserted in connection with any item mentioned in this standard. Users of this standard are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, are entirely their own responsibility.

This standard is subject to revision at any time by the responsible technical committee and must be reviewed every five years and if not revised, either reapproved or withdrawn. Your comments are invited either for revision of this standard or for additional standards and should be addressed to ASTM International Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee, which you may attend. If you feel that your comments have not received a fair hearing you should make your views known to the ASTM Committee on Standards, at the address shown below.

This standard is copyrighted by ASTM International, 100 Barr Harbor Drive, PO Box C700, West Conshohocken, PA 19428-2959, United States. Individual reprints (single or multiple copies) of this standard may be obtained by contacting ASTM at the above address or at 610-832-9585 (phone), 610-832-9555 (fax), or service@astm.org (e-mail); or through the ASTM website (www.astm.org). Permission rights to photocopy the standard may also be secured from the ASTM website (www.astm.org/COPYRIGHT/).