

Specification for Carbon and Low Alloy Steel Electrodes and Fluxes for Electroslag Welding



American Welding Society

Keywords — Filler metal specifications, low alloy steel electrodes, carbon steel electrodes, arc welding electrodes, metal cored electrodes, electroslag welding

ANSI/AWS A5.25-91
An American National Standard

Approved by
American National Standards Institute
June 19, 1991

Specification for Carbon and Low Alloy Steel Electrodes and Fluxes for Electroslag Welding

Supersedes AWS A5.25-78

Prepared by
AWS Committee on Filler Metal

Under the Direction of
AWS Technical Activities Committee

Approved by
AWS Board of Directors

Abstract

Classification requirements are specified for fluxes and solid and composite metal cored electrodes for electroslag welding. The requirements for electrodes include chemical composition of the electrode for solid electrode and of weld metal for metal cored electrodes. Requirements for fluxes include the mechanical properties and soundness of weld metal taken from a groove weld made with a particular electrode using a prescribed welding procedure. Standard electrode sizes, marking and packaging requirements are included.



American Welding Society

550 N.W. LeJeune Road, P.O. Box 351040, Miami, Florida 33135

Statement on Use of AWS Standards

All standards (codes, specifications, recommended practices, methods, classifications, and guides) of the American Welding Society are voluntary consensus standards that have been developed in accordance with the rules of the American National Standards Institute. When AWS standards are either incorporated in, or made part of, documents that are included in federal or state laws and regulations, or the regulations of other governmental bodies, their provisions carry the full legal authority of the statute. In such cases, any changes in those AWS standards must be approved by the governmental body having statutory jurisdiction before they can become a part of those laws and regulations. In all cases, these standards carry the full legal authority of the contract or other document that invokes the AWS standards. Where this contractual relationship exists, changes in or deviations from requirements of an AWS standard must be by agreement between the contracting parties.

International Standard Book Number: 0-87171-362-4

American Welding Society, 550 N.W. LeJeune Road, P.O. Box 351040, Miami, Florida 33135

© 1991 by American Welding Society. All rights reserved
Printed in the United States of America

Note: The primary purpose of AWS is to serve and benefit its members. To this end, AWS provides a forum for the exchange, consideration, and discussion of ideas and proposals that are relevant to the welding industry and the consensus of which forms the basis for these standards. By providing such a forum, AWS does not assume any duties to which a user of these standards may be required to adhere. By publishing this standard, the American Welding Society does not insure anyone using the information it contains against any liability arising from that use. Publication of a standard by the American Welding Society does not carry with it any right to make, use, or sell any patented items. Users of the information in this standard should make an independent investigation of the validity of that information for their particular use and the patent status of any item referred to herein.

With regard to technical inquiries made concerning AWS standards, oral opinions on AWS standards may be rendered. However, such opinions represent only the personal opinions of the particular individuals giving them. These individuals do not speak on behalf of AWS, nor do these oral opinions constitute official or unofficial opinions or interpretations of AWS. In addition, oral opinions are informal and should not be used as a substitute for an official interpretation.

This standard is subject to revision at any time by the AWS Filler Metal Committee. It must be reviewed every five years and if not revised, it must be either reapproved or withdrawn. Comments (recommendations, additions, or deletions) and any pertinent data that may be of use in improving this standard are requested and should be addressed to AWS Headquarters. Such comments will receive careful considerations by the AWS Filler Metal Committee and the author of the comments will be informed of the committee's response to the comments. Guests are invited to attend all meetings of the AWS Filler Metal Committee to express their comments verbally. Procedures for appeal of an adverse decision concerning all such comments are provided in the Rules of Operation of the Technical Activities Committee. A copy of these Rules can be obtained from the American Welding Society, 550 N.W. LeJeune Road, P.O. Box 351040, Miami, Florida 33135.

Personnel

AWS Committee on Filler Metal

<i>W. L. Wilcox, Chairman</i>	Consultant
<i>D. J. Kotecki, 1st Vice Chairman</i>	The Lincoln Electric Company
<i>D. F. Betz, 2nd Vice Chairman</i>	Crane Midwest
<i>W. A. Dierschow, Secretary</i>	American Welding Society
<i>Z. Al-Hillal</i>	Liquid Carbonic
<i>D. R. Amos</i>	Westinghouse Turbine Plant
<i>B. E. Anderson</i>	Alcotec
<i>K. E. Banks</i>	Teledyne McKay
<i>J. B. Bolton</i>	Kennametal Incorporated
<i>J. Caprarola, Jr.</i>	Alloy Rods Corporation
<i>L. J. Christensen*</i>	Consultant
<i>R. J. Christoffel</i>	Consultant
<i>D. A. DeSignore</i>	Westinghouse Electric Company
<i>H. W. Ebert</i>	Exxon Research and Engineering Company
<i>D. A. Fink</i>	Lincoln Electric Company
<i>J. Gonzalez</i>	Lincoln Electric Company
<i>G. Hallstrom, Jr.</i>	USNRC-R11
<i>R. L. Harris*</i>	R. L. Harris Associates
<i>D. C. Helton</i>	Consultant
<i>W. S. Howes</i>	National Electrical Manufacturers Association
<i>J. P. Hunt</i>	Inco Alloys International
<i>P. A. Kammer*</i>	Eutectic Corporation
<i>G. A. Kurisky</i>	Maryland Specialty Wire
<i>R. A. LaFave</i>	Elliott Company
<i>N. E. Larson</i>	Union Carbide
<i>A. S. Laurenson</i>	Consultant
<i>R. K. Lee**</i>	Consultant
<i>G. H. MacShane</i>	Consultant
<i>L. M. Malik*</i>	Arctec Canada Limited
<i>L. B. Matthews</i>	Harley Davidson York, Incorporated
<i>M. T. Merlo</i>	Tri-Mark, Incorporated
<i>G. E. Metzger</i>	Air Force Material Laboratory
<i>J. W. Mortimer</i>	Consultant
<i>L. W. Mott</i>	Hobart Brothers Company
<i>C. L. Null</i>	Department of the Navy
<i>Y. Ogata</i>	Kobe Steel, Limited
<i>J. Payne</i>	Schneider Services International
<i>R. L. Peaslee</i>	Wall Colmonoy Corporation
<i>E. W. Pickering</i>	Combustion Engineering
<i>S. D. Reynolds, Jr.*</i>	Westinghouse Electric GTSD
<i>L. F. Roberts</i>	Canadian Welding Bureau
<i>D. Rozet</i>	Consultant

*Advisor

**Deceased

<i>P. K. Salvesen</i>	American Bureau of Shipping
<i>H. S. Sayre*</i>	Consultant
<i>O. W. Seth</i>	CBI Na-Con, Incorporated
<i>R. W. Straiton</i>	Bechtel Group, Incorporated
<i>R. D. Sutton</i>	L-Tec Welding and Cutting
<i>R. A. Swain</i>	Welders Supply
<i>J. W. Tackett</i>	Haynes International, Incorporated
<i>R. D. Thomas, Jr.</i>	R. D. Thomas and Company
<i>R. Timerman*</i>	CONARCO, S.A.
<i>R. T. Webster</i>	Teledyne Wah Chang
<i>A. E. Wiehe*</i>	Consultant
<i>W. A. Wiehe</i>	Arcos Division, Hoskins Manufacturing Company
<i>F. J. Winsor</i>	Consultant
<i>K. G. Wold</i>	Aqua-Chem, Incorporated
<i>T. J. Wonder</i>	Rexham Aerospace and Defense Group, Incorporated

**AWS Subcommittee on Carbon and Low Alloy Steel Electrodes
for Electroslag and Electrogas Welding**

<i>D. A. Fink, Chairman</i>	Lincoln Electric Company
<i>W. A. Dierschow, Secretary</i>	American Welding Society
<i>D. Y. Ku</i>	American Bureau of Shipping
<i>D. R. Amos</i>	Westinghouse Turbine Plant
<i>L. F. Roberts</i>	Canadian Welding Bureau
<i>H. S. Sayre*</i>	Consultant
<i>B. L. Shuliz</i>	The Taylor-Winfield Corporation

*Advisor

Foreword

(This Foreword is not a part of ANSI/AWS A5.25-91, *Specification for Carbon and Low Alloy Steel Electrodes and Fluxes for Electroslag Welding*, but is included for information only.)

This is the first revision of this specification, as shown below:

Document Development:

AWS A5.25-78 Specification for Consumables Used for Electroslag Welding of Carbon and High Strength Low Alloy Steels.

Comments and suggestions for the improvement of this standard are welcome. They should be sent to the Secretary, Filler Metal Committee, American Welding Society, 550 N.W. LeJeune Road, P.O. Box 351040, Miami, Florida 33135.

Official interpretations of any of the technical requirements of this standard may be obtained by sending a request in writing, to the Director, Standards and Publications, American Welding Society. A formal reply will be issued after it has been reviewed by the appropriate personnel following established procedures.

Table of Contents

	Page No.
<i>Personnel</i>	iii
<i>Foreword</i>	v
<i>List of Tables</i>	vii
<i>List of Figures</i>	vii
1. Scope	1
<i>Part A—General Requirements</i>	
2. Classification	1
3. Acceptance	1
4. Certification	1
5. Units of Measure and Rounding-Off Procedure	4
<i>Part B—Tests, Procedures, and Requirements</i>	
6. Summary of Tests	4
7. Retest	4
8. Weld Test Assemblies	5
9. Chemical Analysis	7
10. Radiographic Test	7
11. Tension Test	7
12. Impact Test	7
<i>Part C—Manufacture, Identification, and Packaging</i>	
13. Method of Manufacture	8
14. Electrode Requirements	8
15. Flux Requirements	12
<i>Appendix: Guide to AWS Specification for Carbon and Low Alloy Steel Electrodes and Fluxes for Electroslag Welding</i>	
A1. Introduction	15
A2. Classification System	15
A3. Acceptance	17
A4. Certification	17
A5. Ventilation During Welding	18
A6. Definition and General Description	18
<i>AWS Filler Metal Related Documents</i>	(Inside Back Cover)

List of Tables

Table		Page No.
1	Chemical Composition Requirements for Solid Electrodes	2
2	Chemical Composition Requirements for Undiluted Weld Metal from Composite Metal Cored Electrodes	3
3	Tension Test Requirements (As Welded)	3
4	Impact Test Requirements (As Welded)	3
5	Required Tests	4
6	Base Metals for Test Assemblies	7
7	Standard Sizes	10
8	Standard Package Dimensions and Weights	13
A1	Comparison of A5.25-91 Classifications and Classifications in Other AWS Specifications	16

List of Figures

Figure		Page No.
1	Weld Ingot	5
2	Groove Weld Test Assembly for Mechanical Properties and Soundness	6
3	Tension Test Specimen	8
4	Radiographic Acceptance Standards	9
5	Charpy V-Notch Impact Test Specimen	11
6A	Dimensions of 12 and 14 in. Standard Spools	14
6B	Dimensions of 22, 24, and 30 in. Standard Spools	14
A1	Classification System	16

Specification for Carbon and Low Alloy Steel Electrodes and Fluxes for Electroslag Welding

1. Scope

This specification prescribes requirements for the classification of electrodes (both solid and composite metal cored) and fluxes for electroslag welding of carbon and low alloy steels.

Part A *General Requirements*

2. Classification

2.1 The solid electrodes covered by this specification are classified according to the chemical composition of the electrode, as specified in Table 1.

2.1.2 The composite metal cored electrodes covered by this specification are classified according to the chemical composition of the weld metal produced by use with a specific brand name flux (i.e., manufacturer and designation) as specified in Table 2.

2.1.3 Fluxes covered by this specification are classified according to the mechanical properties of the weld metal as specified in Tables 3 and 4, when using an electrode of a particular classification.

2.2 Electrodes classified under one classification shall not be classified under any other classification in this specification. Fluxes may be classified under any number of classifications using a different electrode for each. Fluxes classified as FESX2-XXX may also be classified as FESXO-XXX and FESXZ-XXX, as specifically permitted by note (a) to Table 4.

2.3 The electrodes and fluxes classified under this specification are intended for electroslag welding, but that is not to prohibit their use with any other process for which they are found suitable.

3. Acceptance

Acceptance¹ of the electrodes and fluxes shall be in accordance with the provisions of AWS A5.01, *Filler Metal Procurement Guidelines*.²

4. Certification

By affixing the AWS Specification and Classification designations to the packaging, or the classification to the product, the manufacturer certifies that the product meets the requirements of this specification.³

1. See Section A3 (in the Appendix), Acceptance, for further information concerning acceptance, testing of the material shipped, and AWS A5.01, *Filler Metal Procurement Guidelines*.

2. AWS Standards can be obtained from the American Welding Society, 550 N.W. LeJeune Road, P.O. Box 351040, Miami, Florida 33135.

3. See Section A4 (in the Appendix), Certification, for further information concerning certification and the testing called for to meet this requirement.

Table 1
Chemical Composition Requirements for Solid Electrodes

AWS Classi- fication ^c	UNS Number ^d	Weight Percent ^{a,b}											Other Elements, Total	
		C	Mn	P	S	Si	Ni	Cr	Mo	Cu ^e	Ti	Zr		Al
Medium Manganese Classes														
EM5K-EW	K10726	0.07	0.90- 1.40	0.025	0.035	0.40- 0.70	—	—	—	0.35	0.05- 0.15	0.02- 0.12	0.05- 0.15	0.50
EM12-EW	K01112	0.06- 0.15	0.80- 1.25	0.035	0.035	0.10	—	—	—	0.35	—	—	—	0.50
EM12K-EW	K01113	0.05- 0.15	0.80- 1.25	0.035	0.035	0.10- 0.35	—	—	—	0.35	—	—	—	0.50
EM13K-EW	K01313	0.07- 0.19	0.90- 1.40	0.035	0.035 ^f	0.35- 0.75	—	—	—	0.35	—	—	—	0.50
EM15K-EW	K01515	0.10- 0.20	0.80- 1.25	0.035	0.035	0.10- 0.35	—	—	—	0.35	—	—	—	0.50
High Manganese Classes														
EH14-EW	K11585	0.10- 0.20	1.70- 2.20	0.035	0.035	0.10	—	—	—	0.35	—	—	—	0.50
Special Classes														
EWS-EW	K11245	0.07- 0.12	0.35- 0.65	0.035	0.040	0.22- 0.37	0.40- 0.75	0.50- 0.80	—	0.25- 0.55	—	—	—	0.50
EH10Mo-EW	K10945	0.07- 0.12	1.60- 2.10	0.025	0.025	0.50- 0.80	0.15	—	0.40- 0.60	0.35	—	—	—	0.50
EH10K-EW	K01010	0.07- 0.14	1.40- 2.00	0.025	0.030	0.15- 0.30	—	—	—	—	—	—	—	0.50
EH11K-EW	K11140	0.07- 0.15	1.40- 1.85	0.025	0.035	0.80- 1.15	—	—	—	0.35	—	—	—	0.50
ES-G-EW	—	NOT SPECIFIED ^f												

Notes:

- The electrode shall be analyzed for the specific elements for which values are shown in this table. If the presence of other elements is indicated in the course of this work, the amount of those elements shall be determined to ensure that their total (excluding iron) does not exceed the limit specified for "Other Elements, Total" in the last column of the table.
- Single values are maximums.
- Chemical composition requirements may be similar to those in other AWS specifications; see Table A1 in the Appendix.
- SAE/ASTM Unified Numbering System for Metals and Alloys.
- The copper limit includes copper that may be applied as a coating on the electrode.
- Composition shall be reported; the requirements are those agreed to by the purchaser and the supplier.

Table 2
Chemical Composition Requirements for
Undiluted Weld Metal from Composite Metal Cored Electrodes^a

AWS Classi- fication	UNS Number ^d	Weight Percent ^{b,c}										Other Elements, Total
		C	Mn	P	S	Si	Ni	Cr	Mo	Cu	V	
EWT1	W06040	0.13	2.00	0.03	0.03	0.60	—	—	—	—	—	0.50
EWT2	W20140	0.12	0.50– 1.60	0.03	0.04	0.25– 0.80	0.40– 0.80	0.40– 0.70	—	0.25– 0.75	—	0.50
EWT3	W22340	0.12	1.00– 2.00	0.02	0.03	0.15– 0.50	1.50– 2.50	0.20	0.40– 0.65	—	0.05	0.50
EWT4	—	0.12	0.50– 1.30	0.03	0.03	0.30– 0.80	0.40– 0.80	0.45– 0.70	—	0.30– 0.75	—	0.50
EWTG	—	NOT SPECIFIED ^e										

Notes:

- The flux used shall be that with which the electrode is classified for mechanical properties (see Tables 3 and 4).
- The weld metal shall be analyzed for the specific elements for which values are shown in this table. If the presence of other elements is indicated, in the course of this work, the amount of those elements shall be determined to ensure that their total (excluding iron) does not exceed the limit specified for "Other Elements, Total" in the last column of the table.
- Single values are maximums.
- SAE/ASTM Unified Numbering System for Metals and Alloys.
- Composition shall be reported; the requirements are those agreed to by the purchaser and supplier.

Table 3
Tension Test Requirements (As-Welded)

AWS Classification ^a	Tensile Strength		Yield Strength min ^b		Elongation (min.) Percent ^b
	psi	MPa	psi	MPa	
FES6Z-XXX	60 000	(420)			
FES60-XXX	to	to	36 000	(250)	24
FES62-XXX	80 000	(550)			
FES7Z-XXX	70 000	(490)			
FES70-XXX	to	to	50 000	(350)	22
FES72-XXX	95 000	(650)			

Notes:

- The letters "XXX" as used in the AWS Classification column in this table refer to the electrode classification used.
- Yield strength at 0.2 percent offset and elongation in 2 in. (51 mm) gage length.

Table 4
Impact Test Requirements^a
(As Welded)

AWS Classification ^b	Average Impact Strength ^c Minimum
FES6Z-XXX	Not specified
FES7Z-XXX	Not specified
FES60-XXX	15 ft-lbs at 0° F (20J @ -18° C)
FES70-XXX	15 ft-lbs at 0° F (20J @ -18° C)
FES62-XXX	15 ft-lbs at -20° F (20J @ -29° C)
FES72-XXX	15 ft-lbs at -20° F (20J @ -29° C)

Notes:

- A flux-electrode combination that meets impact requirements at a given temperature also meets the requirements at all higher temperatures in this table. In this manner, FESX2-XXX may also be classified as FESXO-XXX and FESXZ-XXX and FESXO-XXX may be classified as FESXZ-XXX.
- The letters "XXX" used in the AWS Classification column in this table refer to the electrode classification used.
- Both the highest and lowest of the five test values obtained shall be disregarded in computing the impact strength. Two of the remaining three values shall equal or exceed 15 ft-lbs (20J) one of the three remaining values may be lower than 15 ft-lbs but not lower than 10 ft-lbs (14J). The average of the three shall not be less than the 15 ft-lbs (20J) specified.

5. Units of Measure and Rounding-Off Procedure

5.1 U. S. Customary Units are the standard units of measure in this specification. The SI Units are given as equivalent values to the U.S. Customary Units. The standard sizes and dimensions in the two systems are not identical, and for this reason conversion from a standard size or dimension in one system will not always coincide with a standard size or dimension in the other. Suitable conversions, encompassing standard sizes of both, can be made, however, if appropriate tolerances are applied in each case.

5.2 For the purpose of determining conformance with this specification, an observed or calculated value shall be rounded to the nearest 1000 psi for tensile and yield strength, and to the "nearest unit" in the last right-hand place of figures used in expressing the limiting value for other quantities in accordance with the rounding-off method given in ASTM E29, *Standard Practice for Using Significant Digits in Test Data to Determine Conformance with Specifications*.⁴

4. ASTM Standards can be obtained from the American Society for Testing and Materials, 1916 Race Street, Philadelphia, Pennsylvania 19103.

Part B Tests, Procedures, and Requirements

6. Summary of Tests

6.1 Chemical analysis of solid electrodes is the only test required for classification of a solid electrode under this specification, as shown in Table 5.

6.2 Chemical analysis of undiluted weld metal from the composite electrode and a particular (specific brand name) flux is the only test required for classification of a composite electrode under this specification, as shown in Table 5.

6.3 The tests required for classification of each electrode/flux combination are specified in Table 5. The purpose of these tests is to determine the mechanical properties and soundness of the weld. The base metal for the weld test assemblies, the welding and testing procedures to be employed, and the results required are given in Sections 8 through 12.

7. Retest

If the results of any test fail to meet the requirement, that test shall be repeated twice. The results of both

**Table 5
Required Tests**

Material to be Classified	AWS Classification ^a	Chemical Analysis		Radiographic Test	Tension Test	Impact Test
		Electrode	Weld Metal			
Solid Electrodes	All	Required	Not Required	Not Required	Not Required	Not Required
Composite Electrodes ^b	All	Not Required	Required	Not Required	Not Required	Not Required
Fluxes	FES6Z-XXX	Not Required	Not Required	Required	Required	Not Required
	FES60-XXX	Not Required	Not Required	Required	Required	Required
	FES62-XXX	Not Required	Not Required	Required	Required	Required
	FES7Z-XXX	Not Required	Not Required	Required	Required	Not Required
	FES70-XXX	Not Required	Not Required	Required	Required	Required
	FES72-XXX	Not Required	Not Required	Required	Required	Required

Notes:

a. The letters "XXX" used in the AWS Classification column in this table refer to the electrode classification used.

b. The flux used when classifying composite electrodes shall be that with which the electrode is classed for mechanical properties.

retests shall meet the requirement. Specimens for retest may be taken from the original test assembly or from one or two new test assemblies. For chemical analysis, retest need be only for those specific elements that failed to meet the test requirement.


8. Weld Test Assemblies

8.1 No weld test assemblies are required for classification of solid electrodes. One weld test assembly is required for classification of composite electrodes. It is the weld ingot as shown in Figure 1, for chemical analysis of weld metal. In addition to the above, one weld test assembly is required for each classification of an electrode/flux combination. This is the groove weld in Figure 2 for mechanical properties and soundness of the weld metal in the as-welded condition.

8.2 Preparation of each weld test assembly shall be as prescribed in 8.3, 8.4 and 9.2. The base metal for each assembly shall be as required in Table 6 and shall meet the requirements of the appropriate ASTM Specification shown there, or an equivalent specification. Testing of the assemblies shall be as prescribed in 9.3 and Sections 10 through 12.

8.3 Weld Ingot. An ingot shall be prepared as specified in Figure 2.


8.4 Groove Weld for Mechanical Properties and Soundness for Flux/Electrode Combinations. A test assembly shall be chosen and welded as specified in Figure 2 using base metal of the appropriate type specified in Table 6. Testing of this assembly shall be as specified in Sections 10 through 12. The assembly shall be tested in the as-welded condition.

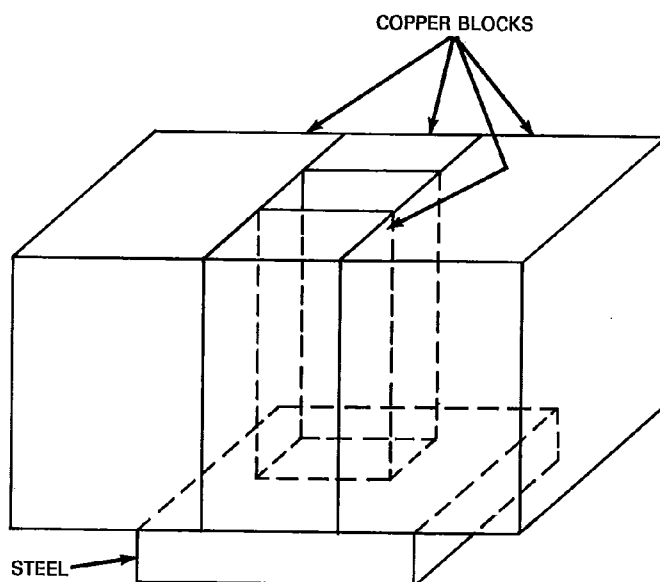

Notes:

1. Weld ingot shall be deposited by arc welding in a water-cooled copper mold using welding conditions shown in Figure 2.
2. Weld ingot shall be of any convenient shape that provides approximately 4 sq. in. (25 sq. cm.) of weld metal cross section.
3. The weld ingot shall be started on a piece of carbon steel of sufficient size as to avoid complete fusion, and the copper mold shall be a sufficient heat sink to avoid contamination of the ingot by molten copper.
4. The sample for chemical analysis shall be taken at least 2 in. (50 mm) from the point of arc initiation and at least 1 in. (25 mm) from the end of the weld.
5. Consumable guide tubes shall be used for preparing the weld ingot if guide tubes were used in welding the groove weld test assembly, as use of consumable guide tubes will affect chemistry.

Figure 1 — Weld Ingot

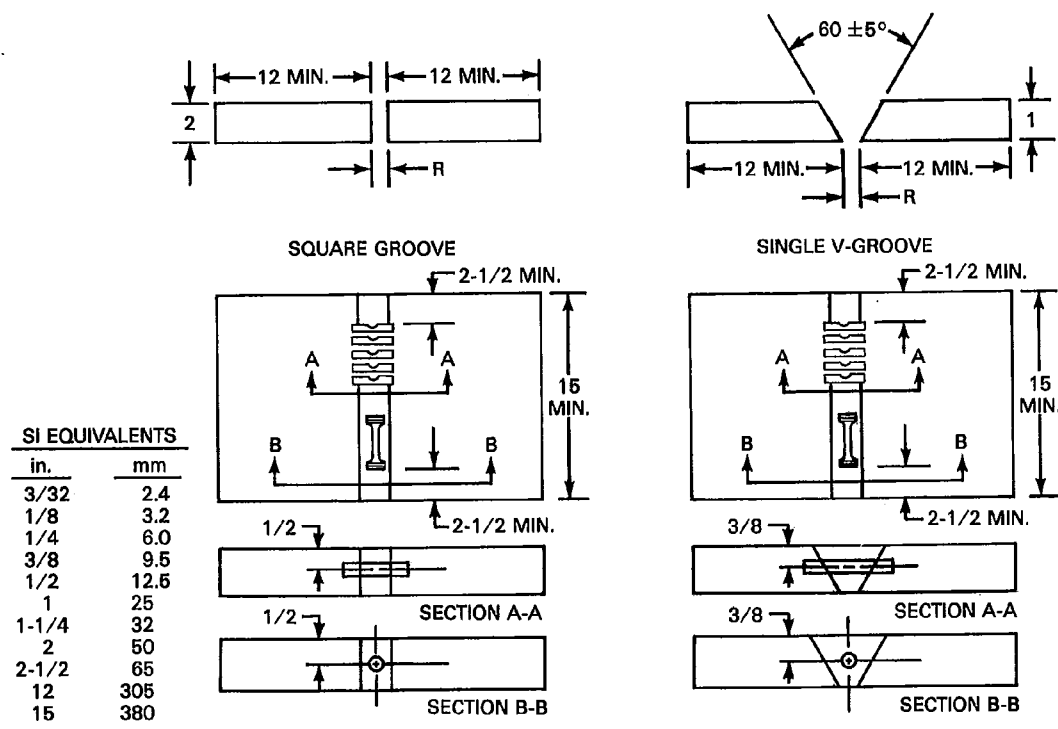

NOTE: ALL DIMENSIONS IN INCHES EXCEPT ANGLES.

Groove Type ^a	Square groove	Square groove ^b	Single V-groove ^b
Thickness, in.	2	2	1
Consumable guide tube (nozzle)	Yes	No	No
Root opening, R, in.	1 to 1-1/4	1 to 1-1/4	1/4 min.
Electrode size, ^c in.	3/32 or 1/8	3/32 or 1/8	3/32 or 1/8
Current: dcnp			
Amperage	500 ± 50	500 ± 50	400 ± 50
Volts	40 ± 2	40 ± 2	40 ± 2

Notes:

- Weld test assembly shall be welded in the vertical position with upward progression.
- The test assembly shall be chosen and fixtured based on the manufacturer's recommendations. Water-cooled copper shoes shall be used except when using consumable guide tubes. For welding with consumable guide tubes, follow the manufacturer's recommendations regarding the use of water-cooled shoes. When using water cooling, the outgoing water temperature shall not exceed 180°F (82°C) near the exit point.
- If the manufacturer does not make the electrode size specified, the nearest size may be used. For sizes other than that shown, follow the manufacturer's recommended procedure.
- Welding shall begin with the assembly at room temperature, 65°F (18°C) minimum. No external heat shall be applied during welding. Run-on and run-off tabs are not required if the test assembly is of sufficient length to provide the required test specimens.
- The weld shall be completed in one pass.
- No thermal treatment shall be performed on the assembly subsequent to the completion of welding.

Figure 2 — Groove Weld Test Assembly for Mechanical Properties and Soundness

Table 6
Base Metals for Test Assemblies

AWS Classification	ASTM Base Metal Specification
FES6X-XXX	A36
FES7X-XXX	A242 Type 2, A441, or A572 Grade 50
FES7X-EWS-EW FES7X-EWT2 FES7X-EWT4	A588

9. Chemical Analysis

9.1 For solid electrodes, a sample of the electrode shall be prepared for chemical analysis. Solid electrodes, when analyzed for elements that are present in a coating (copper flashing, for example), shall be analyzed without removing the coating. When the electrode is analyzed for elements other than those in the coating, the coating must be removed if its presence affects the results of the analysis for other elements.

9.2 Composite electrodes shall be analyzed in the form of undiluted weld metal, not electrode. The sample for analysis shall be taken from weld metal obtained with the electrode (and the specific brand name flux with which it was classified). The sample shall come from an ingot (Figure 1). The top surface of the ingot shall be removed and discarded and a sample for analysis shall be obtained from the underlying metal at a location at least 2 in. (50 mm) from the start of the ingot and at least 1 in. (25 mm) from the end by any appropriate mechanical means. The sample shall be free of slag.

9.3 The sample shall be analyzed by accepted analytical methods. The reference method shall be ASTM Standard Method E350, *Chemical Analysis of Carbon Steel, Low Alloy Steel, Silicon Electrical Steel, Ingot Iron and Wrought Iron*.

9.4 The results of the analysis shall meet the requirements of Table 1 for solid electrodes or Table 2 for composite electrodes, for the classification of electrode under test.

10. Radiographic Test

10.1 The groove weld described in 8.4 and shown in Figure 2 shall be radiographed to evaluate the soundness of the weld metal. In preparation for radiography, both surfaces of the weld may be machined or ground smooth

and flush with the original surfaces of the base metal or with a uniform reinforcement not exceeding 3/32 in. (2.4 mm). Both surfaces of the test assembly, in the area of the weld, shall be smooth enough to avoid difficulty in interpreting the radiograph.

10.2 The weld shall be radiographed in accordance with ASTM E142, *Standard Method for Controlling Quality of Radiographic Testing*. The quality level of inspection shall be 2-2T.

10.3 The soundness of the weld metal meets the requirements of this specification if the radiograph shows no cracks, no incomplete fusion, and no rounded indications in excess of those permitted by the radiographic standards in Figure 4.

In evaluating the radiograph, 2-1/2 in. (65 mm) of the weld on each end of the test assembly shall be disregarded.

A rounded indication is an indication (on the radiograph) whose length is no more than three times its width. Rounded indications may be circular, elliptical, conical, or irregular in shape, and they may have tails. The size of a rounded indication is the largest dimension of the indication, including any tail that may be present.

The indication may be of porosity or slag. Indications whose largest dimension does not exceed 1/64 in. (0.4 mm) shall be disregarded. Test assemblies with indications greater than the largest indications permitted in the radiographic standards do not meet the requirements of this specification.

11. Tension Test


11.1 One all-weld-metal tension test specimen shall be machined from the groove weld described in 8.4 and shown in Figure 2. The dimensions of the specimen shall be as shown in Figure 3.

11.2 The specimen shall be tested in the manner described in the tension test section of AWS B4.0, *Standard Methods for Mechanical Testing of Welds*.

11.3 The results of the tension test shall meet the requirements specified in Table 3.

12. Impact Test

12.1 Five Charpy V-notch impact test specimens (Figure 5) shall be machined from the test assembly shown in Figure 2, for those flux-electrode classifications for which impact testing is required in Table 5. The five specimens shall be tested in accordance with the fracture toughness test section of AWS B4.0, *Standard Methods for Mechanical Testing of Welds*. The test temperature

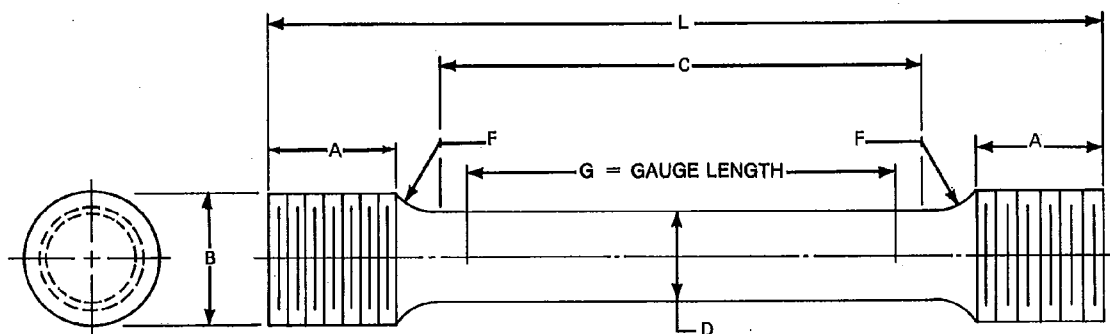

Dimensions of Specimen, in.					
D	G	C	B	F, min.	Approximate Area, in. ²
0.500 ± 0.010	2.000 ± 0.005	2-1/4	3/4	0.375	0.2

Dimensions of Specimen, mm					
D	G	C	B	F, min.	Approximate Area, mm ²
12.7 ± 0.25	50.8 ± 0.13	57	19	9.5	130

Notes:

1. Dimensions G and C shall be as shown, but ends may be of any shape to fit the testing machine holders as long as the load is axial.
2. The diameter of the specimen within the gauge length shall be slightly smaller at the center than at the ends. The difference shall not exceed one percent of the diameter.
3. When the extensometer is required to determine yield strength or other elastic properties, dimension C may be modified. However, the percent of the elongation shall be based on dimension G.
4. The surface finish within the C dimension shall be no rougher than 63 μ in. (1.6 μ m).

Figure 3 — Tension Test Specimen

and the test results shall be those specified in Table 4, for the classification under test.

12.2 In evaluating the test results, the lowest and the highest values obtained shall be disregarded. Two of the remaining three values shall equal, or exceed, the specified 15 ft-lb (20 J) energy level. One of the three may be lower, but not lower than 10 ft-lb (14 J), and the average of the three shall be not less than the required 15 ft-lb (20 J) energy level.

Part C

Manufacture, Identification, and Packaging

13. Method of Manufacture

The welding materials classified according to this specification may be manufactured by any method that will produce material that meets the requirements of this specification.

14. Electrode Requirements

14.1 Standard Sizes. Standard sizes for electrodes in the different package forms (coils with support, coils without support, spools and drums) are shown in Table 7.

14.2 Finish and Uniformity

14.2.1 All electrodes shall have a smooth finish that is free from slivers, depressions, scratches, scale, seams or laps (exclusive of the longitudinal joint in cored electrodes), and foreign matter that would adversely affect the welding characteristics, the operation of the welding equipment or the properties of the weld metal.

14.2.2 Each continuous length of electrode shall be from a single lot of material, and welds, when present, shall have been made so as not to interfere with the uniform, uninterrupted feeding of the electrode on automatic equipment.

14.2.3 The core ingredients in composite electrodes shall be distributed with sufficient uniformity throughout the length of the electrode so as not to adversely affect the performance of the electrode or the properties of the weld metal.

14.2.4 A suitable protective coating may be applied to any of the electrodes in this specification.


14.3 Standard Package Forms

14.3.1 Standard package forms are coils with support, coils without support, spools, and drums. Standard package dimensions and weights for each form are

given in Table 8 and Figure 6. Package forms, sizes and weights other than these shall be as agreed between purchaser and supplier.

14.3.2 The liners in coils with support shall be designed and constructed to prevent distortion of the coil during normal handling and use, and shall be clean and dry enough to maintain the cleanliness of the electrode.

14.3.3 Spools shall be designed and constructed to prevent distortion of the electrode during normal handling and use and shall be clean and dry enough to maintain the cleanliness of the electrode.

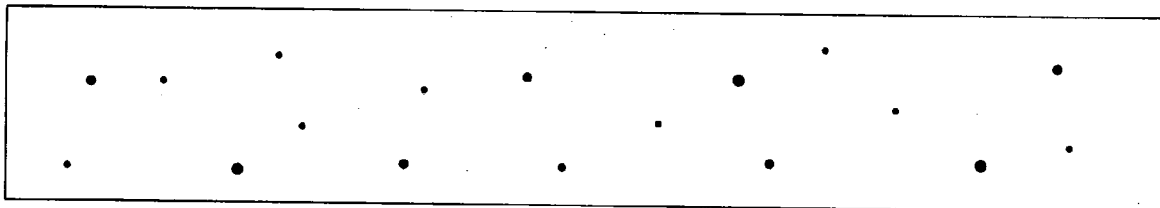

(A) ASSORTED POROSITY AND/OR INCLUSIONS


Size 1/64 in. (0.4 mm) to 1/16 in. (1.6 mm) diameter or in length

Maximum number of indications in any 6 in. (150 mm) of weld = 18, with the following restrictions:

Maximum number of large 3/64 in. (1.2 mm) to 1/16 in. (1.6 mm) diameter and/or length indications = 3

Maximum number of medium 1/32 in. (0.8 mm) to 3/64 in. (1.2 mm) diameter and/or length indications = 5

Maximum number of small 1/64 in. (0.4 mm) to 1/32 in. (0.8 mm) diameter and/or length indications = 10

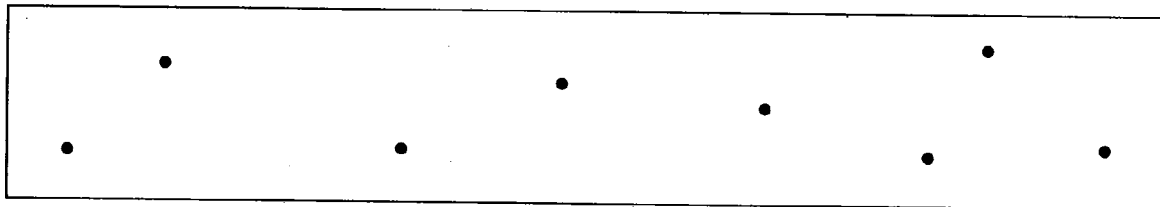

(B) LARGE POROSITY AND/OR INCLUSIONS

Size 3/64 in. (1.2 mm) to 1/16 in. (1.6 mm) diameter and/or length


Maximum number of indications in any 6 in. (150 mm) of weld = 8

Notes:


1. In using these standards, the chart which is most representative of the size of the porosity and/or inclusions present in the test specimen radiograph shall be used for determining conformance to these radiographic standards.
2. Since these are test welds specifically made in the laboratory for classification purposes, the radiographic requirements for these test welds are more rigid than those which may be required for general fabrication.
3. Indications whose largest dimension does not exceed 1/64 in. (0.4 mm) shall be disregarded.

Figure 4 — Radiographic Acceptance Standards

10

**(C) MEDIUM POROSITY AND/OR INCLUSIONS**

Size 1/32 in. (0.8 mm) to 3/64 in. (1.2 mm) diameter and/or length
 Maximum number of indications in any 6 in. (150 mm) of weld = 15

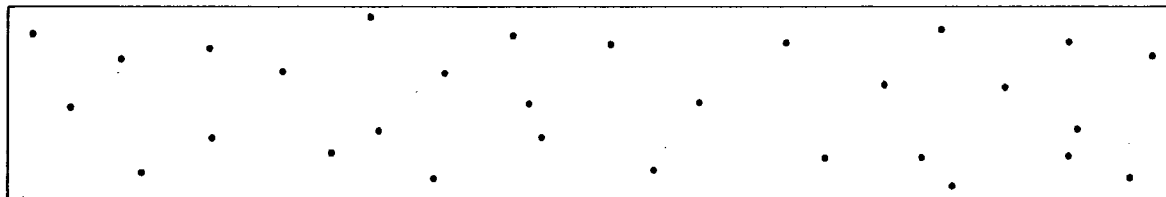**(D) SMALL POROSITY AND/OR INCLUSIONS**

Size 1/64 in. (0.4 mm) to 1/32 in. (0.8 mm) diameter and/or length
 Maximum number of indications in any 6 in. (150 mm) of weld = 30


Notes:

1. In using these standards, the chart which is most representative of the size of the porosity and/or inclusions present in the test specimen radiograph shall be used for determining conformance to these radiographic standards.
2. Since these are test welds specifically made in the laboratory for classification purposes, the radiographic requirements for these test welds are more rigid than those which may be required for general fabrication.
3. Indications whose largest dimension does not exceed 1/64 in. (0.4 mm) shall be disregarded.

Figure 4 (continued) — Radiographic Acceptance Standards

Table 7					
Standard Sizes*					
Standard Package Form	Diameter		Tolerance		
	in.	mm	in.	mm	
Coils with support	1/16	(.062)	1.6	± 0.002	± 0.05
Coils without support	5/64	(.078)	2.0	± 0.003	± 0.08
	3/32	(.094)	2.4		
Drums	.120	3.0	± 0.004	± 0.10	
Spools	1/8	(.125)			
	5/32	(.156)	4.0		

*Dimensions, tolerances and package forms other than those shown shall be as agreed by purchaser and supplier.

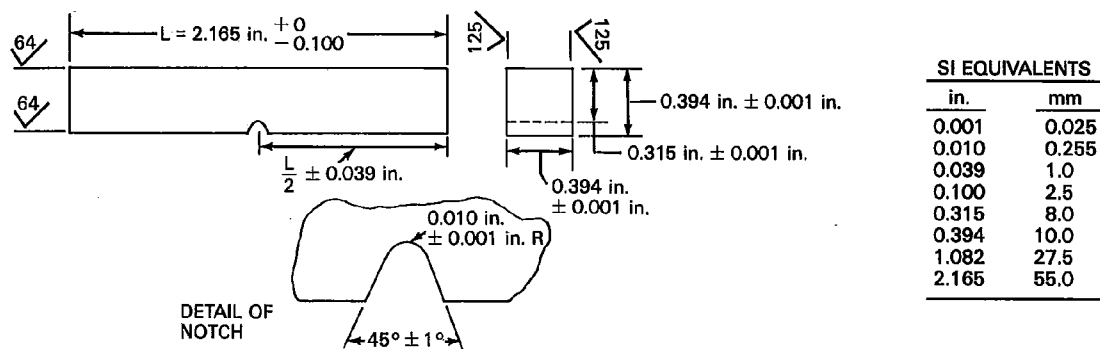

Notes:

1. The notched surface and the surface to be struck shall be parallel within 0.002 in. (0.05 mm) and have at least 64 μ in. (1.6 μ m) finish. The other two surfaces shall be square with the notched or struck surface within ± 10 minutes of the degree and have at least 125 μ in. (3.2 μ m) finish.
2. The notch shall be smoothly cut by mechanical means and shall be square with the longitudinal edge of the specimen within one degree.
3. The geometry of the notch shall be measured on at least one specimen in a set of five specimens. Measurement shall be done at minimum 50 times magnification on either a shadowgraph or a metallograph.
4. The correct location of the notch shall be verified by etching before or after machining.
5. If a specimen does not break upon being struck, the value for energy absorbed shall be reported as the capacity of the impact testing machine followed by a plus sign (+).

Figure 5 — Charpy V-Notch Impact Test Specimen

14.4 Winding Requirements

14.4.1 Electrodes shall be wound so that kinks, waves, sharp bends, overlapping, or wedging are not encountered, leaving the electrode free to unwind without restriction. The outside end of the electrode (the end with which welding is to begin) shall be identified so it can be located readily, and shall be fastened to avoid unwinding.

14.4.2 The cast and helix of electrode in coils, spools and drums shall be such that the electrode will feed in an uninterrupted manner on automatic equipment.

14.5 Electrode Identification

14.5.1 The product information and the precautionary information required in 14.7 for marking each package shall also appear on each coil, spool, and drum.

14.5.2 Coils without support shall have a tag containing this information securely attached to the electrode at the inside end of the coil.

14.5.3 Coils with support shall have the information securely affixed in a prominent location on the support.

14.5.4 Spools shall have the information securely affixed in a prominent location on the outside of at least one flange of the spool.

14.5.5 Drums shall have the information securely affixed in a prominent location on the side of the drum.

14.6 Packaging. Electrodes shall be suitably packaged to ensure against damage during shipment and storage under normal conditions.

14.7 Marking of Packages

14.7.1 The following product information (as a minimum) shall be legibly marked so as to be visible from the outside of each unit package.

(1) AWS Specification and Classification (year of issue may be excluded)

(2) Supplier's name and trade designation. In the case of a composite metal cored electrode, the trade designation of the flux (or fluxes) with which it meets the requirements of Table 2.

(3) Size and net weight

(4) Lot, control, or heat number

14.7.2 The following precautionary information (as a minimum) shall be prominently displayed in legible print on all packages of electrodes including individual unit packages enclosed within a larger package.

WARNING:

Protect yourself and others.

Read and understand this information.

FUMES AND GASES can be dangerous to your health.

ARC RAYS can injure eyes and burn skin.

ELECTRIC SHOCK can kill.

- Read and understand the manufacturer's instructions, the Material Safety Data Sheets (MSDSs), and your employer's safety practices.
- Keep your head out of the fumes.
- Use enough ventilation, exhaust at the arc, or both, to keep fumes and gases away from your breathing zone and the general area.
- Wear correct eye, ear, and body protection.
- Do not touch live electrical parts.
- See American National Standard Z49.1, *Safety in Welding and Cutting*, published by the American Welding Society, 550 N.W. LeJeune Road, P.O. Box 351040, Miami, Florida, 33135 and OSHA Safety and Health Standards, 29 CFR 1910, available from the U.S. Government Printing Office, Washington, DC 20402.

DO NOT REMOVE THIS INFORMATION

15. Flux Requirements

15.1 Form and Particle Size. Flux shall be granular in form and shall be capable of flowing freely through the flux feeding tubes, valves, and nozzles of standard electroslag welding equipment. Particle size is not specified in this specification, but, when it is addressed, it shall be a matter of agreement between the purchaser and the supplier.

15.2 Usability. The flux shall permit the production of uniform, well shaped beads that merge smoothly with the base metal. The molten slag shall have electrical properties suitable for electroslag operation.

15.3 Packaging

15.3.1 Flux shall be suitably packaged to ensure against damage during shipment.

15.3.2 Flux, in its original unopened container, shall withstand storage under normal conditions for at least six months without damage to its welding characteristics

or the properties of the weld. Heating of the flux to assure dryness may be necessary to obtain the very best operation and properties of which the materials are capable. When drying (reconditioning) is necessary, the supplier should be consulted for a recommended procedure.

15.4 Marking of Packages

15.4.1 The following product information (as a minimum) shall be legibly marked so as to be visible from the outside of each unit package.

(1) AWS specification and classification for the appropriate flux-electrode combination (year of issue may be excluded)

(2) Supplier's name and trade designation (brand name)

(3) The trade designation of each composite electrode with which the flux manufacturer has classified the flux, if applicable

(4) Net weight

(5) Lot or control number

(6) Particle size, if more than one size is produced

15.4.2 The following precautionary information (as a minimum) shall be prominently displayed in legible print on all packages of welding material, including individual unit packages enclosed within a larger package:

WARNING:

Protect yourself and others.

Read and understand this information.

FUMES AND GASES can be dangerous to your health.

ARC RAYS can injure eyes and burn skin.

ELECTRIC SHOCK can kill.

- Read and understand the manufacturer's instructions, the Material Safety Data Sheets (MSDSs), and your employer's safety practices.
- Keep your head out of the fumes.
- Use enough ventilation, exhaust at the arc, or both, to keep fumes and gases away from your breathing zone and the general area.
- Wear correct eye, ear, and body protection.
- Do not touch live electrical parts.
- See American National Standard Z49.1, *Safety in Welding and Cutting*, published by the American Welding Society, 550 N.W. LeJeune Road, P.O. Box 351040, Miami, Florida, 33135 and OSHA Safety and Health Standards, 29 CFR 1910, available from the U.S. Government Printing Office, Washington, DC 20402.

DO NOT REMOVE THIS INFORMATION

Table 8
Standard Package Dimensions and Weights^a


Type of Package	Package Size		Net Weight of Electrode ^b	
	in.	mm	lb	kg
Coils without support	(c)		(c)	
Coils with support (See below)	12	300 ID ^d	50, 60 and 65	23, 27 and 30
	23-1/2	600 ID	150 and 200	68 and 91
Spools	12	300 OD ^d	25, 30, 35, and 44	11, 14, 16 and 20
	14	360 OD	50 and 60	23 and 27
	22	560 OD	250	110
	24	610 OD	300	140
	30	760 OD	600 and 750	270 and 340
Drums	15-1/2	400 OD	(c)	
	20	500 OD	(c)	
	23	600 OD	300 and 600	140 and 270

Coils with Support—Standard Dimensions and Weights^a

Electrode Size	Coil Net Weight ^b		Coil Dimensions			
			Inside Dia. of Lining		Width of Wound Electrode	
	lb	kg	in.	mm	in. max.	mm, max.
All	50, 60, and 65	23, 27, and 30	12 ± 1/8	305 ± 3	4-5/8	120
	150 and 200	68 and 91	23-1/2 ± 1/4	600 ± 6	5	125

Notes:

- Sizes and net weights other than those specified shall be as agreed between supplier and purchaser.
- Tolerance on net weight shall be ± 10 percent.
- As agreed by supplier and purchaser.
- ID = inside diameter; OD = outside diameter.

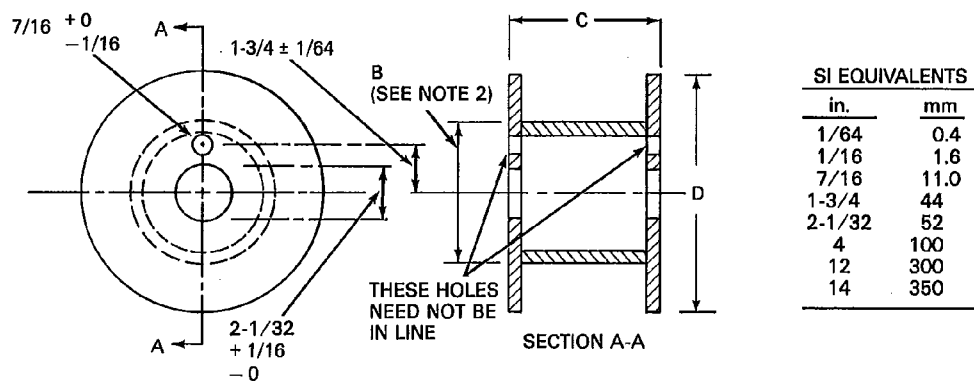


Dimensions		
Spool size in.	C in.	D, maximum in.
12	$4 \pm 1/16$	12
14	$4 \pm 1/16$	14

Notes:

1. All dimensions are in inches.
2. Dimension B, outside diameter of barrel, shall be such as to permit proper feeding of the electrodes.

Figure 6A — Dimensions of 12 and 14 in. (300 and 350 mm) Standard Spools

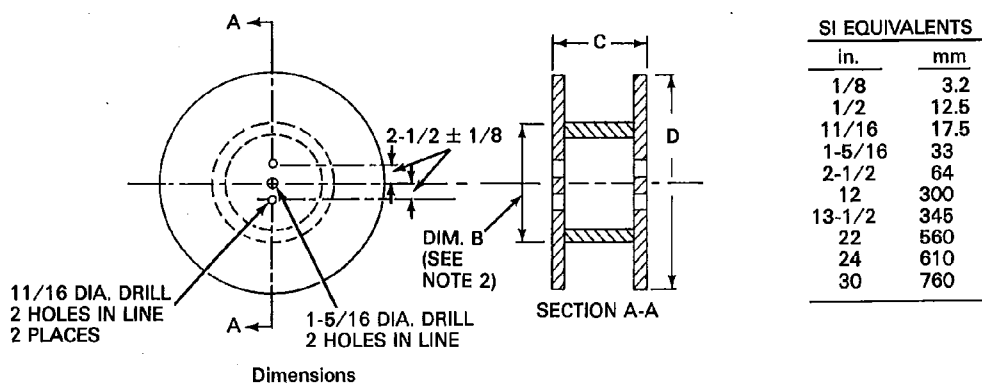

Dimensions		
Spool size in.	D in.	C, maximum in.
22	$22 \pm 1/2$	12
24	$24 \pm 1/2$	13-1/2
30	$30 \pm 1/2$	13-1/2

Notes:

1. All dimensions are in inches.
2. Dimension B, outside diameter of barrel, shall be such as to permit proper feeding of the electrode.

Figure 6B — Dimensions of 22, 24, and 30 in. (560, 610, and 760 mm) Standard Spools (Reels)

Appendix

Guide to ANSI/AWS A5.25-91, Specification for Carbon and Low Alloy Steel Electrodes and Fluxes for Electroslag Welding

(This Appendix is not a part of ANSI/AWS A5.25-91, *Specification for Carbon and Low Alloy Steel Electrodes and Fluxes for Electroslag Welding*, but is included for information only.)

A1. Introduction

The purpose of this guide is to correlate the electrode and flux classifications with their intended applications so the specification can be used effectively. Reference to appropriate base metal specifications is made whenever that can be done and when it would be helpful. Such references are intended only as examples rather than complete listings of the materials for which each filler metal is suitable.

A2. Classification System

A2.1 Classification of Electrodes. The system for identifying the electrode classifications in this specification follows the standard pattern used in other AWS filler metal specifications. The letter "E" at the beginning of each classification designation stands for electrode. The remainder of the designation indicates the chemical composition of the electrode, or, in the case of composite metal cored electrodes, of the undiluted weld metal obtained with a particular flux. See Figure A1.

The letter "M" indicates that the solid electrode is of a medium manganese content, while the letter "H" would indicate a comparatively high manganese content. The one or two digits following the manganese designator indicate the nominal carbon content of the electrode. The letter "K", which appears in some designations, indicates that the electrode is made from a heat of silicon-killed steel. The designation for a solid wire is followed by the suffix "EW". Solid electrodes are classified only on the basis of their chemical composition, as specified in Table 1 of this specification. A composite electrode is indicated by the letters "WT" after the "E",

and a numerical suffix. The composition of a composite electrode is meaningless, and the user is therefore referred to weld metal composition (Table 2) with a particular flux, rather than to electrode composition.

A comparison of solid electrode classifications in this specification and those of other specifications is shown in Table A1.

A2.2 Classification of Fluxes. Fluxes are classified on the basis of the mechanical properties of the weld metal made with some certain classification of electrode, under the specific test conditions called for in this specification.

As examples of flux classifications, consider the following:

FES60-EH14-EW

FES72-EWT2

The prefix "FES" designates a flux for electroslag welding. This is followed by a single digit representing the minimum tensile strength required of the weld metal in 10 000 psi (see Table 3).

The digit that follows is a number or the letter "Z". This digit refers to the impact strength of the weld metal. Specifically it designates the temperature at (and above) which the weld metal meets, or exceeds, the required 15 ft-lb (20 J) Charpy V-notch impact strength (except for the letter "Z", which indicates that no impact strength requirement is specified (see Table 4). These mechanical property designators are followed by the designation of the electrode used in classifying the flux (see Tables 1 and 2). The suffix (EM12-EW, EH10K-EW, EWT2, etc.) included after the first hyphen refers to the electrode classification with which the flux will produce weld metal that meets the specified mechanical properties when tested as called for in the specification.

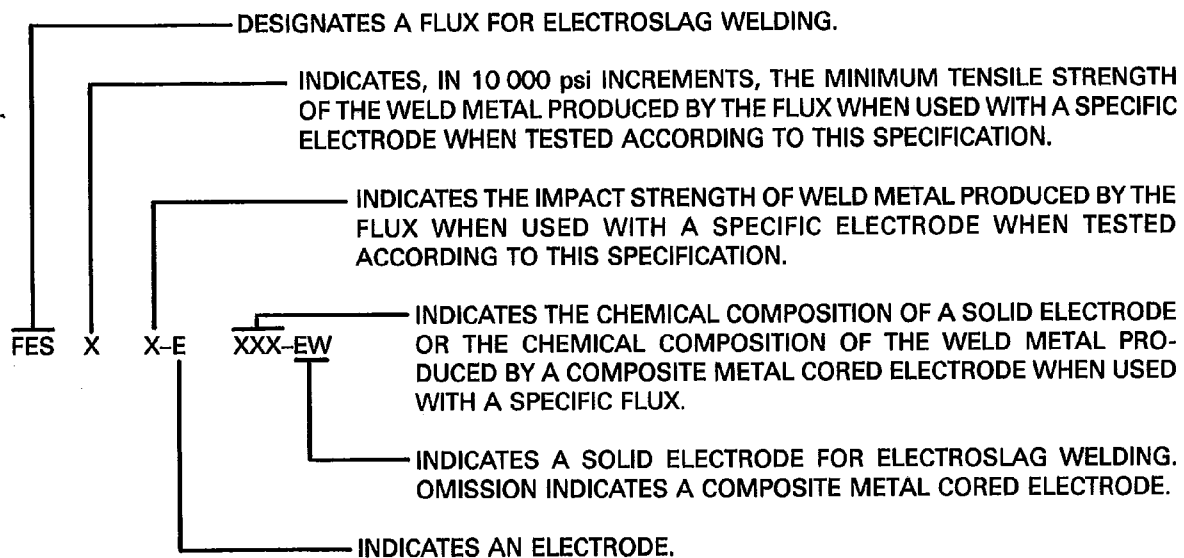


Figure A1 — Classification System

Table A1
Comparison of A5.25-91 Classifications and
Classifications in Other AWS Specifications

AWS A5.25-91 Classification	Similar Classifications*			
	AWS A5.17-89	AWS A5.18-79	AWS A5.23-90	AWS A5.28-79
EM5K-EW	—	ER70S-2	—	—
EM12-EW	EM12	—	—	—
EM12K-EW	EM12K	—	EM12K	—
EM13K-EW	EM13K	ER70S-3	—	—
EM15K-EW	EM15K	—	—	—
EH14-EW	EH14	—	—	—
EWS-EW	—	—	EW	—
EH10Mo-EW	—	—	EA3K	ER80S-D2
EH10K-EW	—	—	—	—
EH11K-EW	EH11K	ER70S-6	—	—

*Classifications are similar, but not necessarily identical in composition:

AWS A5.17-89, *Specification for Carbon Steel Electrodes and Fluxes for Submerged Arc Welding*

AWS A5.18-79, *Specification for Carbon Steel Filler Metals for Gas Shielded Arc Welding*

AWS A5.23-90, *Specification for Low Alloy Steel Electrodes and Fluxes for Submerged Arc Welding*

AWS A5.28-79, *Specification for Low Alloy Steel Filler Metals for Gas Shielded Arc Welding*

It should be noted that flux of any specific trade designation may have many classifications. The number is limited only by the number of different electrode classifications with which the flux can meet the classification requirements. The flux marking lists at least one, and may list all, classifications to which the flux conforms. Solid electrodes having the same classification are interchangeable when used with a specific flux; composite metal cored electrodes may not be. However, the specific usability (or operating) characteristics of various fluxes of the same classification may differ in one respect or another.

A2.3 "G" Classification

A2.3.1 This specification includes filler metals classified as ES-G-EW or EWTG. The letter "G" indicates that the filler metal is of a general classification. It is general because not all of the particular requirements specified for each of the other classifications are specified for this classification. The intent, in establishing this classification is to provide a means by which filler metals that differ in one respect or another (chemical composition, for example) from all other classifications (meaning that the composition of the filler metal—in the case of the example—does not meet the composition specified for any of the classifications in the specification) can still be classified according to the specification. The purpose is to allow a useful filler metal—one that otherwise would have to await a revision of the specification—to be classified immediately, under the existing specification. This means, then, that two filler metals—each bearing the same "G" classification—may be quite different in some certain respect (chemical composition, again, for example).

A2.4 The point of difference (although not necessarily the amount of the difference) referred to above will be readily apparent from the use of the words "not required" and "not specified" in the specification. The use of these words is as follows:

"Not Specified" is used in those areas of the specification that refer to the results of some particular test. It indicates that the requirements for that test are not specified for that particular classification.

"Not Required" is used in those areas of the specification that refer to the test that must be conducted in order to classify a filler metal (or a welding flux). It indicates that test is not required because the requirements (results) for the test have not been specified for that particular classification. Restating the case, when a requirement is not specified, it is not necessary to conduct the corresponding test in order to classify a filler metal to that classification. When a purchaser wants the information provided by that test, in order to consider a

particular product of that classification for a certain application, the purchaser will have to arrange for that information with the supplier. The purchaser and supplier also will have to establish the specific testing procedure and the acceptance requirements. These may be incorporated (via A5.01, *Filler Metal Procurement Guidelines*) in the purchase order.

A3. Acceptance

Acceptance of all welding materials classified under this specification is in accordance with AWS A5.01, *Filler Metal Procurement Guidelines*, as the specification states. Any testing a purchaser requires of the supplier, for material shipped in accordance with this specification, shall be clearly stated in the purchase order, according to the provisions of AWS A5.01, *Filler Metal Procurement Guidelines*. In the absence of any such statement in the purchase order, the supplier may ship the material with whatever testing normally is conducted on material of that classification, as specified in Schedule F, Table 1, of AWS A5.01, *Filler Metal Procurement Guidelines*. Testing in accordance with any other Schedule in that Table shall be specifically required by the purchase order. In such cases, acceptance of the material shipped shall be in accordance with those requirements.

A4. Certification

The act of placing the AWS Specification and Classification designations on the packaging enclosing the product or the classification on the product itself, constitutes the supplier's (manufacturer's) certification that the product meets all of the requirements of the specification. The only testing requirement implicit in the certification is that the manufacturer has actually conducted the tests required by the specification on material that is representative of that being shipped and that material met the requirements of the specification.

Representative material, in this case, is any production run of that classification using the same formulation. "Certification" is not to be construed to mean that tests of any kind were necessarily conducted on samples of the specific material shipped. Tests on such material may or may not have been conducted. The basis for the certification required by the specification is the classification test of "representative material" cited above, and the "Manufacturer's Quality Assurance Program" in AWS A5.01, *Filler Metal Procurement Guidelines*.

A5. Ventilation During Welding

A5.1 Five major factors govern the quantity of fumes in the atmosphere to which welders and welding operators are exposed during welding:

- (1) Dimensions of the space in which welding is done (with special regard to the height of the ceiling)
- (2) Number of welders and welding operators working in that space
- (3) Rate of evolution of fumes, gases, or dust, according to the materials and processes used
- (4) The proximity of the welders or welding operators to the fumes as the fumes issue from the welding zone, and to the gases and dusts in the space in which they are working
- (5) The ventilation provided to the space in which the welding is done

A5.2 American National Standard Z49.1, *Safety in Welding and Cutting* (published by the American Welding Society), discusses the ventilation that is required during welding and should be referred to for details. Attention is drawn particularly to the section of that document on Health Protection and Ventilation.

A6. Definition and General Description

Electroslag welding is a process producing coalescence of metals with molten slag which melts the filler metal and the surfaces of the workpiece to be welded. The process is initiated by an arc which heats the slag. The arc is then extinguished by the conductive slag which is kept molten by its resistance to electric current passing between the electrode and the workpiece. The weld pool is shielded by this slag which covers the full cross section of the joint as welding progresses. The joint is generally welded in a single pass.

A6.1 Principles of Operation (Conventional Method)

A6.1.1 The process is initiated by starting an arc beneath a layer of granular welding flux. As soon as a sufficiently thick layer of hot molten slag is formed, all arc action stops and current passes from the electrode to the workpiece through the conductive slag. Heat generated by the resistance to the current through the molten slag is sufficient to fuse the edges of the workpiece and melt the welding electrode.

Since no arc exists, the welding action is quiet and spatter-free. The liquid metal coming from the filler metal and the fused base metal collects in a pool beneath the slag bath and slowly solidifies to form the weld.

A6.1.2 Because of the necessity to contain the large volume of molten slag and weld metal produced in electroslag welding, the process is used for welding in the

vertical position. Water-cooled or solid copper backing shoes are usually used on each side of the joint to retain the molten metal and slag pool and to act as a mold to cool and shape the weld faces. The copper backing shoes are normally moved upward on the plate surfaces as welding progresses.

A6.1.3 The entire assembly—including electrode, copper shoes, wire-feeding mechanism, controls, and oscillator—generally moves vertically during operation. The length of vertical travel is unlimited and is dependent upon the design of the equipment used.

A6.1.4 Because of the uniform heat distribution throughout the plate thickness during welding, electroslag welds are virtually free of axial or transverse distortion; however, the joint may contract. The weld interface contour is a function of the welding voltage, current and slag pool depth. The weld metal usually consists of approximately 30 to 50% of base metal.

A6.1.5 The standard joint preparation is a square groove in a butt joint. Joint preparations other than square grooves in butt joints can be used.

A6.2 Principles of Operation (Consumable Guide Method)

A6.2.1 The consumable guide method uses a metal tube extending the full length of the weld joint to guide the electrode to the welding zone. The molds and all wire-feeding equipment remain stationary, with the electrode being the only moving part. The guide tube melts into the weld pool as the pool rises, supplying additional filler metal.

A6.2.2 A flux coating is sometimes provided on the outside of the consumable guide to insulate the tube if it should contact the base metal or copper backing shoes. The coating also helps to replenish flux that solidifies on the surface of the copper shoes forming the weld face contour. The flux coating thus helps to maintain a level of molten slag adequate to provide resistance heating and to protect the weld pool from atmospheric contamination. The manufacturer should be consulted for specific recommendations regarding consumable guide tubes.

A6.2.3 The effect of the consumable guide tube generally is to dilute the alloy content of the weld metal. For this reason, weld metal strength and toughness should be determined.

A6.3 The specification requires the use of certain base metals for classification purposes. This does not signify any restriction on the application of the process for joining other base metals, but rather provides a means

for obtaining reproducible results. Electroslag welding is a "high dilution" process, meaning that the base metal forms a significant portion of the weld metal. The type of base metal, especially given the wide variety of available low alloy structural steels, will influence the mechanical and other properties of the joint. Weld procedure qualification tests, as distinguished from filler metal classification tests, should be used for assessing the properties of welds for a given application.

A6.4 Electroslag welding is a high deposition process for thick plates. Since it usually is operated as a single pass process, the weld metal and heat-affected zone are subject to no subsequent weld thermal cycles, such as is

common with arc welding of thick materials. The weld metal is characterized by large unrefined dendrites. The relatively wide heat-affected zone is characterized by large grains. The as-welded mechanical properties may therefore be somewhat lower than that of the base metal. This specification requires a minimum of 15 ft-lb (20 J) at the specified temperature while most other AWS filler metal specifications require 20 ft-lb (27 J). Considerable improvement in mechanical properties can be effected by a postweld heat treatment. Subcritical stress relieving heat treatments are generally less effective for electroslag welding than for arc welding. For this reason, many code requirements require an austenitizing, or normalizing, postweld heat treatment.

AWS Filler Metal Related Documents

AWS Designation	Title
FMC	Filler Metal Comparison Charts
A4.2	Standard Procedures for Calibrating Magnetic Instruments to Measure the Delta Ferrite Content of Austenitic Stainless Steel Weld Metal
A4.3	Standard Methods for Determination of the Diffusible Hydrogen Content of Martensitic, Bainitic, and Ferritic Steel Weld Metal Produced by Arc Welding
A5.01	Filler Metal Procurement Guidelines
A5.1	Specification for Carbon Steel Electrodes for Shielded Metal Arc Welding
A5.2	Specification for Carbon and Low Alloy Steel Rods for Oxyfuel Gas Welding
A5.3	Specification for Aluminum and Aluminum Alloy Electrodes for Shielded Metal Arc Welding
A5.4	Specification for Covered Corrosion-Resisting Chromium and Chromium-Nickel Steel Welding Electrodes
A5.5	Specification for Low Alloy Steel Covered Arc Welding Electrodes
A5.6	Specification for Covered Copper and Copper Alloy Arc Welding Electrodes
A5.7	Specification for Copper and Copper Alloy Bare Welding Rods and Electrodes
A5.8	Specification for Filler Metals for Brazing
A5.9	Specification for Corrosion-Resisting Chromium and Chromium-Nickel Steel Bare and Composite Metal Cored and Stranded Welding Electrodes and Welding Rods
A5.10	Specification for Bare Aluminum and Aluminum Alloy Welding Electrodes and Rods
A5.11	Specification for Nickel and Nickel Alloy Welding Electrodes for Shielded Metal Arc Welding
A5.12	Specification for Tungsten Arc Welding Electrodes
A5.13	Specification for Solid Surfacing Welding Rods and Electrodes
A5.14	Specification for Nickel and Nickel Alloy Bare Welding Electrodes and Rods
A5.15	Specification for Welding Electrodes and Rods for Cast Iron
A5.16	Specification for Titanium and Titanium Alloy Welding Electrodes and Rods
A5.17	Specification for Carbon Steel Electrodes and Fluxes for Submerged Arc Welding
A5.18	Specification for Carbon Steel Filler Metals for Gas Shielded Arc Welding
A5.19	Specification for Magnesium Alloy Welding Rods and Bare Electrodes
A5.20	Specification for Carbon Steel Electrodes for Flux Cored Arc Welding
A5.21	Specification for Composite Surfacing Welding Rods and Electrodes
A5.22	Specification for Flux Cored Corrosion-Resisting Chromium and Chromium-Nickel Steel Electrodes
A5.23	Specification for Low Alloy Steel Electrodes and Fluxes for Submerged Arc Welding
A5.24	Specification for Zirconium and Zirconium Alloy Welding Electrodes and Rods
A5.25	Specification for Carbon and Low Alloy Steel Electrodes and Fluxes for Electroslag Welding
A5.26	Specification for Carbon and Low Alloy Steel Electrodes for Electrode Gas Welding
A5.27	Specification for Copper and Copper Alloy Rods for Oxyfuel Gas Welding
A5.28	Specification for Low Alloy Steel Filler Metals for Gas Shielded Arc Welding
A5.29	Specification for Low Alloy Steel Electrodes for Flux Cored Arc Welding
A5.30	Specification for Consumable Inserts

For additional information, contact the Order Department, American Welding Society, 550 N.W. LeJeune Road, P.O. Box 351040, Miami, Florida 33135.