

AWS A5.34/A5.34M:2007
An American National Standard

Specification for Nickel-Alloy Electrodes for Flux Cored Arc Welding



American Welding Society



AWS A5.34/A5.34M:2007
An American National Standard

Approved by the
American National Standards Institute
July 12, 2007

Specification for Nickel-Alloy Electrodes for Flux Cored Arc Welding

1st Edition

Prepared by the
American Welding Society (AWS) A5 Committee on Filler Metals and Allied Materials

Under the Direction of the
AWS Technical Activities Committee

Approved by the
AWS Board of Directors

Abstract

The composition, soundness, and properties of weld metal from nine grades of flux cored electrodes are specified. Standard electrode sizes together with their package forms and package sizes are detailed.

This specification makes use of both U.S. Customary Units and the International System of Units (SI). Since these are not equivalent, each system must be used independently of the other.



American Welding Society

550 N.W. LeJeune Road, Miami, FL 33126

International Standard Book Number: 978-0-87171-072-7

American Welding Society

550 N.W. LeJeune Road, Miami, FL 33126

© 2007 by American Welding Society

All rights reserved

Printed in the United States of America

Photocopy Rights. No portion of this standard may be reproduced, stored in a retrieval system, or transmitted in any form, including mechanical, photocopying, recording, or otherwise, without the prior written permission of the copyright owner.

Authorization to photocopy items for internal, personal, or educational classroom use only or the internal, personal, or educational classroom use only of specific clients is granted by the American Welding Society provided that the appropriate fee is paid to the Copyright Clearance Center, 222 Rosewood Drive, Danvers, MA 01923, tel: (978) 750-8400; Internet: <www.copyright.com>.

Statement on the Use of American Welding Society Standards

All standards (codes, specifications, recommended practices, methods, classifications, and guides) of the American Welding Society (AWS) are voluntary consensus standards that have been developed in accordance with the rules of the American National Standards Institute (ANSI). When AWS American National Standards are either incorporated in, or made part of, documents that are included in federal or state laws and regulations, or the regulations of other governmental bodies, their provisions carry the full legal authority of the statute. In such cases, any changes in those AWS standards must be approved by the governmental body having statutory jurisdiction before they can become a part of those laws and regulations. In all cases, these standards carry the full legal authority of the contract or other document that invokes the AWS standards. Where this contractual relationship exists, changes in or deviations from requirements of an AWS standard must be by agreement between the contracting parties.

AWS American National Standards are developed through a consensus standards development process that brings together volunteers representing varied viewpoints and interests to achieve consensus. While AWS administers the process and establishes rules to promote fairness in the development of consensus, it does not independently test, evaluate, or verify the accuracy of any information or the soundness of any judgments contained in its standards.

AWS disclaims liability for any injury to persons or to property, or other damages of any nature whatsoever, whether special, indirect, consequential or compensatory, directly or indirectly resulting from the publication, use of, or reliance on this standard. AWS also makes no guaranty or warranty as to the accuracy or completeness of any information published herein.

In issuing and making this standard available, AWS is neither undertaking to render professional or other services for or on behalf of any person or entity, nor is AWS undertaking to perform any duty owed by any person or entity to someone else. Anyone using these documents should rely on his or her own independent judgment or, as appropriate, seek the advice of a competent professional in determining the exercise of reasonable care in any given circumstances.

This standard may be superseded by the issuance of new editions. Users should ensure that they have the latest edition.

Publication of this standard does not authorize infringement of any patent or trade name. Users of this standard accept any and all liabilities for infringement of any patent or trade name items. AWS disclaims liability for the infringement of any patent or product trade name resulting from the use of this standard.

Finally, AWS does not monitor, police, or enforce compliance with this standard, nor does it have the power to do so.

On occasion, text, tables, or figures are printed incorrectly, constituting errata. Such errata, when discovered, are posted on the AWS web page (www.aws.org).

Official interpretations of any of the technical requirements of this standard may only be obtained by sending a request, in writing, to the appropriate technical committee. Such requests should be addressed to the American Welding Society, Attention: Managing Director, Technical Services Division, 550 N.W. LeJeune Road, Miami, FL 33126 (see Annex B). With regard to technical inquiries made concerning AWS standards, oral opinions on AWS standards may be rendered. These opinions are offered solely as a convenience to users of this standard, and they do not constitute professional advice. Such opinions represent only the personal opinions of the particular individuals giving them. These individuals do not speak on behalf of AWS, nor do these oral opinions constitute official or unofficial opinions or interpretations of AWS. In addition, oral opinions are informal and should not be used as a substitute for an official interpretation.

This standard is subject to revision at any time by the AWS A5 Committee on Filler Metals and Allied Materials. It must be reviewed every five years, and if not revised, it must be either reaffirmed or withdrawn. Comments (recommendations, additions, or deletions) and any pertinent data that may be of use in improving this standard are required and should be addressed to AWS Headquarters. Such comments will receive careful consideration by the AWS A5 Committee on Filler Metals and Allied Materials and the author of the comments will be informed of the Committee's response to the comments. Guests are invited to attend all meetings of the AWS A5 Committee on Filler Metals and Allied Materials to express their comments verbally. Procedures for appeal of an adverse decision concerning all such comments are provided in the Rules of Operation of the Technical Activities Committee. A copy of these Rules can be obtained from the American Welding Society, 550 N.W. LeJeune Road, Miami, FL 33126.

This page is intentionally blank.

Personnel

AWS A5 Committee on Filler Metals and Allied Materials

D. A. Fink, Chair	<i>The Lincoln Electric Company</i>
J. S. Lee, 1st Vice Chair	<i>CB&I</i>
H. D. Wehr, 2nd Vice Chair	<i>Arcos Industries, LLC</i>
R. Gupta, Secretary	<i>American Welding Society</i>
J. M. Blackburn	<i>Naval Sea Systems Command</i>
R. Brown	<i>RSB Alloy Applications, LLC</i>
J. C. Bundy	<i>Hobart Brothers Company</i>
R. J. Christoffel	<i>Consultant</i>
D. D. Crockett	<i>The Lincoln Electric Company</i>
J. J. DeLoach Jr.	<i>Naval Surface Warfare Center</i>
D. A. DelSignore	<i>Consultant</i>
J. DeVito	<i>ESAB Welding and Cutting Products</i>
H. W. Ebert	<i>Consultant</i>
D. M. Fedor	<i>The Lincoln Electric Company</i>
J. G. Feldstein	<i>Foster Wheeler North America</i>
S. E. Ferree	<i>ESAB Welding and Cutting Products</i>
G. L. Franke	<i>Naval Surface Warfare Center</i>
R. D. Fuchs	<i>Bohler Thyssen Welding USA, Incorporated</i>
C. E. Fuerstenau	<i>Lucas-Milhaupt, Incorporated</i>
J. A. Henning	<i>Nuclear Management Company</i>
R. M. Henson	<i>J. W. Harris Company, Incorporated</i>
M. Q. Johnson	<i>Los Alamos National Laboratory</i>
S. D. Kiser	<i>Special Metals</i>
P. J. Konkol	<i>Concurrent Technologies Corporation</i>
D. J. Kotecki	<i>The Lincoln Electric Company</i>
L. Kvidahl	<i>Northrop Grumman Ship Systems</i>
A. Y. Lau	<i>Canadian Welding Bureau</i>
A. S. Laurenson	<i>Consultant</i>
W. A. Marttila	<i>DaimlerChrysler Corporation</i>
R. Menon	<i>Stoody Company</i>
M. T. Merlo	<i>Edison Welding Institute</i>
D. R. Miller	<i>ABS Americas Materials Department</i>
B. Mosier	<i>Polymet Corporation</i>
A. K. Mukherjee	<i>Siemens Power Generation, Incorporated</i>
C. L. Null	<i>Consultant</i>
M. P. Parekh	<i>Consultant</i>
R. L. Peaslee	<i>Wall Colmonoy Corporation</i>
S. D. Reynolds, Jr.	<i>Consultant</i>
P. K. Salvesen	<i>Det Norske Veritas (DNV)</i>
K. Sampath	<i>Consultant</i>
W. S. Severance	<i>ESAB Welding and Cutting Products</i>
M. J. Sullivan	<i>NASSCO—National Steel and Shipbuilding</i>
R. Sutherlin	<i>ATI Wah Chang</i>
R.A. Swain	<i>Euroweld, Limited</i>
R. D. Thomas, Jr.	<i>R. D. Thomas and Company</i>
K. P. Thornberry	<i>Care Medical, Incorporated</i>
L. T. Vernam	<i>AlcoTec Wire Corporation</i>

Advisors to the AWS A5 Committee on Filler Metal and Allied Materials

R. L. Bateman	<i>Electromanufacturas, S. A.</i>
R. A. Daemen	<i>Consultant</i>
J. P. Hunt	<i>Consultant</i>
S. Imaoka	<i>Kobe Steel Limited</i>
M. A. Quintana	<i>The Lincoln Electric Company</i>
E. R. Stevens	<i>Stevens Welding Consulting</i>
E. S. Surian	<i>National University of Lomas de Zamora</i>

AWS A5E Subcommittee on Nickel and Nickel Alloy Filler Metals

R. D. Fuchs, Chair	<i>Bohler Thyssen Welding USA, Incorporated</i>
J. S. Lee, Vice Chair	<i>CB&I</i>
R. Gupta, Secretary	<i>American Welding Society</i>
D. C. Agarwal	<i>Krupp VDM Technologies</i>
R. B. Brown	<i>RSB Alloy Applications LLC</i>
G. J. Bruch	<i>Siemens Power Generation, Incorporated</i>
R. E. Cantrell	<i>Constellation Energy Group</i>
J. J. DeLoach, Jr.	<i>Naval Surface Warfare Center</i>
K. K. Gupta	<i>Westinghouse Electric Corporation</i>
G. L. Hoback	<i>Haynes International</i>
S. R. Jana	<i>Select Arc, Incorporated</i>
D. D. Kiilunen	<i>Cor-Met, Incorporated</i>
S. D. Kiser	<i>Special Metals</i>
G. A. Kurisky	<i>Consultant</i>
F. B. Lake	<i>ESAB Welding and Cutting Products</i>
W. E. Layo	<i>Midalloy</i>
R. Menon	<i>Stoody Company</i>
R. A. Swain	<i>Euroweld</i>
R. D. Thomas, Jr.	<i>R. D. Thomas and Company</i>
J. F. Turner	<i>Electrode Engineering, Incorporated</i>
H. D. Wehr	<i>Arcos Industries LLC</i>

Advisors to the AWS A5E Subcommittee on Nickel and Nickel Alloy Filler Metals

F. S. Babish	<i>Sandvik Steel Company</i>
D. A. DelSignore	<i>Consultant</i>
P. Ditzel	<i>Parker Hannifin Corporation</i>
V. W. Hartmann	<i>Westinghouse Electric Corporation</i>
J. P. Hunt	<i>Special Metals</i>
S. Imaoka	<i>Kobe Steel Limited</i>
V. van der Mee	<i>Lincoln Electric Europe bv</i>
J. B. Wu	<i>Deloro Stellite Group</i>

Foreword

This foreword is not part of AWS A5.34/A5.34M:2007, *Specification for Nickel-Alloy Electrodes for Flux Cored Arc Welding*, but is included for informational purposes only.

Flux cored arc welding (FCAW) has been a major welding process for the fabrication of carbon, low-alloy, and stainless steel for more than 40 years. Initially, application of the process was limited, to some extent, by: (1) the size of the electrode that could be manufactured; and (2) compositions of weld metal that could be developed using mild steel strip. Manufacturing improvements now permit the manufacture of a much wider range of electrode diameters. Likewise, these improvements permit the use of strip compositions such as stainless steel, aluminum, cobalt, and nickel alloys.

This first specification for nickel-alloy flux cored electrodes represents the state-of-the-art. The AWS Subcommittee on Nickel and Nickel-Alloy Filler Metal recognizes that the recent rapid growth and development in nickel alloy welding will continue. Revision of this specification before the normal five-year period may be necessary to keep abreast of developments.

This document makes use of both U.S. Customary Units and the International System of Units (SI). The measurements are not exact equivalents; therefore each system must be used independently of the other, without combining values in any way. In selecting rational metric units AWS A1.1, *Metric Practice Guide for the Welding Industry*, and ISO 544, *Consumables — Technical delivery conditions for welding filler materials — Type of product, dimensions, tolerances and markings*, are used where suitable. Tables and figures make use of both U.S. Customary and SI Units, which, with the application of the specified tolerances, provides for interchangeability of products in both the U.S. Customary and SI Units.

Comments and suggestions for the improvement of this standard are welcome. They should be sent to the Secretary, AWS A5 Committee on Filler Metals and Allied Materials, American Welding Society, 550 N.W. LeJeune Road, Miami, FL 33126.

This page is intentionally blank.

Table of Contents

	Page No.
<i>Personnel</i>	v
<i>Foreword</i>	vii
<i>List of Tables</i>	x
<i>List of Figures</i>	x
1. Scope	1
2. Normative References	1
3. Classification	2
4. Acceptance	2
5. Certification	2
6. Rounding-Off Procedure	4
7. Summary of Tests	4
8. Retest	4
9. Weld Test Assemblies	4
10. Chemical Analysis	11
11. Radiographic Test	11
12. Tension Test	11
13. Bend Test	11
14. Fillet Weld Test	13
15. Method of Manufacture	13
16. Standard Sizes	13
17. Finish and Uniformity	14
18. Standard Package Forms	14
19. Winding Requirements	16
20. Filler Metal Identification	17
21. Packaging	17
22. Marking of Packages	18
Annex A (Informative)—Guide to AWS Specification for Nickel-Alloy Electrodes for Flux Cored Arc Welding	19
Annex B (Informative)—Guidelines for the Preparation of Technical Inquiries	25
AWS Filler Metal Specifications by Material and Welding Process	27
AWS Filler Metal Specifications and Related Documents	29

List of Tables

Table	Page No.
1 Chemical Composition Requirements for Undiluted Weld Metal	3
2 Required Shielding Gas, Welding Current, and Welding Position	4
3 Required Tests	5
4 Required Base Metals	5
5 Base Metal Specifications	6
6 Tension Test Requirements	13
7 Standard Electrode Sizes and Tolerances	15
8 Standard Package Dimensions and Weights	15
A.1 Comparison of Classifications	21

List of Figures

Figure	Page No.
1 Pad for Chemical Analysis of Undiluted Weld Metal	7
2 Groove Weld Test Assembly for Tension and Radiographic Tests	8
3 Groove Weld for Longitudinal Face-Bend Test	9
4 Fillet Weld Test Assembly	10
5 Radiographic Standards for 3/4 in [19 mm] Test Assembly in Figure 2	12
6 Fillet Weld Test Specimen and Dimensional Requirements	14
7 Dimensions of 4 in, 8 in, 12 in, and 14 in [100 mm, 200 mm, 300 mm, and 350 mm] Standard Spools....	16
8 Dimensions of 22 in, 24 in, and 30 in [560 mm, 610 mm, and 760 mm] Standard Spools (Reels)	17
A.1 A5.34/A5.34M Classification System Utilizing the ISO Format	20
A.2 A5.34/A5.34M Classification System Utilizing the Traditional Format	20

Specification for Nickel-Alloy Electrodes for Flux Cored Arc Welding

1. Scope

1.1 This specification prescribes requirements for the classification of nickel-alloy electrodes for flux cored arc welding. It includes those compositions in which the nickel content exceeds that of any other element, but excludes nickel-base alloy compositions intended for the joining of cast irons.

1.2 Safety and health issues and concerns are beyond the scope of this standard and, therefore, are not fully addressed herein. Some safety and health information can be found in Annex A, Clauses A5 and A10. Safety and health information is available from other sources, including, but not limited to, ANSI Z49.1, *Safety in Welding, Cutting, and Allied Processes*, and applicable federal and state regulations.

1.3 This specification makes use of both U.S. Customary Units and the International System of Units (SI), according to the guidelines in AWS A1.1. The measurements are not exact equivalents; therefore, each system must be used independently of the other without combining in any way when referring to material properties. The specification with the designation A5.34 uses U.S. Customary Units. The specification A5.34M uses SI Units. The latter are shown within brackets [] or in appropriate columns in tables and figures. Standard dimensions based on either system may be used for sizing of filler metal or packaging or both under the A5.34 or A5.34M specification.

2. Normative References

2.1 The following standards contain provisions which, through reference in this text, constitute provisions of this AWS standard. For dated references, subsequent amendments to, or revisions of, any of these publications do not apply. However, parties to agreement based on this AWS standard are encouraged to investigate the

possibility of applying the most recent editions of the documents shown below. For undated references, the latest edition of the standard referred to applies.

2.2 The following AWS standards¹ are referenced in the mandatory clauses of this document:

AWS A1.1, *Metric Practice Guide for the Welding Industry*

AWS A5.01, *Filler Metal Procurement Guidelines*

AWS A5.32/A5.32M, *Specification for Welding Shielding Gases*

AWS B4.0 or AWS B4.0M, *Standard Methods for Mechanical Testing of Welds*

2.3 The following ANSI standard² is referenced in the mandatory clauses of this document:

ANSI Z49.1 *Safety in Welding, Cutting, and Allied Processes*

2.4 The following ASTM standards³ are referenced in the mandatory clauses of this document:

ASTM A 131/A 131M, *Standard Specification for Structural Steel for Ships*

ASTM A 240/A 240M, *Standard Specification for Chromium and Chromium-Nickel Stainless Steel Plate, Sheet, and Strip for Pressure Vessels and for General Applications*

¹ AWS standards are published by the American Welding Society, 550 N.W. LeJeune Road, Miami, FL 33126.

² This ANSI standard is published by the American Welding Society, 550 N.W. LeJeune Road, Miami, FL 33126.

³ ASTM standards are published by the American Society for Testing and Materials, 100 Barr Harbor Drive, West Conshohocken, PA 19428-2959.

ASTM A 515/A 515M, *Standard Specification for Pressure Vessel Plates, Carbon Steel, for Intermediate- and Higher-Temperature Service*

ASTM A 516/A 516M, *Standard Specification for Pressure Vessel Plates, Carbon Steel, for Moderate- and Lower-Temperature Service*

ASTM A 666, *Standard Specification for Annealed or Cold-Worked Austenitic Stainless Steel Sheet, Strip, Plate, and Flat Bar*

ASTM B 166, *Standard Specification for Nickel-Chromium-Iron Alloys (UNS N06600, N06601, N06603, N06690, N06693, N06025, and N06045) and Nickel-Chromium-Cobalt-Molybdenum Alloy (UNS N06617) Rod, Bar, and Wire*

ASTM B 168, *Standard Specification for Nickel-Chromium-Iron Alloys (UNS N06600, N06601, N06603, N06690, N06693, N06025, and N06045) and Nickel-Chromium Cobalt-Molybdenum Alloy (UNS N06617) Plate, Sheet, and Strip*

ASTM B 435, *Standard Specification for UNS N06002, N06230, UNS N12160, and R30556 Plate, Sheet, and Strip*

ASTM B 443, *Standard Specification for Nickel-Chromium-Molybdenum-Columbium Alloy (UNS N06625) and Nickel-Chromium-Molybdenum-Silicon Alloy (UNS N06219) Plate, Sheet, and Strip*

ASTM B 446, *Standard Specification for Nickel-Chromium-Molybdenum-Columbium Alloy (UNS N06625) and Nickel-Chromium-Molybdenum-Silicon Alloy (UNS N06219) Rod and Bar*

ASTM B 575, *Specification for Low-Carbon Nickel-Molybdenum-Chromium, Low-Carbon Nickel-Chromium-Molybdenum, Low-Carbon Nickel-Chromium-Molybdenum-Copper, Low-Carbon Nickel-Chromium-Molybdenum-Tantalum, Low-Carbon Nickel-Chromium-Molybdenum-Tungsten Alloy Plate, Sheet and Strip*

ASTM E 29, *Standard Practice for Using Significant Digits in Test Data to Determine Conformance with Specifications*

ASTM E 354, *Standard Test Methods for Chemical Analysis of High-Temperature, Electrical, Magnetic, and Other Similar Iron, Nickel, and Cobalt Alloys*

ASTM E 1019, *Standard Test Methods for Determination of Carbon, Sulfur, Nitrogen, and Oxygen in Steel and in Iron, Nickel, and Cobalt Alloys*

ASTM E 1032, *Standard Test Methods for Radiographic Examination of Weldments*

ASTM E 1473, *Standard Test Methods for Chemical Analysis of Nickel, Cobalt, and High-Temperature Alloys*

2.5 The following ISO standard⁴ is referenced in the mandatory clauses of this document:

ISO 544, *Welding Consumables — Technical delivery conditions for welding filler materials — Type of product, dimensions, tolerances and markings*

3. Classification

3.1 The flux cored electrodes covered by the A5.34/A5.34M specifications are classified using a system that is independent of U.S. Customary Units and the International System of Units (SI). Classification is according to the chemical composition of the undiluted weld metal, the shielding gas employed during welding, and the welding position usability, as specified in Tables 1 and 2.

3.2 Electrodes classified under one classification may be classified under any other classification of this specification provided they meet all the requirements for those classifications.

4. Acceptance

Acceptance⁵ of the electrodes shall be in accordance with the provisions of AWS A5.01.

5. Certification

By affixing the AWS specification and classification designations to the packaging or the classification to the product, the manufacturer certifies that the product meets the requirements of this specification.⁶

⁴ISO standards are published by the International Organization for Standardization, 1, rue de Varembe, Case postale 56, CH-1211 Geneva 20, Switzerland.

⁵See Clause A3, Acceptance (in Annex A), for further information concerning acceptance, testing of the material shipped, and AWS A5.01.

⁶See Clause A4, Certification (in Annex A), for further information concerning certification and the testing called for to meet this requirement.

Table 1
Chemical Composition Requirements for Undiluted Weld Metal

AWS Classifications ^c			Wt. Percent ^{a, b}															
ISO Format	Traditional	UNS Number ^d	C	Mn	Fe	P	S	Si	Cu	Ni ^e	Co	Ti	Cr	Nb(Cb) plus Ta ^g	Mo	V	W	Other
TNi 6082-xy	ENiCr3Tx-y	W86082	0.10	2.5– 3.5	3.0	0.03	0.015	0.50	0.50	67.0 min.	(Note f)	0.75	18.0– 22.0	2.0– 3.0	—	—	—	0.50
TNi 6062-xy	ENiCrFe1Tx-y	W86132	0.08	3.5	11.0	0.03	0.015	0.75	0.50	62.0 min.	—	—	13.0– 17.0	1.5– 4.0	—	—	—	0.50
TNi 6133-xy	ENiCrFe2Tx-y	W86133	0.10	1.0– 3.5	12.0	0.03	0.02	0.75	0.50	62.0 min.	(Note f)	—	13.0– 17.0	0.5– 3.0	0.5– 2.5	—	—	0.50
TNi 6182-xy	ENiCrFe3Tx-y	W86182	0.10	5.0– 9.5	10.0	0.03	0.015	1.0	0.50	59.0 min.	(Note f)	1.0	13.0– 17.0	1.0– 2.5	—	—	—	0.50
TNi 6002-xy	ENiCrMo2Tx-y	W86002	0.05– 0.15	1.0	17.0– 20.0	0.04	0.03	1.0	0.50	Rem.	0.50– 2.50	—	20.5– 23.0	—	8.0– 10.0	—	0.2– 1.0	0.50
TNi 6625-xy	ENiCrMo3Tx-y	W86625	0.10	0.50	5.0 ^h	0.02	0.015	0.50	0.50	58.0 min.	(Note f)	0.40	20.0– 23.0	3.15– 4.15	8.0– 10.0	—	—	0.50
TNi 6276-xy	ENiCrMo4Tx-y	W80276	0.02	1.0	4.0– 7.0	0.03	0.03	0.2	0.50	Rem.	2.5	—	14.5– 16.5	—	15.0– 17.0	0.35	3.0– 4.5	0.50
TNi 6022-xy	ENiCrMo10Tx-y	W86022	0.02	1.0	2.0– 6.0	0.03	0.015	0.2	0.50	Rem.	2.5	—	20.0– 22.5	—	12.5– 14.5	0.35	2.5– 3.5	0.50
TNi 6117-xy	ENiCrCoMo1Tx-y	W86117	0.05– 0.15	0.3– 2.5	5.0	0.03	0.015	0.75	0.50	Rem.	9.0– 15.0	—	21.0– 26.0	1.0	8.0– 10.0	—	—	0.50

^a The weld metal shall be analyzed for the specific elements for which values are shown in this table. If the presence of other elements is indicated in the course of this work, the amount of those elements shall be determined, the total of which shall not exceed 0.50%.

^b Single values are maximum, except where otherwise specified. Rem. = Remainder.

^c Both designations shall be shown as described in 22.1. The letter “x” stands for the numerals 0 or 1 which denotes the welding position for which the alloy is classified, as described in Table 2. The letter “y” stands for one of the numerals 1, 3, or 4, which denotes the particular shielding gas (or none at all) required when conducting the classification tests, as described in Table 2.

^d SAE HS-1086/ASTM DS-56, *Metals & Alloys in the Unified Numbering System*.

^e Includes residual cobalt.

^f Cobalt is 0.10 maximum, when specified by the purchaser.

^g Tantalum is 0.30 maximum, when specified by the purchaser.

^h Iron is 1.0 maximum, when specified by the purchaser.

Table 2
Required Shielding Gas, Welding Current, and Welding Position

AWS Classifications ^a		External Shielding Gas Classification ^b	Current and Polarity	Welding Position ^c
ISO Format	Traditional			
TNi xxxx-01	ENiXXXXT0-1	SG-C	dcep	F & HF
TNi xxxx-11	ENiXXXXT1-1	SG-C	dcep	All
TNi xxxx-03	ENiXXXXT0-3	None	dcep	F & HF
TNi xxxx-04	ENiXXXXT0-4	SG-AC-25 or SG-AC-20	dcep	F & HF
TNi xxxx-14	ENiXXXXT1-4	SG-AC-25 or SG-AC-20	dcep	All

^a The letters xxxx stand for numeric designators, and the letters XXXX stand for the chemical symbol designators for the chemical composition.

^b See AWS A5.32/A5.32M. SG-C = CO₂; SG-AC-25 is nominally 25% CO₂, balance argon; SG-AC-20 is nominally 20% CO₂, balance argon. The external shielding gas specified here is required when making welds for classification. This requirement is not intended to preclude the use of another shielding gas in the application of the electrode.

^c Welding position usability is determined by the Fillet Weld Test as required by Table 3.

F = flat; HF = horizontal fillet; All = flat, horizontal, overhead, and vertical with upward progression.

6. Rounding-Off Procedure

For the purpose of determining conformance with this specification, an observed or calculated value shall be rounded to the nearest 1000 psi for tensile strength for A5.34, or to the nearest 10 MPa for tensile strength for A5.34M and to the “nearest unit” in the last right-hand place of figures used in expressing the limiting value for other quantities in accordance with the rounding-off method given in ASTM E 29.

7. Summary of Tests

7.1 The tests required for each classification are specified in Table 3. The purpose of these tests is to determine the chemical composition, the mechanical properties, soundness of the weld metal, and the welding position usability characteristics of the electrode using the specified shielding gas.

7.2 The base metals for the weld test assemblies are as specified in Tables 4 and 5. The welding and testing procedures to be employed, and the results required are given in Clauses 9 through 14.

8. Retest

If any test fails to meet the requirement, that test shall be repeated twice. The results of both retests shall meet the requirement. Specimens for the retest may be taken from the original test assembly or from a new test assembly.

For chemical analysis, retest need be only for those specific elements that failed to meet their requirement. If the results of one or both retests fail to meet the requirement, the material under test shall be considered as not meeting the requirements of this specification for that classification.

In the event that, during preparation or after completion of any test, it is clearly determined that prescribed or proper procedures were not followed in preparing the weld test assembly or test specimen(s) or in conducting the test, the test shall be considered invalid without regard to whether the test was actually completed, or whether test results met, or failed to meet, the requirement. That test shall be repeated, following prescribed procedures. In this case, the requirement for doubling of the number of test specimens does not apply.

9. Weld Test Assemblies

9.1 Up to four weld test assemblies may be required, depending upon the classification, as specified in Table 3. They are:

- (1) the weld pad in Figure 1 for chemical analysis of the undiluted weld metal
- (2) the groove weld in Figure 2 for mechanical properties and soundness of the weld metal
- (3) the groove weld in Figure 3 for longitudinal bend testing
- (4) the fillet weld in Figure 4 for welding position usability of the electrode.

Table 3
Required Tests^a

AWS Classifications		Chemical Analysis	Radiographic Test	Tension Test	Longitudinal Bend Test	Fillet Weld Test
ISO Format	Traditional					
TNi 6082-0y TNi 6082-1y	ENiCr3T0-y ENiCr3T1-y	Required Required	Required Required	Required Required	Required Required	Not Required Required
TNi 6062-0y TNi 6062-1y	ENiCrFe1T0-y ENiCrFe1T1-y	Required Required	Required Required	Required Required	Required Required	Not Required Required
TNi 6133-0y TNi 6133-1y	ENiCrFe2T0-y ENiCrFe2T1-y	Required Required	Required Required	Required Required	Required Required	Not Required Required
TNi 6182-0y TNi 6182-1y	ENiCrFe3T0-y ENiCrFe3T1-y	Required Required	Required Required	Required Required	Required Required	Not Required Required
TNi 6002-0y TNi 6002-1y	ENiCrMo2T0-y ENiCrMo2T1-y	Required Required	Required Required	Required Required	Required Required	Not Required Required
TNi 6625-0y TNi 6625-1y	ENiCrMo3T0-y ENiCrMo3T1-y	Required Required	Required Required	Required Required	Required Required	Not Required Required
TNi 6276-0y TNi 6276-1y	ENiCrMo4T0-y ENiCrMo4T1-y	Required Required	Required Required	Required Required	Required Required	Not Required Required
TNi 6022-0y TNi 6022-1y	ENiCrMo10T0-y ENiCrMo10T1-y	Required Required	Required Required	Required Required	Required Required	Not Required Required
TNi 6117-0y TNi 6117-1y	ENiCrCoMo1T0-y ENiCrCoMo1T1-y	Required Required	Required Required	Required Required	Required Required	Not Required Required

^a The tests specified are required for each size of electrode to be classified.

Table 4
Required Base Metals^{a, b}

AWS Classification		Chemical Analysis ^c	Radiographic Test	Tension Test	Bend Test	Fillet Weld Test
ISO Format	Traditional					
TNi 6082-xy	ENiCr3Tx-y		Ni-Cr-Fe, Stainless, or Carbon Steels			
TNi 6062-xy	ENiCrFe1Tx-y					
TNi 6133-xy	ENiCrFe2Tx-y					
TNi 6182-xy	ENiCrFe3Tx-y					
TNi 6002-xy	ENiCrMo2Tx-y		Ni-Cr-Mo, Stainless, or Carbon Steels			
TNi 6625-xy	ENiCrMo3Tx-y					
TNi 6276-xy	ENiCrMo4Tx-y					
TNi 6022-xy	ENiCrMo10Tx-y					
TNi 6117-xy	ENiCrCoMo1Tx-y		Ni-Cr-Co-Mo, Stainless, or Carbon Steels			

^a See Table 5 for specifications for the required base metals.

^b Where nickel alloy, carbon steel, or stainless steel is shown, any type or any combination of those may be used. When either or both members are carbon steel, two layers of buttering shall be applied to the face of the groove on the carbon steel member and, if the backing strip is also carbon steel, to the mating surface of that as well. The buttering shall be applied in the flat position using electrodes of the same classification as the one being tested prior to joint fit up.

^c For chemical analysis, carbon steel, stainless steel, or nickel alloy base metals other than those specified in tables may be used in preparation of the undiluted weld metal pad provided the minimum pad height (weld metal) is 3/4 in [20 mm] and the sample for analysis is taken at least 5/8 in [16 mm] from the nearest surface of the base metal.

Table 5
Base Metal Specifications^a

AWS Classification		Base Metal	ASTM Specification	UNS Number of Base Metal
ISO Format	Traditional			
TNi 6082-xy TNi 6062-xy TNi 6133-xy TNi 6182-xy	ENiCr3Tx-y ENiCrFe1Tx-y ENiCrFe2Tx-y ENiCrFe3Tx-y	Nickel-chromium iron alloy	B 166, B 168	N06600
TNi 6002-xy TNi 6625-xy	ENiCrMo2Tx-y ENiCrMo3Tx-y	Nickel-chromium-molybdenum alloy or Low carbon nickel-chromium-molybdenum alloy	B 443, B 446, B 435 B 575	N06625, N06002 N10276
TNi 6276-xy TNi 6022-xy	ENiCrMo4Tx-y ENiCrMo10Tx-y	Low carbon nickel-chromium-molybdenum alloy	B 575	N10276, N06022
TNi 6117-xy	ENiCrCoMo1Tx-y	Nickel-chromium-cobalt-molybdenum alloy	B 166, B 168	N06617
All		Carbon steel	A 131, A 285, A 515, A 516	—
All		Austenitic stainless steel	A 240, A 666	S301xx, S302xx, S304xx, S316xx

^a All base metals, except carbon steel, shall be in the annealed condition prior to welding.

The sample for chemical analysis may be taken from the reduced section of the fractured tension specimen, or from a corresponding location (or any location above it) in the weld metal of the groove weld in Figure 2, thereby avoiding the need to make the weld pad. In case of dispute, the weld pad shall be the referee method.


9.2 Preparation of each weld test assembly shall be as prescribed in 9.3, 9.4, 9.5, and 9.6. The base metal for each assembly shall be as required in Table 4, according to the tests to be conducted, and shall meet the requirements of the appropriate ASTM specification shown in Table 5, or an equivalent specification. Testing shall be as prescribed in Clause 10, Chemical Analysis; Clause 11, Radiographic Test; Clause 12, Tension Test; Clause 13, Bend Test; and Clause 14, Fillet Weld Test.

9.3 Weld Pad. A weld pad shall be prepared as specified in Table 3 and shown in Figure 1, except when one of the alternatives in 9.1 (taking the sample from the weld metal in the groove weld or from the tension test specimen) is selected. Base metal of any convenient size, of the type specified in Tables 4 and 5, shall be used as the base for the weld pad. The surface of the base metal on which the

filler metal is deposited shall be clean. The pad shall be welded in the flat position, with multiple layers to obtain undiluted weld metal using the applicable shielding gas, if any. Welding conditions shall be those recommended by the manufacturer. The preheat temperature shall be not less than 60°F [15°C], and the interpass temperature shall not exceed 300°F [150°C]. The slag shall be removed after each pass. The pad may be quenched in water between passes. Dimensions of the completed weld pad shall be as shown in Figure 1. Testing of this assembly shall be as specified in Clause 10, Chemical Analysis.

9.4 Groove Weld. A test assembly shall be prepared and welded as specified in Table 3 and Figure 2, using base metal of the appropriate type specified in Tables 4 and 5. Testing of this assembly shall be as specified in Clause 11, Radiographic Test, and Clause 12, Tension Test. The assembly shall be tested in the as-welded condition.

9.5 Longitudinal Face Bend. The test assembly shall be prepared and welded as specified in Table 3 and Figure 3, using base metal of the appropriate type as specified in Tables 4 and 5. Testing of this assembly shall be as specified in Clause 13, Bend Test.

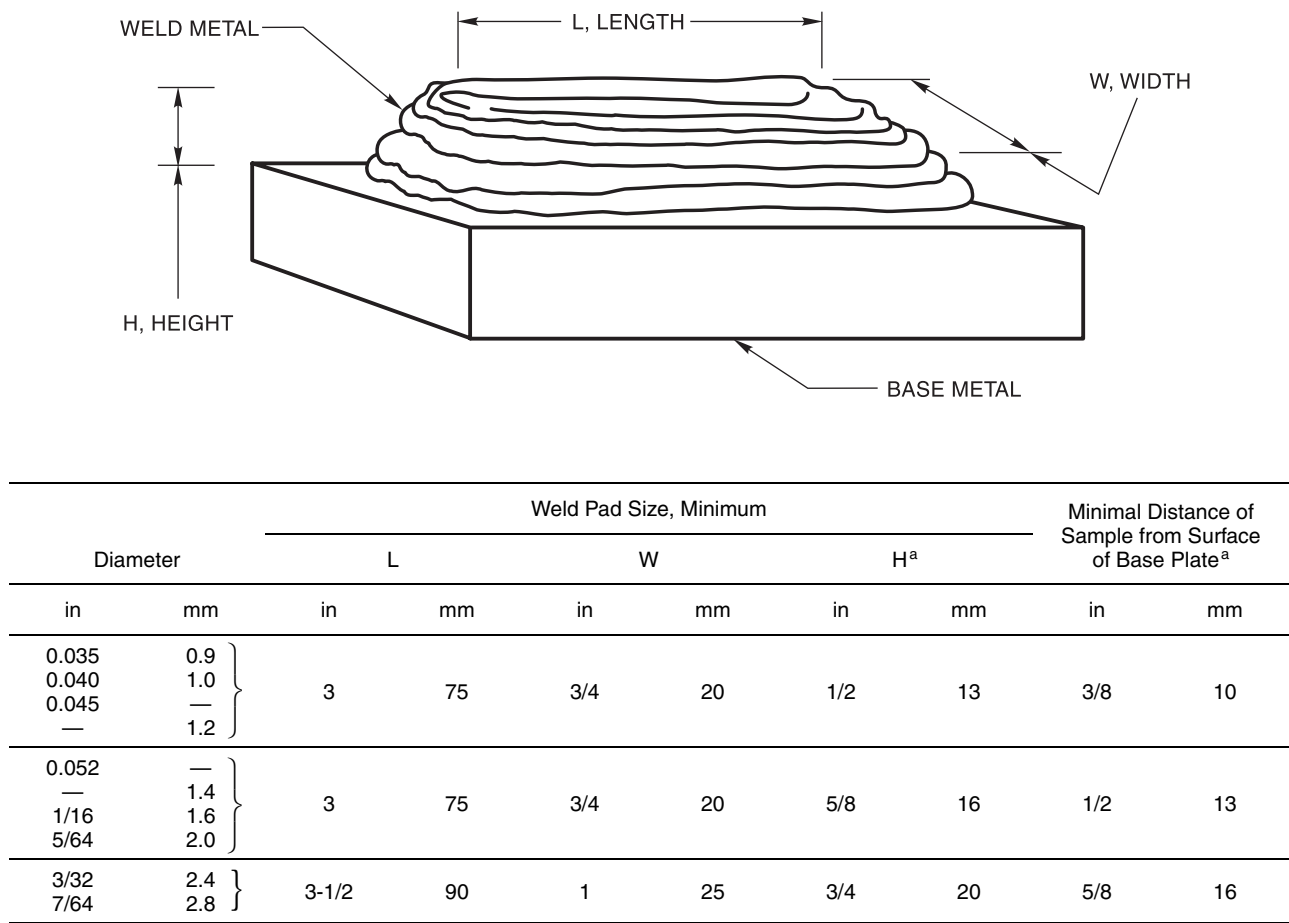

^aNumber of passes per layer is optional.

- Notes:
1. Width and thickness of the base plate may be any dimensions suitable for the electrode diameter and current used.
 2. The first and last inch [25 mm] of the weld length shall be disregarded. The top surface shall be removed and chemical analysis samples shall be taken from the top of the remaining deposited metal.
 3. The use of copper chill bar is optional.
 4. For chemical analysis, carbon steel, stainless steel, or nickel alloy base metals other than those specified in tables may be used in preparation of the undiluted weld metal pad provided the minimum pad height (weld metal) is 3/4 in [20 mm] and the sample for analysis is taken at least 5/8 in [16 mm] from the nearest surface of the base metal.



Figure 1—Pad for Chemical Analysis of Undiluted Weld Metal

9.6 Fillet Weld

9.6.1 Fillet weld tests, when required by Table 3, shall be performed in the vertical and overhead positions. A test assembly shall be prepared and welded as shown in Figure 4 using base metal of the appropriate type as specified in Tables 4 and 5, the shielding gas, current, and polarity specified in Table 2, and the amperage or wire feed speed and arc voltage recommended by the manufacturer. Testing of the assembly shall be as specified in Clause 14, Fillet Weld Test.

9.6.2 In preparing the two plates forming the test assembly, the standing member (web) shall have one edge prepared so that when the web is set upon the base plate (flange), which shall be straight and smooth, there will be intimate contact along the entire length of the joint.

9.6.3 A single-pass fillet weld shall be deposited on one side of the joint. When welding in the vertical position, the welding shall progress upward.

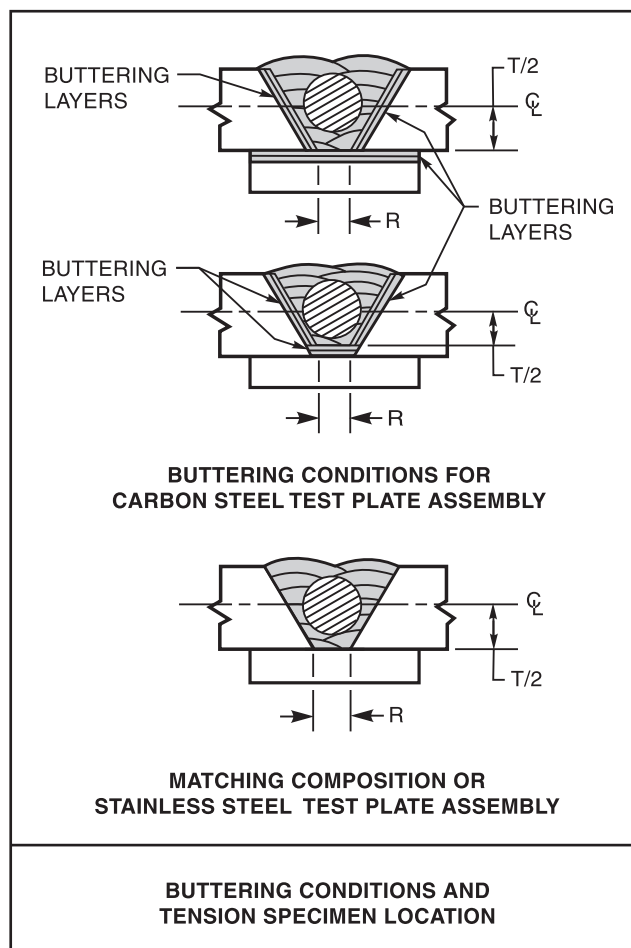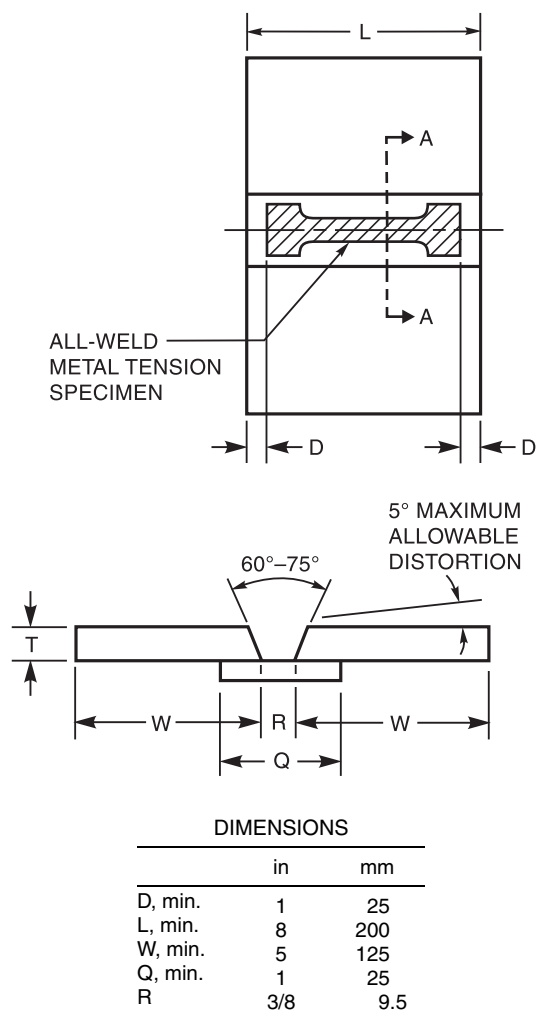


Electrode Diameter		(T) Plate Thickness		Recommended Passes per Layer		Recommended Number of Layers
		in	mm	Layer 1 and 2	Layer 3 to Top	
0.035	0.9	3/4	20	1 or 2	2, 3, or 4	8 to 12
0.040	1.0					
0.045	—					
—	1.2					
0.052	—	3/4	20	1 or 2	2 or 3 ^a	5 to 8
1/16	1.6					
5/64	2.0					
3/32	2.4					
7/64	2.8	3/4	20	1 or 2	2 or 3 ^a	4 to 6

^a Final layer may be 4 passes.

Notes:

1. The assembly shall be as long as necessary to provide the specimens needed for the number and type of tests required.
2. The root opening (R) tolerance is $\pm 1/16$ in [1.5 mm].
3. The base metal shall be as specified in Table 4.
4. The surfaces to be welded shall be clean.
5. Prior to welding, the assembly may be preset so that the welded joint will be sufficiently flat to facilitate removal of the test specimens. As an alternative, restraint or a combination of restraint and presetting may be used to keep the welded joint within 5° of plane. A test assembly that is more than 5° out of plane shall be discarded. Straightening of the test assembly is prohibited.
6. Welding shall be performed in the flat position, using welding parameters and technique recommended by the electrode manufacturer.
7. The preheat temperature shall be 60°F [15°C] minimum. The interpass temperature shall not exceed 300°F [150°C].
8. The tests shall be conducted without a postweld heat treatment.

Figure 2—Groove Weld Test Assembly for Tension and Radiographic Tests

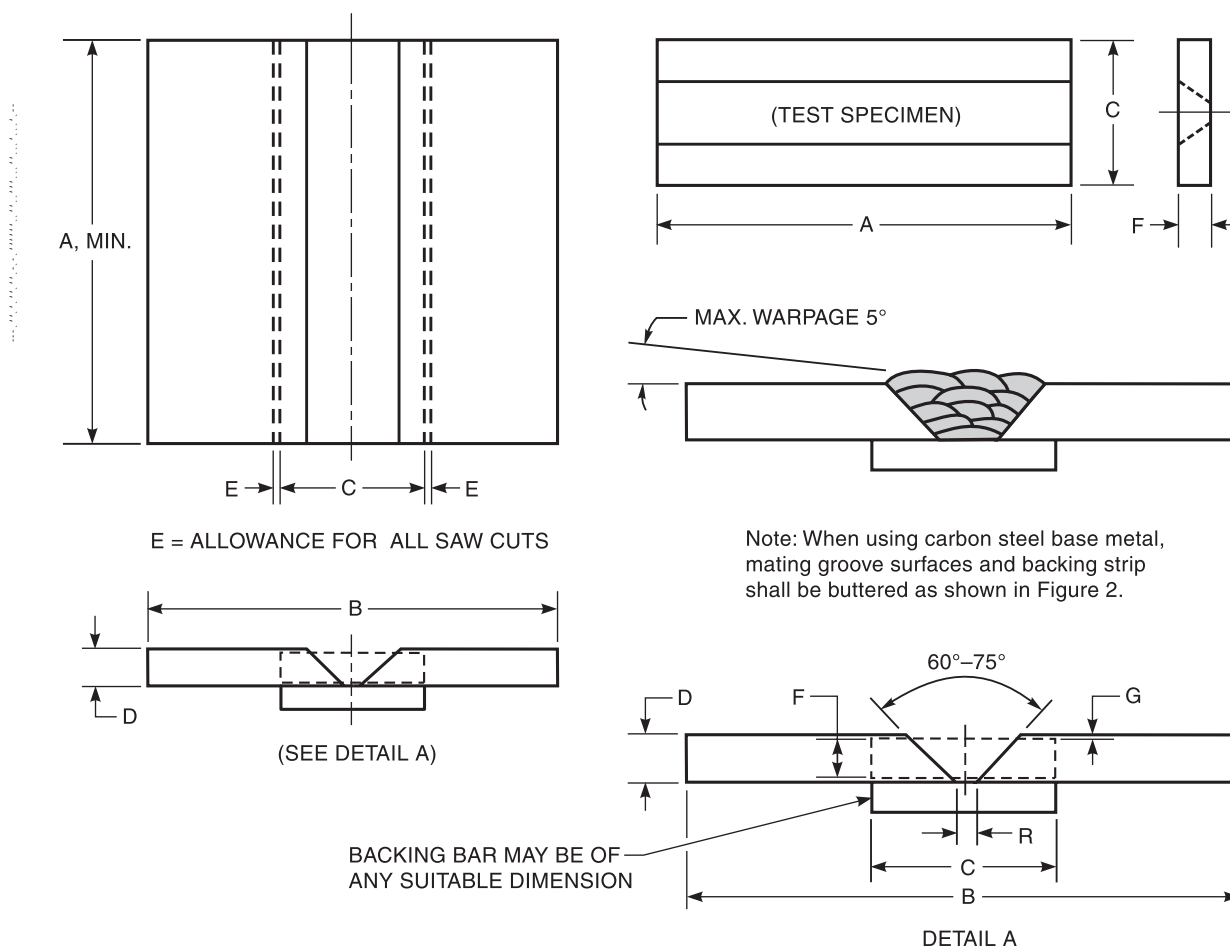

Electrode Diameter	Passes per Layer		
	Layer 1	Layer 2 to Top	Number of Layers
0.035	0.9		
0.040	1.0		
0.045	—		
—	1.2		
0.052	—		
—	1.4	2 to 3 ^a	3 to 5
1/16	1.6		
5/64	2.0		
3/32	2.4		
7/64	2.8		


	DIMENSIONS	
	in	mm
A	6 min.	150 min.
B	6	150
C	2	50
D	1/2	13
E	1/8	3
F	3/8	9.5
G	1/16	1.6
R	3/8	10

^a Top layer must be 3.

Notes:

1. The assembly shall be as long as necessary to provide the specimens needed for the number and type of tests required.
2. The root opening (R) tolerance is $\pm 1/16$ in [1.6 mm].
3. The base metal shall be as specified in Table 4.
4. The surfaces to be welded shall be clean.
5. Prior to welding, the assembly may be preset so that the welded joint will be sufficiently flat to facilitate removal of the test specimen. As an alternative, restraint or a combination of restraint and presetting may be used to keep the welded joint within 5° of plane. A welded test assembly that is more than 5° out of plane shall be discarded. Straightening of the test assembly is prohibited.
6. Welding shall be performed in the flat position, using welding parameters and technique recommended by the electrode manufacturer.
7. The preheat temperature shall be 60°F [15°C] minimum. The interpass temperature shall not exceed 300°F [150°C].
8. The tests shall be conducted without a postweld heat treatment.

Figure 3—Groove Weld for Longitudinal Face-Bend Test

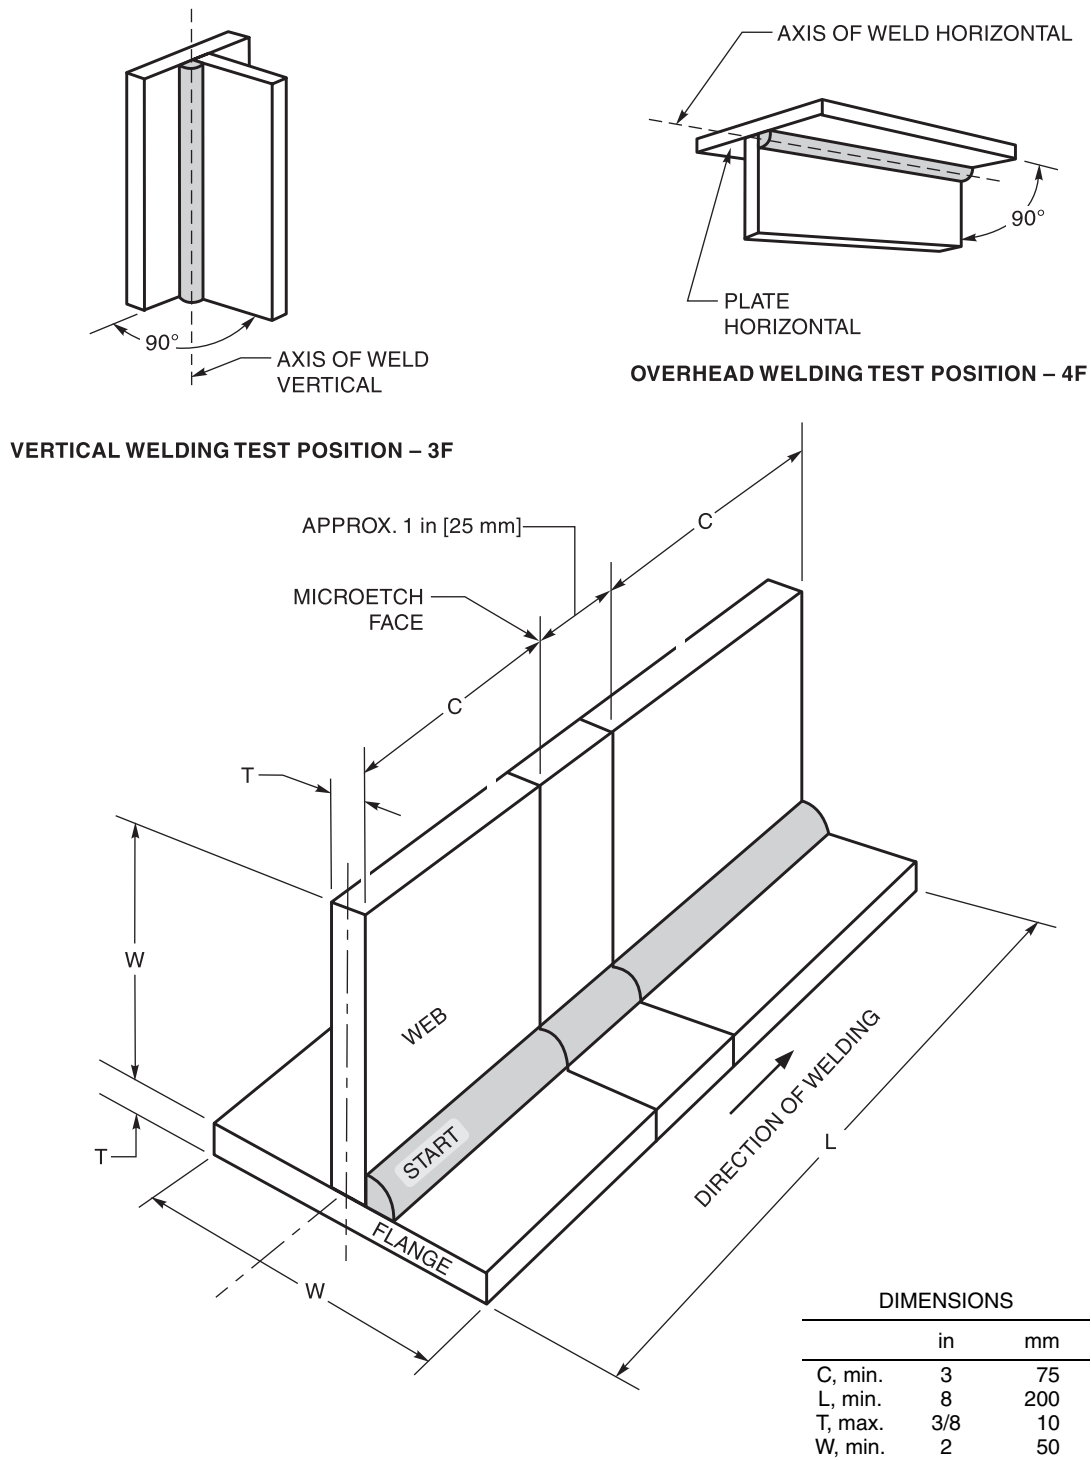

Notes:

1. The base metal shall be as specified in Table 4.
2. The surface to be welded shall be clean.
3. The assembly shall be at room temperature at the start of the welding pass.
4. Weld cleaning shall be limited to slag chipping, brushing, and needle scaling. Grinding or filing of the weld face is prohibited.

Figure 4—Fillet Weld Test Assembly

10. Chemical Analysis

10.1 The sample for analysis shall be taken from weld metal produced with the filler metal and the shielding gas with which it is classified. The top surface of the pad described in 9.3 and shown in Figure 1 shall be removed and discarded, and a sample for analysis shall be obtained from the underlying metal by any appropriate mechanical means. The sample shall be free of slag. The sample shall be taken at least 3/8 in [10 mm] from the nearest surface of the base metal (see Table 4, Note c, for sample removal when base metals other than those specified are used). Samples from the reduced section of the fractured tension specimen or from a corresponding location (or any location above it) in the groove weld in Figure 2 shall be prepared for chemical analysis by any suitable mechanical means.

10.2 The sample shall be analyzed by accepted analytical methods. The primary referee method shall be ASTM Method E 1473, supplemented by ASTM Method E 1019 for carbon and ASTM Method E 354 for phosphorus.

10.3 The results of the analysis shall meet the requirements of Table 1 for the classification of electrode under test.

11. Radiographic Test

11.1 The groove weld described in 9.4 and shown in Figure 2 shall be radiographed to evaluate the soundness of the weld metal. In preparation for radiography, the backing shall be removed and both surfaces of the weld shall be machined or ground smooth and flush with the original surfaces (except as noted) of the base metal or with a uniform reinforcement not exceeding 3/32 in [2.5 mm]. It is permitted on both sides of the test assembly to remove base metal to a depth of 1/16 in [1.5 mm] nominal below the original base metal surface in order to facilitate backing and/or buildup removal. Thickness of the weld metal shall not be reduced by more than 1/16 in [1.5 mm] less than the nominal base metal thickness. Both surfaces of the test assembly, in the area of the weld, shall be smooth enough to avoid difficulty in interpreting the radiograph.

11.2 The weld shall be radiographed in accordance with ASTM E 1032, *Standard Test Method for Radiographic Examination of Weldments*. The quality level of inspection shall be 2-2T.

11.3 The soundness of the weld metal meets the requirements of this specification if the radiograph shows:

(1) no cracks, no incomplete fusion, and no incomplete penetration; and

(2) no rounded indications in excess of those permitted by the radiographic standard in Figure 5.

In evaluating the radiograph 1 in [25 mm] of the weld on each end of the test assembly shall be disregarded.

11.3.1 The alternative method of evaluation involves calculation of the total area of the rounded indications as they appear on the radiograph. This total area shall not exceed 1% of the thickness of the test assembly multiplied by the length of the weld used in evaluation (length of the weld in the test assembly minus 1 in [25 mm] on each end). The value given in Note 3 of the Figure 5 has been calculated for 6 in [150 mm] of weld (an 8 in [200 mm] long test assembly). The value for weld lengths other than this will differ on a linearly proportional basis.

11.3.2 A rounded indication is an indication on the radiograph whose length is no more than three times its width. Rounded indications may be circular or irregular in shape, and they may have tails. The size of a rounded indication is the largest dimension of the indication, including any tail that may be present. The indication may be of porosity or slag.

11.3.3 Indications whose largest dimension does not exceed 1/64 in [0.4 mm] shall be disregarded. Test assemblies with indications larger than the large indications permitted in the radiographic standard (Figure 5) do not meet the requirements of this specification.

12. Tension Test


12.1 One all-weld-metal tension test specimen, as specified in the Tension Test clause of AWS B4.0 or AWS B4.0M, shall be machined from the groove weld described in 9.4 and shown in Figure 2. The all-weld-metal tensile specimen shall have a nominal diameter of 0.500 in [12.5 mm] and a nominal gage length-to-diameter ratio of 4:1.

12.2 The specimen shall be tested in the manner described in the Tension Test clause of AWS B4.0 or AWS B4.0M.

12.3 The results of the tension test shall meet the requirements specified in Table 6.

13. Bend Test

13.1 One longitudinal face bend specimen, as required in Table 3, shall be machined from the groove weld test assembly shown in Figure 3, as described in AWS B4.0

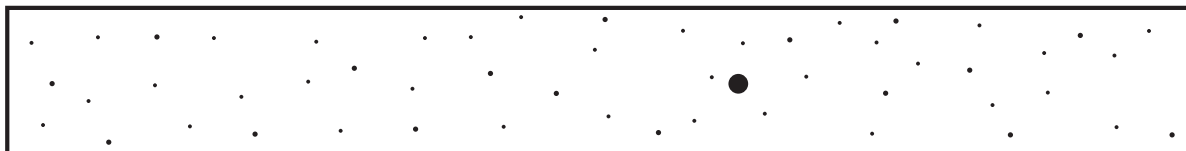**(A) ASSORTED ROUNDED INDICATIONS**

SIZE PERMITTED IS 0.125 in [3.2 mm] MAXIMUM.

NUMBER PERMITTED IN ANY 6 in [150 mm] OF WELD IS 53, WITH THE FOLLOWING RESTRICTIONS:

LARGE: UP TO 0.125 in [3.2 mm] – 1 PERMITTED


MEDIUM: UP TO 0.034 in [0.9 mm] – 17 PERMITTED

SMALL: UP TO 0.024 in [0.6 mm] – 35 PERMITTED

**(B) LARGE ROUNDED INDICATIONS**


SIZE PERMITTED IS 0.125 in [3.2 mm] MAXIMUM.

NUMBER PERMITTED IN ANY 6 in [150 mm] OF WELD IS 4.

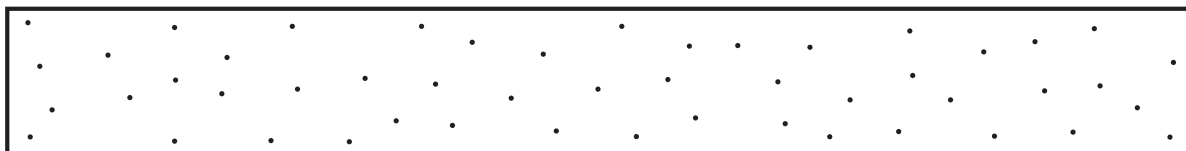**(C) MEDIUM ROUNDED INDICATIONS**

SIZE PERMITTED IS 0.034 in [0.9 mm] MAXIMUM.

NUMBER PERMITTED IN ANY 6 in [150 mm] OF WELD IS 50.

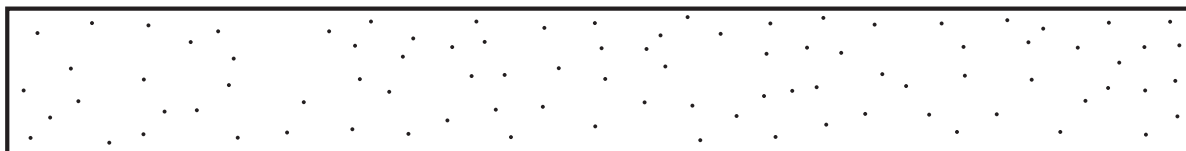**(D) SMALL ROUNDED INDICATIONS**

SIZE PERMITTED IS 0.024 in [0.6 mm] MAXIMUM.

NUMBER PERMITTED IN ANY 6 in [150 mm] OF WELD IS 90.

Notes:

1. The chart that is most representative of the size of the rounded indications in the radiograph of the test assembly shall be used to determine conformance with this specification. Rounded indications 1/64 in [0.4 mm] and smaller shall be disregarded. The largest dimension of the indication (including any tail) is the size of the indication.
2. These radiographic requirements are for test welds made in the laboratory specifically for classification purposes. They are more restrictive than those normally encountered in general fabrication.
3. When using the alternative method of evaluation described in 11.3.1, the total cross-sectional area of the rounded indications (calculated from measurements taken from the radiograph) shall not exceed 0.045 in² [29.0 mm²] in any 6 in [150 mm] of weld.
4. The acceptance standard for slag inclusions in this assembly is the following:
 - (a) Length of each individual slag indication: 5/16 in [8 mm] maximum.
 - (b) Total length of all slag indications: 15/32 in [12 mm] maximum.

Figure 5—Radiographic Standards for 3/4 in [19 mm] Test Assembly in Figure 2

Table 6
Tension Test Requirements^a

AWS Classification		Tensile Strength, min.		Elongation ^b
ISO Format	Traditional	psi	MPa	%, min.
TNi 6082-xy TNi 6062-xy TNi 6133-xy TNi 6182-xy	ENiCr3Tx-y ENiCrFe1Tx-y ENiCrFe2Tx-y ENiCrFe3Tx-y	80 000	550	25
TNi 6002-xy	ENiCrMo2Tx-y	90 000	620	25
TNi 6625-xy TNi 6276-xy TNi 6022-xy	ENiCrMo3Tx-y ENiCrMo4Tx-y ENiCrMo10Tx-y	100 000	690	25
TNi 6117-xy	ENiCrCoMo1Tx-y	90 000	620	25

^a As-welded condition.

^b The elongation shall be determined from gage length equal to 4 times the gage diameter.

or AWS B4.0M. The dimensions of the specimen shall be as shown in Figure 3. The backing strip and weld reinforcement shall be removed by machining.

13.2 The specimen shall be tested in the manner described in the Bend Test clause of AWS B4.0 or AWS B4.0M by bending it uniformly through 180° over a 3/4 in [19 mm] radius. Any suitable jig, as specified in the Bend Test clause of AWS B4.0 or AWS B4.0M, may be used.

13.3 The specimen, after bending, shall conform to the 3/4 in [19 mm] radius, with appropriate allowance for spring back, and the weld metal shall show no defects on the tension face greater than 1/8 in [3 mm].

14. Fillet Weld Test

14.1 The fillet weld test, when required by Table 3, shall be made in accordance with the requirements of 9.6 and Figure 4. The entire face of the completed fillet shall be examined visually, and shall show no cracks and be reasonably free of undercut. After the visual examination, a specimen containing approximately one inch of weld (in the lengthwise direction) shall be prepared as shown in Figure 4. One cross-sectional surface of the specimen shall be polished and etched, then examined as required in 14.2.

14.2 Scribe lines shall be placed on the prepared surface, as shown in Figure 6, and the leg lengths and convexity of the fillet shall be determined to the nearest 1/64 in

[0.5 mm] by actual measurement (see Figure 6). These dimensions shall meet the requirements in Figure 6 for fillet size, convexity, and permissible difference in the length of the legs.

14.2.1 The fillet shall have penetration to or beyond the junction of the edges of the plates.

14.2.2 The legs and convexity of the fillet weld shall be within the limits prescribed in Figure 6.

14.2.3 The fillet weld shall show no evidence of cracks.


14.2.4 The weld shall be reasonably free from undercutting, overlap, trapped slag, and porosity.

15. Method of Manufacture

The electrodes classified according to this specification may be manufactured by any method that will produce material that meets the requirements of this specification.

16. Standard Sizes

Standard sizes for electrode in the different package forms (coils with support, coils without support, spools, and drums) are shown in Table 7 (see Clause 18, Standard Package Forms).

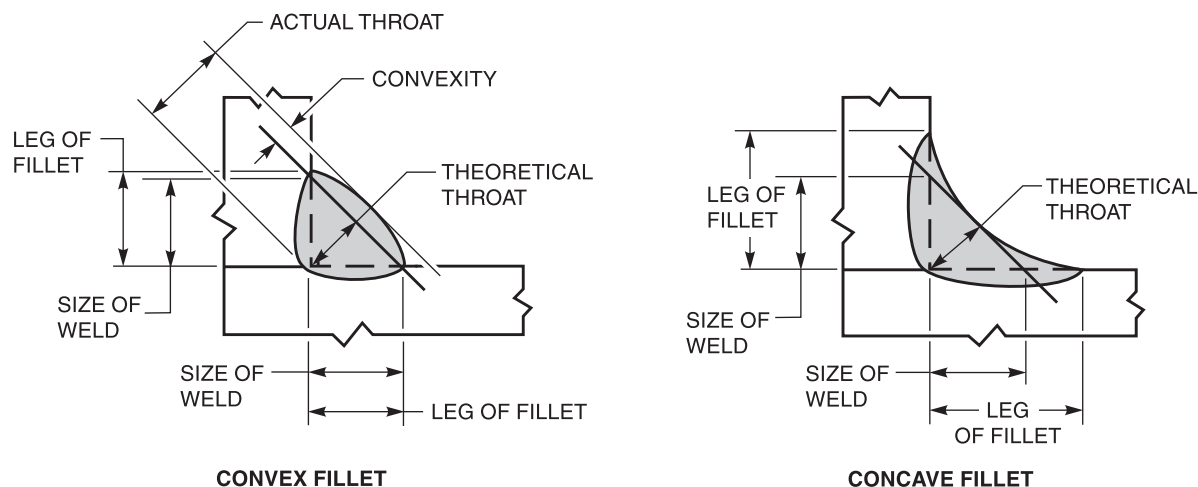

Measured Fillet Weld Size		Maximum Convexity		Maximum Difference Between Fillet Weld Legs	
in	mm	in	mm	in	mm
1/8 or less	3.0 or less	5/64	2.0	1/32	0.8
9/64	3.5	5/64	2.0	3/64	1.2
5/32	4.0	5/64	2.0	3/64	1.2
11/64	4.5	5/64	2.0	1/16	1.6
3/16	5.0	5/64	2.0	1/16	1.6
13/64	5.2	5/64	2.0	5/64	2.0
7/32	5.5	5/64	2.0	5/64	2.0
15/64	6.0	5/64	2.0	3/32	2.4
1/4	6.5	5/64	2.0	3/32	2.4
17/64	6.7	3/32	2.4	7/64	2.8
9/32	7.0	3/32	2.4	7/64	2.8
19/64	7.5	3/32	2.4	1/8	3.2
5/16	8.0	3/32	2.4	1/8	3.2
21/64	8.5	3/32	2.4	9/64	3.6
11/32	8.7	3/32	2.4	9/64	3.6
23/64	9.0	3/32	2.4	5/32	4.0
3/8 or more	9.5 or more	3/32	2.4	5/32	4.0

Notes:

1. Size of fillet weld = leg length of largest inscribed isosceles right triangle.
2. Fillet weld size, convexity, and leg lengths of fillet welds shall be determined by actual measurement (nearest 1/64 in [0.5 mm]) on a section laid out with scribed lines shown.

Figure 6—Fillet Weld Test Specimen and Dimensional Requirements

17. Finish and Uniformity

17.1 All electrodes shall have a smooth finish which is free from slivers, depressions, scratches, scale, seams, laps (exclusive of the longitudinal joint), and foreign matter that would adversely affect the welding characteristics, the operation of the welding equipment, or the properties of the weld metal.

17.2 Each continuous length of electrode shall be from a single lot of material, and welds, when present, shall have been made so as not to interfere with the uniform, uninterrupted feeding of the filler metal on automatic and semiautomatic equipment.

17.3 Core ingredients shall be distributed with sufficient uniformity throughout the length of the electrode so as not to adversely affect the performance of the electrode or the properties of the weld metal.

18. Standard Package Forms

18.1 Standard package forms are coils with support, coils without support, spools, and drums. Standard package dimensions and weights for each form are given in Table 8,

Table 7
Standard Electrode Sizes and Tolerances^a

U.S. Customary Units		International System of Units (SI)	
Diameter (in)	Tolerance (in)	Diameter (mm)	Tolerance (mm)
0.035	±0.002	0.9	+0.02, -0.05
0.040	±0.002	1.0	+0.02, -0.05
0.045	±0.002	—	—
—	—	1.2	+0.02, -0.05
0.052	±0.002	—	—
—	—	1.4	+0.02, -0.05
1/16 (0.062)	±0.002	1.6	+0.02, -0.06
5/64 (0.078)	±0.003	2.0	+0.02, -0.06
3/32 (0.094)	±0.003	2.4	+0.02, -0.06
7/64 (0.109)	±0.003	2.8	+0.02, -0.06

^a Electrodes sizes other than those shown may be manufactured by using the tolerances shown for the next larger size or as agreed between supplier and purchaser.

Table 8
Standard Package Dimensions and Weights^a

Type of Package	Package Size				Net Weight of Electrode ^b	
	in		mm		lb	kg
Coils without Support	(Note c)		(Note c)		(Note c)	(Note c)
Coils with Support (see below)	6-3/4 12	ID ID	170 300	ID ID	14 25, 30, 50, and 60	6.4 11, 14, 23, and 27
Spools	4	OD	100	OD	1-1/2 and 2-1/2	0.7 and 1.1
	8	OD	200	OD	10, 15, and 22	4.5, 6.8, and 10
	12	OD	300	OD	25, 30, and 35	11, 14, and 16
	14	OD	360	OD	50 and 60	23 and 27
	22	OD	560	OD	250	110
	24	OD	610	OD	300	140
	30	OD	760	OD	600 and 750	270 and 340
Drums	15-1/2	OD	400	OD	(Note c)	(Note c)
	20	OD	500	OD	(Note c)	(Note c)
	23	OD	600	OD	300 and 600	(140 and 270)

Coils with Support—Standard Dimensions and Weights

Electrode Size	Coil Dimensions					
	Coil Net Weight ^b		Inside Diameter of Liner		Width of Wound Electrode	
	lb	kg	in	mm	in (max.)	mm (max.)
All	14	6.4	6-3/4 ± 1/8	170 ± 3	3	75
	25 and 30	11 and 14	12 ± 1/8	305 ± 3	2-1/2 or 4-5/8	65 or 120
	50 and 60	23 and 27	12 ± 1/8	305 ± 3	4-5/8	120

^a Sizes and net weights other than those specified may be supplied as agreed between supplier and purchaser.

^b Tolerance on net weight shall be ±10%.

^c As agreed between supplier and purchaser.

and Figures 7 and 8. Package forms, sizes, and weights other than these shall be as agreed between purchaser and supplier.


18.2 The liners in coils with support shall be designed and constructed to prevent distortion of the coil during normal handling and use and shall be clean and dry enough to maintain the cleanliness of the filler metal.

18.3 Spools shall be designed and constructed to prevent distortion of the spool and the filler metal during normal handling and use and shall be clean and dry enough to maintain the cleanliness of the filler metal.

19. Winding Requirements

19.1 Electrodes on spools and in coils (including drums) shall be wound so that kinks, waves, sharp bends, overlapping, or wedging are not encountered, leaving the electrode free to unwind without restriction. The outside end of the filler metal (the end with which welding is to begin) shall be identified so it can be readily located and shall be fastened to avoid unwinding.

19.2 The cast and helix of the electrode in coils, spools, and drums shall be such that the electrode will feed in an uninterrupted manner in automatic and semiautomatic equipment.

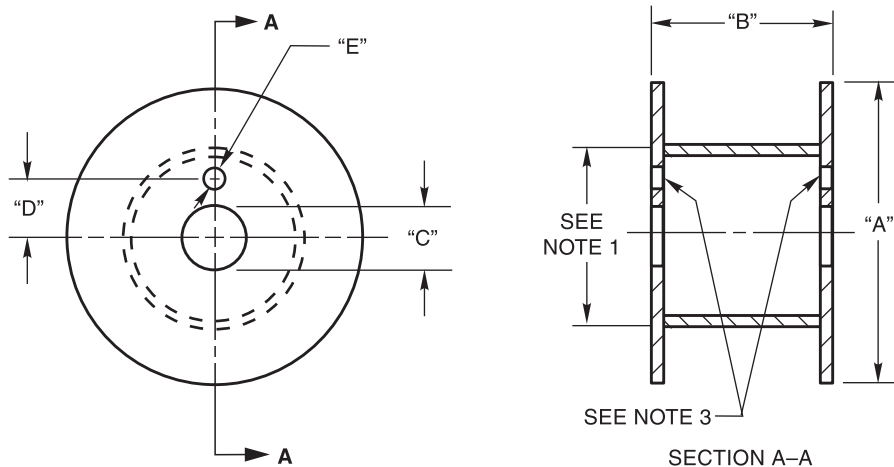


DIMENSIONS

		4 in [100 mm] Spools		8 in [200 mm] Spools		12 in [300 mm] Spools		14 in [350 mm] Spools	
		in	mm	in	mm	in	mm	in	mm
A	Diameter, max. (Note 4)	4.0	102	8.0	203	12	305	14	355
B	Width	1.75	46	2.16	56	4.0	103	4.0	103
	Tolerance	± 0.03	$+0, -2$	± 0.03	$+0, -3$	± 0.06	$+0, -3$	± 0.06	$+0, -3$
C	Diameter	0.63	16	2.03	50.5	2.03	50.5	2.03	50.5
	Tolerance	$+0.01, -0$	$+1, -0$	$+0.06, -0$	$+2.5, -0$	$+0.06, -0$	$+2.5, -0$	$+0.06, -0$	$+2.5, -0$
D	Distance between axes	—	—	1.75	44.5	1.75	44.5	1.75	44.5
	Tolerance	—	—	± 0.02	± 0.5	± 0.02	± 0.5	± 0.02	± 0.5
E	Diameter (Note 3)	—	—	0.44	10	0.44	10	0.44	10
	Tolerance	—	—	$+0, -0.06$	$+1, -0$	$+0, -0.06$	$+1, -0$	$+0, -0.06$	$+1, -0$

Notes:

1. Outside diameter of barrel shall be such as to permit feeding of the filler metals.
2. Inside diameter of the barrel shall be such that swelling of the barrel or misalignment of the barrel and flanges will not result in the inside of the diameter of the barrel being less than the inside diameter of the flanges.
3. Holes are provided on each flange, but they need not be aligned. No driving holes required for 4 in [100 mm] spools.
4. Metric dimensions and tolerances conform to ISO 544 except that "A" specifies $\pm$ tolerances on the nominal diameter, rather than a plus tolerance only, which is shown here as a maximum.

Figure 7—Dimensions of 4 in, 8 in, 12 in, and 14 in [100 mm, 200 mm, 300 mm, and 350 mm] Standard Spools

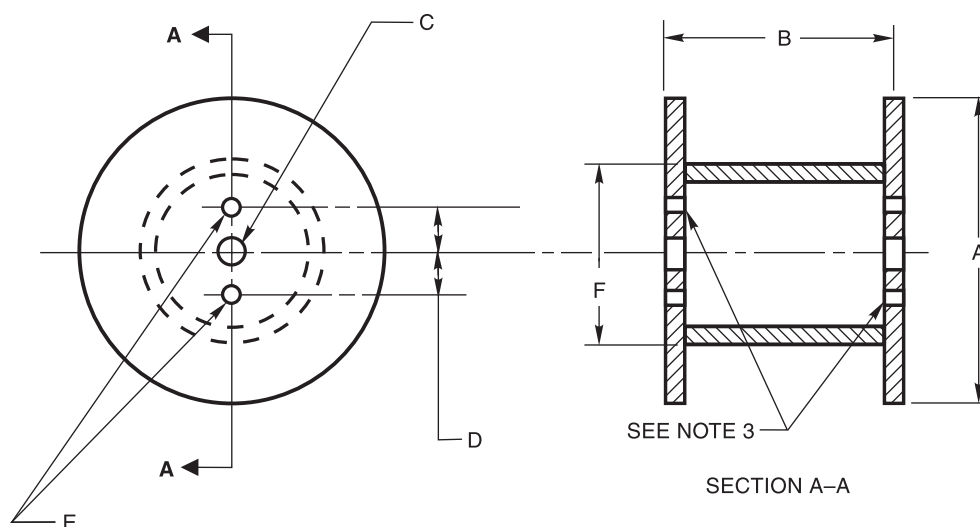

DIMENSIONS

		22 in [560 mm] Spools		24 in [610 mm] Spools		30 in [760 mm] Spools	
		in	mm	in	mm	in	mm
A	Diameter, max.	22	560	24	610	30	760
B	Width, max.	12	305	13.5	345	13.5	345
C	Diameter Tolerance	1.31 +0.13, -0	35.0 ±1.5	1.31 +0.13, -0	35.0 ±1.5	1.31 +0.13, -0	35.0 ±1.5
D	Distance, Center-to-Center Tolerance	2.5 ±0.1	63.5 ±1.5	2.5 ±0.1	63.5 ±1.5	2.5 ±0.1	63.5 ±1.5
E	Diameter (Note 3) Tolerance	0.69 +0, -0.06	16.7 ±0.7	0.69 +0, -0.06	16.7 ±0.7	0.69 +0, -0.06	16.7 ±0.7

Notes:

1. Outside diameter of barrel, dimension F, shall be such as to permit proper feeding of the electrode.
2. Inside diameter of barrel shall be such that swelling of the barrel or misalignment of the barrel and flanges will not result in the inside of the diameter of the barrel being less than the inside diameter of the flanges.
3. Two holes are provided on each flange and shall be aligned on both flanges with the center hole.

**Figure 8—Dimensions of 22 in, 24 in, and 30 in
[560 mm, 610 mm, and 760 mm] Standard Spools (Reels)**

20. Filler Metal Identification

20.1 The product information and the precautionary information required in Clause 22 for marking each package shall also appear on each coil, spool, and drum.

20.2 Coils without support shall have a tag containing this information securely attached to the filler metal at the inside end of the coil.

20.3 Coils with support shall have the information securely affixed in a prominent location on the support.

20.4 Spools shall have the information securely affixed in a prominent location on the outside of one flange of the spool.

20.5 Drums shall have the information securely affixed in a prominent location on the side of the drum.

21. Packaging

Filler metal shall be suitably packaged to ensure against damage during shipment and storage under normal conditions.

22. Marking of Packages

22.1 The following product information (as a minimum) shall be legibly marked so as to be visible from the outside of each unit package:

(1) AWS specification and classification designation⁷ (year of issue may be excluded)

(2) Supplier's name and trade designation

⁷ The classification designation shall make use of both the ISO and traditional formats (see Table 1).

(3) Size and net weight

(4) Lot, control, or heat number

22.2 The appropriate precautionary information⁸ as given in ANSI Z49.1, latest edition (as a minimum) or its equivalent, shall be prominently displayed in legible print on all packages of electrodes, including individual unit packages enclosed within a larger package.

⁸ Typical examples of "warning labels" are shown in figures in ANSI Z49.1 for some common or specific consumables used with certain processes.

Annex A

Guide to AWS Specification for Nickel-Alloy Electrodes for Flux Cored Arc Welding

This annex is not part of AWS A5.34/A5.34M:2007, *Specification for Nickel-Alloy Electrodes for Flux Cored Arc Welding*, but is included for informational purposes only.

A1. Introduction

The purpose of this guide is to correlate the electrode classifications with their intended applications so the specification can be used effectively. Reference to appropriate base metal specifications is made whenever that can be done and when it would be helpful. Such references are intended only as examples rather than complete listings of the base materials for which each filler metal is suitable.

A2. Classification System

A2.1 An international system for designating filler metals (Figure A.1) is being adopted for nickel filler metals by the International Standards Organization (ISO). In order that the AWS filler metal specifications can easily conform to international standards, this specification adopts the new system along with that of the traditional designations. Both designations are to be employed for identification of the filler metal.

A2.1.1 The international, or ISO, designation system for nickel flux cored wire starts with “T” for tubular, followed by “Ni” for nickel. Four numeric digits based upon the UNS numbers are then assigned according to the composition.

A2.1.2 The composition designation is followed by two digits, marked x and y in Table 1. As defined in Table 2, the “x” stands for the welding position, and the “y” stands for the shielding gas (if any) with which the filler metal was classified by the manufacturer.



A2.2 The traditional designation system (Figure A.2) is also shown in a parallel column in Tables 1 to 6.

A2.2.1 The letter E at the beginning of each classification stands for electrode. The chemical symbol Ni appears right after the E as a means of identifying the electrodes as nickel base alloys. The other symbols (Cr, Fe, Mo, Co) in the designation are intended to group the electrodes according to their major alloying elements. The individual members of each family are designated by a numeral. These numerals are used only once in each family of compositions.

A2.2.2 Following the chemical symbols and their numeric designator comes the letter “T,” which is used to designate the filler metal as a flux cored electrode. As in the ISO system, two numeric digits, marked x and y, are appended. As defined in Table 2, the “x” stands for the welding position, and the “y” stands for the shielding gas (if any) with which the filler metal was classified by the manufacturer.

A2.3 In both systems “x” in Table 1 stands for the capability of the electrode for use out of position. As shown in Table 2, “0” is for flat and horizontal fillet positions only, and “1” for all position capability.

A2.4 In both systems the symbol “y” in Table 1 stands for the external shielding gas, if any: “1” for carbon dioxide (AWS A5.32/A5.32M Class SG-C) as the shielding gas, “3” for no external shielding gas, or “4” for 75% to 80% argon, balance carbon dioxide (AWS A5.32/A5.32M Class SG-AC-25 or SG-AC-20) shielding gas.

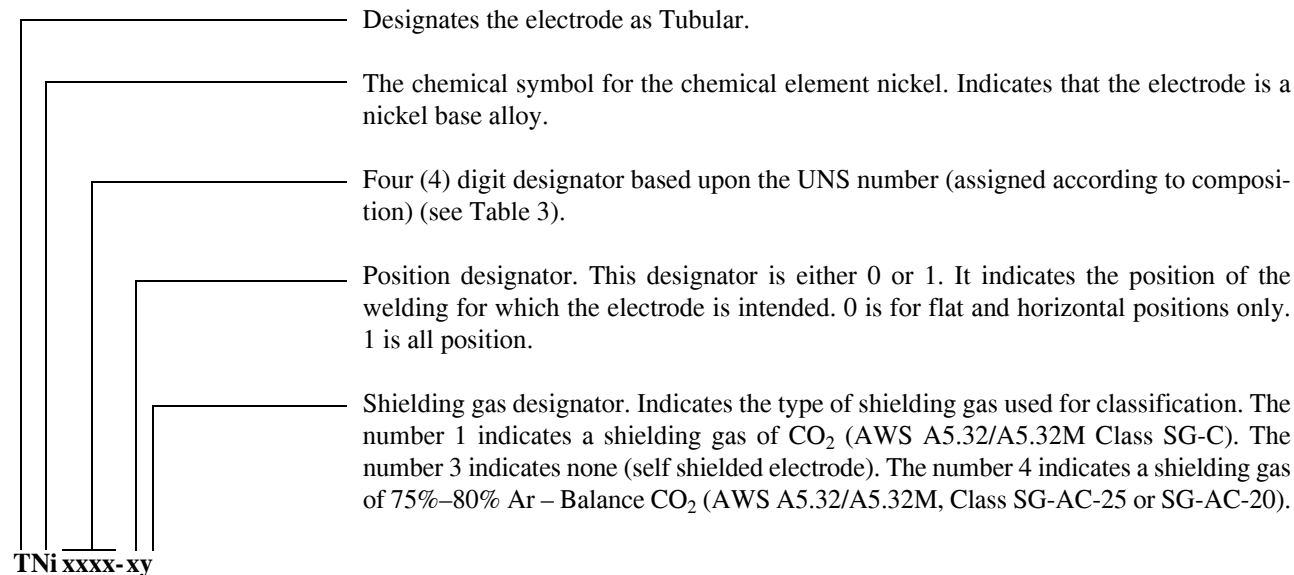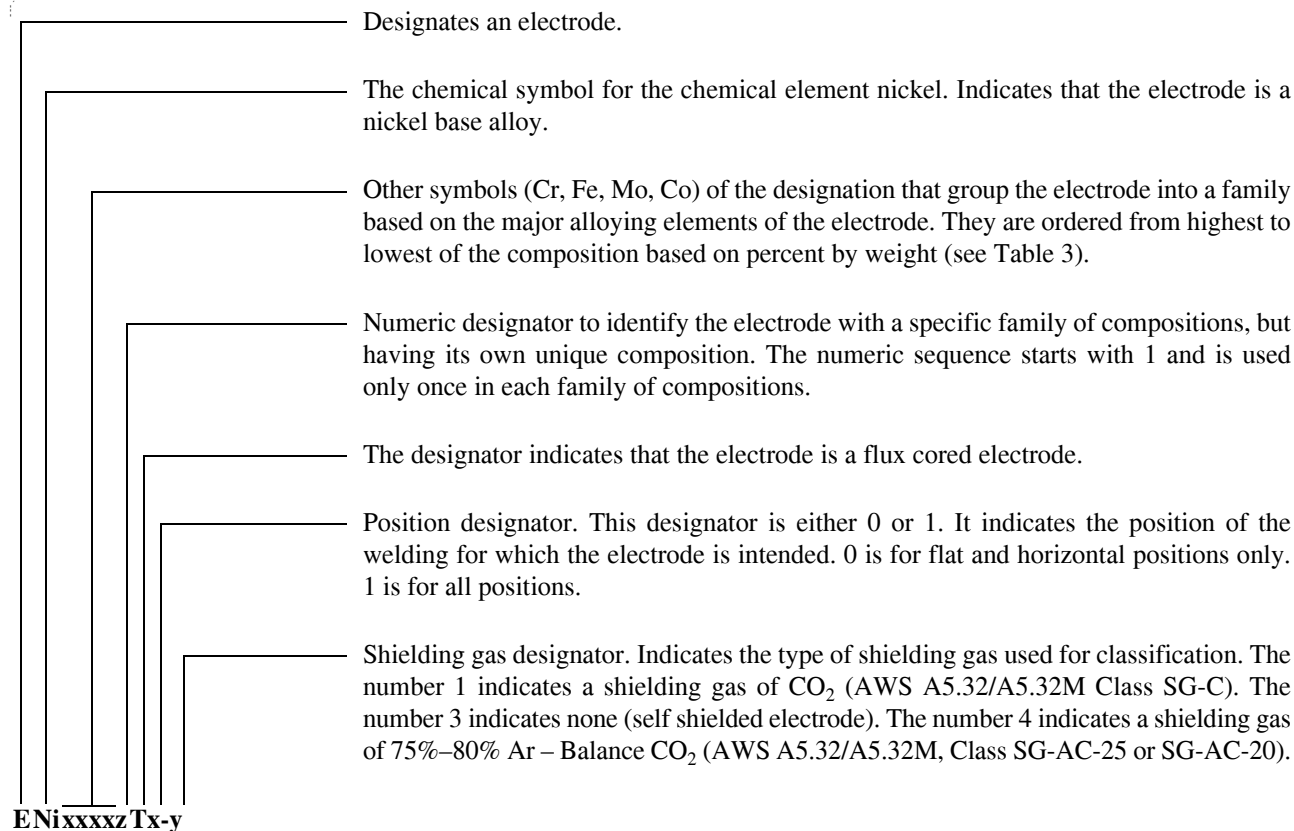Mandatory Classification Designators**Figure A.1—A5.34/A5.34M Classification System Utilizing the ISO Format****Mandatory Classification Designators****Figure A.2—A5.34/A5.34M Classification System Utilizing the Traditional Format**

A2.5 Many of the classifications in this specification correspond with classifications having the same composition in AWS A5.11 and A5.14. Where the composition of weld metal from the flux cored electrodes in this specification is similar to that of the covered electrodes in A5.11 and the bare wire in A5.14, an effort has been made to maintain the same composition designators for the corresponding electrode in this specification. A comparison of the classifications is given in Table A.1.

A3. Acceptance

Acceptance of all welding materials classified under this specification is in accordance with AWS A5.01, *Filler Metal Procurement Guidelines*, as the specification states. Any testing a purchaser requires of the supplier, for material shipped in accordance with this specification, shall be clearly stated in the purchase order, according to the provisions of AWS A5.01. In the absence of any such statement in the purchase order, the supplier may ship the material with whatever testing he normally conducts on material of that classification, as specified in Schedule F, Table 1, of AWS A5.01, *Filler Metal Procurement Guidelines*. Testing in accordance with any other Schedule in that Table must be specifically required by the purchase order. In such cases, acceptance of the material shipped will be in accordance with those requirements.

A4. Certification

The act of placing the AWS specification and classification designations on the packaging enclosing the product, or the classification on the product itself, constitutes the supplier's (manufacturer's) certification that the product meets all of the requirements of the specification.

The only testing requirement implicit in this "certification" is that the manufacturer has actually conducted the tests required by the specification on material that is representative of that being shipped and that the material met the requirements of the specification. Representative material, in this case, is any production run of that classification using the same formulation. "Certification" is not to be construed to mean that tests of any kind were necessarily conducted on samples of the specific material shipped. Tests on such material may, or may not, have been made. The basis for the "certification" required by the specification is the classification test of "representative material" cited above, and the "Manufacturer's Quality Assurance System" in AWS A5.01, *Filler Metal Procurement Guidelines*.

A5. Ventilation During Welding

A5.1 Five major factors govern the quantity of fumes in the atmosphere to which welders and welding operators are exposed during welding. These are as follows:

- (1) Dimensions of the space in which welding is done (with special regard to the height of the ceiling)

Table A.1
Comparison of Classifications^a

AWS Classification in A5.34/A5.34M		Corresponding Classification in A5.11/A5.11M	Corresponding Classification in A5.14/A5.14M
ISO Format ^b	Traditional		
TNi 6082-xy	ENiCr3Tx-y	—	ERNiCr-3
TNi 6062-xy	ENiCrFe1Tx-y	ENiCrFe-1	ERNiCrFe-5
TNi 6133-xy	ENiCrFe2Tx-y	ENiCrFe-2	ERNiCrFe-6
TNi 6182-xy	ENiCrFe3Tx-y	ENiCrFe-3	—
TNi 6002-xy	ENiCrMo2Tx-y	ENiCrMo-2	ERNiCrMo-2
TNi 6625-xy	ENiCrMo3Tx-y	ENiCrMo-3	ERNiCrMo-3
TNi 6276-xy	ENiCrMo4Tx-y	ENiCrMo-4	ERNiCrMo-4
TNi 6022-xy	ENiCrMo10Tx-y	ENiCrMo-10	ERNiCrMo-10
TNi 6117-xy	ENiCrCoMo1Tx-y	ENiCrCoMo-1	ERNiCrCoMo-1

^a This comparison is based on chemical composition only. Mechanical properties may not necessarily be the same.

^b The ISO format is based on the generic designations system set forth in the annex of IFS 2002: *International Index of Welding Filler Metal Classifications*. Table 10 B of that document applies to flux-cored nickel alloys. The four-digit number is intended to relate to the designations used for the corresponding covered electrodes and solid wire filler metals designated TNi in this specification, ENi in A5.11, and ERNi in A5.14.

(2) Number of welders and welding operators working in that space

(3) Rate of evolution of fumes, gases, or dust, according to the materials and processes involved

(4) The proximity of the welder or welding operator to the fumes as they issue from the welding zone, and to the gases and dusts in the space in which they are working

(5) The ventilation provided to the space in which the welding is done

A5.2 American National Standard ANSI Z49.1, *Safety in Welding, Cutting, and Allied Processes* (published by the American Welding Society), discusses the ventilation that is required during welding and should be referred to for details. Attention is drawn particularly to the clause of that document on Ventilation. Further details about ventilation can be found in AWS F3.2, *Ventilation Guide for Welding Fume*.

A6. Welding Considerations

A6.1 Before welding or heating any nickel-base alloy, the material must be clean. Oil, grease, paint, lubricants, marking pencils, temperature indicating materials, threading compounds, and other such materials frequently contain sulfur, lead, phosphorus, or other surface contaminants, which may cause cracking (embrittlement) of the base metal or the weld metal if present during welding or heating.

A6.2 Electrodes of some of the classifications are used for dissimilar metal welds. When making such welds it is important to obtain as little dilution as possible from the dissimilar metal member (steel, for example). This can be done by traveling slowly to deposit a thicker bead and to dissipate the energy of the arc against the molten weld metal or the nickel base metal rather than the steel member.

A6.3 Flux cored electrodes can absorb significant moisture if stored in a humid environment in damaged or open packages, especially if unprotected for a long period of time. In the case of excessive exposure, weldability, and weld integrity can be adversely affected. In the event the electrode has been exposed, the manufacturer should be consulted regarding possible reconditioning of the electrode.

A7. Description and Intended Use of Electrodes

A7.1 Nickel-Chromium Classifications

A7.1.1 TNi 6082-xy and ENiCr3Tx-y. The nominal composition (wt.-%) of the weld metal of this classifica-

tion is 72 Ni, 20 Cr, 3 Mn, 2.5 Nb (+ Ta). Electrodes of this classification are used for welding nickel-chromium-iron alloys, for dissimilar welding of nickel based alloys, for the clad side of joints in steel clad with nickel-chromium alloy, for surfacing steel with nickel-chromium-iron weld metal, and for joining carbon and low alloy steels to nickel-base alloys and to austenitic stainless steels. Typical specifications for the nickel-chromium-iron base metal are ASTM B 163, B 166, B 167, and B 168, all of which have UNS Number N06600.

A7.2 Nickel-Chromium-Iron Classifications

A7.2.1 TNi 6062-xy and ENiCrFe1Tx-y. The nominal composition (wt.-%) of the weld metal of this classification is 73 Ni, 15 Cr, 8 Fe, 2.5 Mn, 2.5 Nb (+ Ta). Electrodes of this classification are used for welding nickel-chromium-iron alloys, for the clad side of joints in steel clad with nickel-chromium-iron alloy, and for surfacing steel with nickel-chromium-iron weld metal. This electrode is also suitable for joining steel to nickel-base alloys. Typical specifications for the nickel-chromium-iron base metal are ASTM B 163, B 166, B 167, and B 168, all of which have UNS Number N06600.

A7.2.2 TNi 6133-xy and ENiCrFe2Tx-y. The nominal composition (wt.-%) of the weld metal of this classification is 70 Ni, 15 Cr, 8 Fe, 2 Mn, 2 Nb (+ Ta), 1.5 Mo. Electrodes of this classification are used for welding nickel-chromium-iron alloys, 9% nickel steel and a variety of dissimilar metal joints (involving carbon steel, low alloy steels, stainless steel, nickel and nickel-base alloys). The base metal can be wrought or cast (welding grade), or both. Typical specifications for the nickel-chromium-iron base metal are ASTM B 163, B 166, B 167, and B 168, all of which have UNS Number N06600. Weld metal of this classification is more resistant to fissuring than weld metal of the TNi6062-xy and ENiCrFe1Tx-y classification.

A7.2.3 TNi 6182-xy and ENiCrFe3Tx-y. The nominal composition (wt.-%) of the weld metal of this classification is 67 Ni, 15 Cr, 7 Fe, 7.5 Mn, 2 Nb (+ Ta). Electrodes of this classification are used for welding nickel-chromium-iron and nickel-iron-chromium alloys, for welding the clad side of joints in steel clad with nickel-chromium-iron alloy and steel clad with ferritic chromium steel, and for surfacing steel with nickel-chromium-iron weld metal, when comparatively high manganese content in the weld metal is not detrimental for the intended service. This electrode is frequently used for welding carbon steel and low alloy steels to austenitic stainless steels and nickel-base alloys. Typical specifications for nickel-chromium-iron base metal are ASTM B 163, B 166, B 167, and B 168, all of which have UNS

Number 06600. Typical specifications for nickel-iron-chromium base metals are ASTM B 407, B 409, B 512, and B 564, all of which have UNS Number N08800. Weld metal of this classification is more resistant to fissuring than weld metal of the TNi6062-xy (ENiCrFe1Tx-y) and TNi6133-xy (ENiCrFe2Tx-y) classifications.

A7.3 Nickel-Chromium-Molybdenum Classifications

A7.3.1 TNi 6002-xy and ENiCrMo2Tx-y. The nominal composition (wt.-%) of weld metal produced by electrodes of this classification is 47 Ni, 22 Cr, 18 Fe, 9 Mo, 1.5 Co. Electrodes of this classification are used for welding nickel-chromium-molybdenum alloys, for welding the clad side of joints in steel clad with nickel-chromium-molybdenum alloy, and for welding nickel-chromium-molybdenum alloys to steel and to other nickel-base alloys. Typical specifications for the nickel-chromium-molybdenum base metals are ASTM B 435, B 572, B 619, B 622, and B 626, all of which have UNS Number N06002.

A7.3.2 TNi 6625-xy and ENiCrMo3Tx-y. The nominal composition (wt.-%) of the weld metal of this classification is 60 Ni, 22 Cr, 9 Mo, 3 Fe, 3.6 Nb (+ Ta). Electrodes of this classification are used for welding nickel-chromium-molybdenum and nickel-iron-chromium alloys to themselves and to steel, and for surfacing steel with nickel-chromium-molybdenum weld metal. This electrode can be used also for welding other nickel-base alloys to steel. Typical specifications for the nickel-chromium-molybdenum base metal are ASTM B 443, B 444, and B 446, all of which have UNS Number N06625. Typical specifications for nickel-iron-chromium base metal are ASTM B 407, B 409, B 514, and B 564, all of which have UNS Number N08800.

A7.3.3 TNi 6276-xy and ENiCrMo4Tx-y. The nominal composition (wt.-%) of the weld metal of this classification is 57 Ni, 16 Mo, 15.5 Cr, 5.5 Fe, 4 W, low C. Electrodes of this classification are used for welding low carbon nickel-chromium-molybdenum alloy to steel or to other nickel-base alloys, and for clad side of joints in steel clad with low carbon NiCrMo alloys. Typical specifications for the nickel-chromium-molybdenum base metals are B 574, B 575, B 619, B 622, and B 626, all of which have UNS Number N10276.

A7.3.4 TNi 6022-xy and ENiCrMo10Tx-y. The nominal composition (wt.-%) of weld metal produced by electrodes of this classification is 56 Ni, 22 Cr, 13 Mo, 4 Fe, 3 W. Electrodes of this classification are used for welding nickel-chromium-molybdenum alloys, for the clad side of joints in steel clad with nickel-base alloys; and for joining nickel-chromium-molybdenum alloys. Typical specifications for the nickel-chromium-molybdenum base metals are ASTM B 574, B 575,

B 619, B 622, and B 626, all of which have UNS Number N06022.

A7.4 Nickel-Chromium-Cobalt-Molybdenum Classifications

A7.4.1 TNi 6117-xy and ENiCrCoMo1Tx-y. The nominal composition (wt.-%) of weld metal produced by electrodes of this classification is 52 Ni, 23 Cr, 12 Co, 9 Mo, 2 Fe, 1.5 Mn. Electrodes of this classification are used for welding nickel-chromium-cobalt-molybdenum alloys (UNS No. N06617) to themselves and to steel and for surfacing steel with nickel-chromium-cobalt-molybdenum weld metal. The electrodes are used for applications where optimum strength and oxidation resistance are required above 1500°F [820°C] up to 2100°F [1150°C], especially when welding on base metals of nickel-iron-chromium alloys.

A8. Mechanical Tests

The mechanical tests required for classification of an electrode in this specification measure the strength and ductility of the weld metal. These properties are sometimes less important than the corrosion and heat resistance of these weld metals. The mechanical tests (tension and bend tests), as well as the radiographic test, however, do provide an indication of the weld metal defects which, if present, may cause or contribute to premature failure in service.

A9. Special Tests

It is recognized that supplementary tests may be required for certain applications. In such cases, tests to determine specific properties such as corrosion resistance, scaling resistance, or strength at elevated or cryogenic temperatures may be required. AWS A5.01, *Filler Metal Procurement Guidelines*, contains provisions for ordering such tests. This clause is included for the guidance of those who desire to specify such tests which may be conducted as agreed upon between supplier and purchaser.

A9.1 Corrosion or Scaling Tests. Although welds made with electrodes in this specification are commonly used in corrosion and heat-resisting applications, tests for those properties are not included in the specification. When required for a particular application, tests can be conducted on specimens taken from either a weld pad or a welded joint. Specimens from a joint are suitable for qualifying the welding procedure (for a specific application involving corrosion or oxidation resistance) but not for qualifying the electrode. Tests on specimens from a joint have the disadvantage of being a combined test of

the properties of the weld metals, the heat-affected zone and the unaffected base metal. With them, it is more difficult to obtain reproducible data (when a difference exists in the properties of the metal in the various parts of the specimen). Specimens taken from a joint have the advantage of being able to duplicate the joint design and the welding sequence planned for fabrication.

A9.1.1 Specimens for testing corrosion or oxidation resistance of the weld metal alone are prepared by following the procedure outlined in 9.3 of the specification. The pad size should be at least 3/4 in [20 mm] in height, 2-1/2 in [65 mm] in width, and $1 + 5/8n$ in [25 + 16n mm] in length where n is a multiplier for the number of specimens required from the pad. Specimens measuring 1/2 in $\times$ 2 in $\times$ 1/4 in [13 mm $\times$ 50 mm $\times$ 6 mm] are machined from the top of the pad in a manner such that the 2 in [50 mm] dimension of the specimen is parallel to the 2-1/2 in [65 mm] dimension of the pad and the 1/2 in [13 mm] dimension is parallel with the length of the pad.

A9.1.2 The heat treatment, surface finish, and marking of the specimens prior to testing should be in accordance with standard practices for tests of similar alloys in the wrought or cast forms. The testing procedures should correspond to ASTM G 4, *Standard Practice for Conducting Plant Corrosion Tests*, or ASTM G 31, *Recommended Practice for Laboratory Immersion Corrosion Testing of Metals*, as the case may be.

A10. General Safety Considerations

A10.1 Safety and health issues and concerns are beyond the scope of this standard and, therefore, are not fully addressed herein. Some safety and health information can be found in Annex A, Clause A5. Safety and health information is available from other sources, including, but not limited to Safety and Health Fact Sheets listed in A10.3, ANSI Z49.1 *Safety in Welding, Cutting, and Allied Processes*,⁹ and applicable federal and state regulations.

A10.2 Safety and Health Fact Sheets. The Safety and Health Fact Sheets listed below are published by the American Welding Society (AWS). They may be down-

loaded and printed directly from the AWS website at <http://www.aws.org>. The Safety and Health Fact Sheets are revised and additional sheets added periodically.

A10.3 AWS Safety and Health Fact Sheets Index (SHF)¹⁰

No.	Title
1	<i>Fumes and Gases</i>
2	<i>Radiation</i>
3	<i>Noise</i>
4	<i>Chromium and Nickel in Welding Fume</i>
5	<i>Electrical Hazards</i>
6	<i>Fire and Explosion Prevention</i>
7	<i>Burn Protection</i>
8	<i>Mechanical Hazards</i>
9	<i>Tripping and Falling</i>
10	<i>Falling Objects</i>
11	<i>Confined Spaces</i>
12	<i>Contact Lens Wear</i>
13	<i>Ergonomics in the Welding Environment</i>
14	<i>Graphic Symbols for Precautionary Labels</i>
15	<i>Style Guidelines for Safety and Health Documents</i>
16	<i>Pacemakers and Welding</i>
17	<i>Electric and Magnetic Fields (EMF)</i>
18	<i>Lockout/Tagout</i>
19	<i>Laser Welding and Cutting Safety</i>
20	<i>Thermal Spraying Safety</i>
21	<i>Resistance Spot Welding</i>
22	<i>Cadmium Exposure from Welding & Allied Processes</i>
23	<i>California Proposition 65</i>
24	<i>Fluxes for Arc Welding and Brazing: Safe Handling and Use</i>
25	<i>Metal Fume Fever</i>
26	<i>Arc Welding Distance</i>
27	<i>Thoriated Tungsten Electrodes</i>
28	<i>Oxyfuel Safety: Check Valves and Flashback Arrestors</i>
29	<i>Grounding of Portable and Vehicle Mounted Welding Generators</i>
30	<i>Cylinders: Safe Storage, Handling, and Use</i>
31	<i>Eye and Face Protection for Welding and Cutting Operations</i>

⁹ ANSI Z49.1 is published by the American Welding Society, 550 N.W. LeJeune Road, Miami, FL 33126.

¹⁰ AWS standards are published by the American Welding Society, 550 N.W. LeJeune Road, Miami, FL 33126.

Annex B (Informative)

Guidelines for the Preparation of Technical Inquiries

This annex is not part of AWS A5.34/A5.34M:2007, *Specification for Nickel-Alloy Electrodes for Flux Cored Arc Welding*, but is included for informational purposes only.

B1. Introduction

The American Welding Society (AWS) Board of Directors has adopted a policy whereby all official interpretations of AWS standards are handled in a formal manner. Under this policy, all interpretations are made by the committee that is responsible for the standard. Official communication concerning an interpretation is directed through the AWS staff member who works with that committee. The policy requires that all requests for an interpretation be submitted in writing. Such requests will be handled as expeditiously as possible, but due to the complexity of the work and the procedures that must be followed, some interpretations may require considerable time.

B2. Procedure

All inquiries shall be directed to:

Managing Director
Technical Services Division
American Welding Society
550 N.W. LeJeune Road
Miami, FL 33126

All inquiries shall contain the name, address, and affiliation of the inquirer, and they shall provide enough information for the committee to understand the point of concern in the inquiry. When the point is not clearly defined, the inquiry will be returned for clarification. For efficient handling, all inquiries should be typewritten and in the format specified below.

B2.1 Scope. Each inquiry shall address one single provision of the standard unless the point of the inquiry

involves two or more interrelated provisions. The provision(s) shall be identified in the scope of the inquiry along with the edition of the standard that contains the provision(s) the inquirer is addressing.

B2.2 Purpose of the Inquiry. The purpose of the inquiry shall be stated in this portion of the inquiry. The purpose can be to obtain an interpretation of a standard's requirement or to request the revision of a particular provision in the standard.

B2.3 Content of the Inquiry. The inquiry should be concise, yet complete, to enable the committee to understand the point of the inquiry. Sketches should be used whenever appropriate, and all paragraphs, figures, and tables (or annex) that bear on the inquiry shall be cited. If the point of the inquiry is to obtain a revision of the standard, the inquiry shall provide technical justification for that revision.

B2.4 Proposed Reply. The inquirer should, as a proposed reply, state an interpretation of the provision that is the point of the inquiry or provide the wording for a proposed revision, if this is what the inquirer seeks.

B3. Interpretation of Provisions of the Standard

Interpretations of provisions of the standard are made by the relevant AWS technical committee. The secretary of the committee refers all inquiries to the chair of the particular subcommittee that has jurisdiction over the portion of the standard addressed by the inquiry. The subcommittee reviews the inquiry and the proposed reply to determine what the response to the inquiry should

be. Following the subcommittee's development of the response, the inquiry and the response are presented to the entire committee for review and approval. Upon approval by the committee, the interpretation is an official interpretation of the Society, and the secretary transmits the response to the inquirer and to the *Welding Journal* for publication.

B4. Publication of Interpretations

All official interpretations will appear in the *Welding Journal* and will be posted on the AWS web site.

B5. Telephone Inquiries

Telephone inquiries to AWS Headquarters concerning AWS standards should be limited to questions of a general nature or to matters directly related to the use of the standard. The *AWS Board Policy Manual* requires that all AWS staff members respond to a telephone request

for an official interpretation of any AWS standard with the information that such an interpretation can be obtained only through a written request. Headquarters staff cannot provide consulting services. However, the staff can refer a caller to any of those consultants whose names are on file at AWS Headquarters.

B6. AWS Technical Committees

The activities of AWS technical committees regarding interpretations are limited strictly to the interpretation of provisions of standards prepared by the committees or to consideration of revisions to existing provisions on the basis of new data or technology. Neither AWS staff nor the committees are in a position to offer interpretive or consulting services on (1) specific engineering problems, (2) requirements of standards applied to fabrications outside the scope of the document, or (3) points not specifically covered by the standard. In such cases, the inquirer should seek assistance from a competent engineer experienced in the particular field of interest.

AWS Filler Metal Specifications by Material and Welding Process

	OFW	SMAW	GTAW GMAW PAW	FCAW	SAW	ESW	EGW	Brazing
Carbon Steel	A5.2	A5.1	A5.18	A5.20	A5.17	A5.25	A5.26	A5.8, A5.31
Low-Alloy Steel	A5.2	A5.5	A5.28	A5.29	A5.23	A5.25	A5.26	A5.8, A5.31
Stainless Steel		A5.4	A5.9, A5.22	A5.22	A5.9	A5.9	A5.9	A5.8, A5.31
Cast Iron	A5.15	A5.15	A5.15	A5.15				A5.8, A5.31
Nickel Alloys		A5.11	A5.14	A5.34	A5.14			A5.8, A5.31
Aluminum Alloys		A5.3	A5.10					A5.8, A5.31
Copper Alloys		A5.6	A5.7					A5.8, A5.31
Titanium Alloys			A5.16					A5.8, A5.31
Zirconium Alloys			A5.24					A5.8, A5.31
Magnesium Alloys			A5.19					A5.8, A5.31
Tungsten Electrodes			A5.12					
Brazing Alloys and Fluxes								A5.8, A5.31
Surfacing Alloys	A5.21	A5.13	A5.21	A5.21	A5.21			
Consumable Inserts			A5.30					
Shielding Gases			A5.32	A5.32			A5.32	

This page is intentionally blank.

AWS Filler Metal Specifications and Related Documents

Designation	Title
FMC	<i>Filler Metal Comparison Charts</i>
IFS	<i>International Index of Welding Filler Metal Classifications</i>
UGFM	<i>User's Guide to Filler Metals</i>
A4.2M (ISO 8249: 2000 MOD)	<i>Standard Procedures for Calibrating Magnetic Instruments to Measure the Delta Ferrite Content Austenitic and Duplex Ferritic-Austenitic Stainless Steel Weld Metal</i>
A4.3	<i>Standard Methods for Determination of the Diffusible Hydrogen Content of Martensitic, Bainitic, and Ferritic Steel Weld Metal Produced by Arc Welding</i>
A4.4M	<i>Standard Procedures for Determination of Moisture Content of Welding Fluxes and Welding Electrode Flux Coverings</i>
A5.01	<i>Filler Metal Procurement Guidelines</i>
A5.02/A5.02M	<i>Specification for Filler Metal Standard Sizes, Packaging, and Physical Attributes</i>
A5.1/A5.1M	<i>Specification for Carbon Steel Electrodes for Shielded Metal Arc Welding</i>
A5.2/A5.2M	<i>Specification for Carbon and Low-Alloy Steel Rods for Oxyfuel Gas Welding</i>
A5.3/A5.3M	<i>Specification for Aluminum and Aluminum-Alloy Electrodes for Shielded Metal Arc Welding</i>
A5.4/A5.4M	<i>Specification for Stainless Steel Electrodes for Shielded Metal Arc Welding</i>
A5.5/A5.5M	<i>Specification for Low-Alloy Steel Electrodes for Shielded Metal Arc Welding</i>
A5.6	<i>Specification for Covered Copper and Copper-Alloy Arc Welding Electrodes</i>
A5.7/A5.7M	<i>Specification for Copper and Copper-Alloy Bare Welding Rods and Electrodes</i>
A5.8/A5.8M	<i>Specification for Filler Metals for Brazing and Braze Welding</i>
A5.9/A5.9M	<i>Specification for Bare Stainless Steel Welding Electrodes and Rods</i>
A5.10/A5.10M	<i>Specification for Bare Aluminum and Aluminum-Alloy Welding Electrodes and Rods</i>
A5.11/A5.11M	<i>Specification for Nickel and Nickel-Alloy Welding Electrodes for Shielded Metal Arc Welding</i>
A5.12/A5.12M	<i>Specification for Tungsten and Tungsten-Alloy Electrodes for Arc Welding and Cutting</i>
A5.13	<i>Specification for Surfacing Electrodes for Shielded Metal Arc Welding</i>
A5.14/A5.14M	<i>Specification for Nickel and Nickel-Alloy Bare Welding Electrodes and Rods</i>
A5.15	<i>Specification for Welding Electrodes and Rods for Cast Iron</i>
A5.16/A5.16M	<i>Specification for Titanium and Titanium Alloy Welding Electrodes and Rods</i>
A5.17/A5.17M	<i>Specification for Carbon Steel Electrodes and Fluxes for Submerged Arc Welding</i>
A5.18/A5.18M	<i>Specification for Carbon Steel Electrodes and Rods for Gas Shielded Arc Welding</i>
A5.19	<i>Specification for Magnesium Alloy Welding Electrodes and Rods</i>
A5.20/A5.20M	<i>Specification for Carbon Steel Electrodes for Flux Cored Arc Welding</i>
A5.21	<i>Specification for Bare Electrodes and Rods for Surfacing</i>
A5.22	<i>Specification for Stainless Steel Electrodes for Flux Cored Arc Welding and Stainless Steel Flux Cored Rods for Gas Tungsten Arc Welding</i>
A5.23/A5.23M	<i>Specification for Low-Alloy Steel Electrodes and Fluxes for Submerged Arc Welding</i>
A5.24/A5.24M	<i>Specification for Zirconium and Zirconium Alloy Welding Electrodes and Rods</i>
A5.25/A5.25M	<i>Specification for Carbon and Low-Alloy Steel Electrodes and Fluxes for Electroslag Welding</i>
A5.26/A5.26M	<i>Specification for Carbon and Low-Alloy Steel Electrodes for Electrogas Welding</i>
A5.28/A5.28M	<i>Specification for Low-Alloy Steel Electrodes and Rods for Gas Shielded Arc Welding</i>
A5.29/A5.29M	<i>Specification for Low-Alloy Steel Electrodes for Flux Cored Arc Welding</i>
A5.30/A5.30M	<i>Specification for Consumable Inserts</i>
A5.31	<i>Specification for Fluxes for Brazing and Braze Welding</i>
A5.32/A5.32M	<i>Specification for Welding Shielding Gases</i>
A5.34/A5.34M	<i>Specification for Nickel-Alloy Electrodes for Flux Cored Arc Welding</i>

This page is intentionally blank.

