



BS 302 : Part 3 : 1987

UDC 677.721 : 669.58 : 629.12

© British Standards Institution. No part of this publication may be photocopied or otherwise reproduced without the prior permission in writing of BSI

British Standard

Stranded steel wire ropes

Part 3. Specification for zinc coated ropes for ships

Câbles toronnés en acier

Partie 3. Câbles galvanisés pour la construction navale — Spécifications

Litzenseile aus Stahldrähten

Teil 3. Verzinkte Seile für Schiffe

British Standards Institution

Foreword

This Part of BS 302 has been prepared under the direction of the Mechanical Handling Standards Committee. It is one Part of a combined revision of BS 302 : 1968, BS 236 : 1968, BS 329 : 1968, BS 330 : 1968, BS 365 : 1968 and BS 3530 : 1968, which are withdrawn. BS 302 is now published in six Parts and takes account of both national and international developments since 1968.

This Part (Part 3) specifies requirements for zinc coated ropes for ships additional to the general requirements in Part 1. Other Parts specify the additional requirements for other particular uses of ropes:

- Part 2 Specification for ropes for general purposes
- Part 4 Specification for ropes for lifts
- Part 5 Specification for ropes for hauling purposes
- Part 6 Specification for ropes for mine hoisting

Two further Parts are in preparation, covering larger diameter ropes (64 mm to 205 mm diameter) and higher strength ropes and will be Parts 7 and 8 respectively.

In line with the principles of international standard ISO 2408, published by the International Organization for Standardization (ISO), the constructions are grouped according to the number of outer wires in the strands. The general requirements of BS 302 : Part 1 and the methods used for calculating breaking loads and approximate masses are in accordance with ISO 2408. In respect of individual usages the ropes in Parts 2 and 3 are fully in accordance with ISO 2408 and those in section two of Part 4 are in accordance with ISO 4344. In each of these Parts however, certain additional ropes still in common use in the UK have been included.

In line with current international practice, the term 'zinc coated' has been adopted in this standard in place of 'galvanized'. The terms are synonymous.

Purchasers ordering to BS 302 are advised to specify in their purchasing contract that the manufacturer operate a quality system in compliance with the appropriate Part of BS 5750, or suitable equivalent, to ensure themselves that products claimed to comply with BS 302 consistently achieve the required level of quality.

Wire rope users will find valuable information in the companion publication BS 6570 'Code of practice for the selection, care and maintenance of steel wire ropes'.

Compliance with a British Standard does not of itself confer immunity from legal obligations.

Contents

	Page
Foreword	Inside front cover
Committees responsible	Back cover
Specification	
1 Scope	2
2 Definitions	2
3 Compliance	2
4 Wire rope constructions and sizes	2
5 Material	2
6 Direction of lay	3
7 Lubrication	3
8 Minimum breaking load	3
Tables	
1 Wire rope constructions and sizes	2
2 Construction groups with steel core	3
3 6 x 12 construction group with fibre cores	4
4 6 x 24 construction group with fibre cores	5
5 6 x 19 construction group with fibre main core	6
6 6 x 37 construction group with fibre main core	7

Specification

1 Scope

This Part of BS 302 specifies the requirements for zinc coated steel wire ropes for ships and includes ropes for standing rigging, cargo lashings, moorings, towing and certain types of cargo handling gear. It is for use in conjunction with Part 1.

NOTE 1. Information to be supplied by the purchaser on the enquiry and order is given in appendix F of BS 302 : Part 1 : 1987.

NOTE 2. The titles of the publications referred to in this standard are listed on the inside back cover.

2 Definitions

For the purposes of this Part of BS 302, the definitions given in BS 302 : Part 1 apply.

3 Compliance

Ropes in accordance with BS 302 : Part 3 shall comply with this Part and with BS 302 : Part 1.

4 Wire rope constructions and sizes

Constructions and size ranges shall be as given in table 1.

NOTE. In the absence of a precise indication by the purchaser on the enquiry and order, the choice of construction within a group is at the discretion of the supplier.

5 Material

5.1 Wire

5.1.1 General. The wire used for the manufacture of wire ropes specified in this Part, as shown in table 1, shall comply with sections one and two of BS 2763 : 1982. The mechanical tests shall be confined to the tensile strength and torsion requirements.

5.1.2 Wire finish. The wire shall be zinc coated according to BS 2763. The zinc coating shall be class Z or class A.

NOTE. It will need to be stated by the purchaser on the enquiry and order if class A is required, otherwise class Z will be supplied.

5.1.3 Tensile grade of wires. The tensile grade of the wires, other than the king wires, shall be 1420 N/mm² * or 1570 N/mm² tensile grades, as indicated in tables 2 to 6

Table 1. Wire rope constructions and sizes

	Rope group	Description	Size range (diameter)	Typical construction
Ropes with steel wire main core	7 x 7	Up to seven outer wires in a strand. One layer of wires over a king wire.	mm 12 to 28	6 x 7 (6/1) WSC
	7 x 19	8 to 12 outer wires in a strand. Two layers of wires over a king wire.	32 to 48	6 x 19 (12/6/1) WSC
Ropes with fibre main core	6 x 12	8 to 15 outer wires in a strand. One layer of wires over a fibre strand core.	3 to 16	6 x 12 (12/Fibre) FC
	6 x 24	12 to 15 outer wires in a strand. Two layers of wires over a fibre strand core.	8 to 40	6 x 24 (15/9/Fibre) FC 6 x 24 (12/12 Fibre) FC
	6 x 19	8 to 12 outer wires in a strand. Two layers of wires over a king wire.	3 to 24	6 x 19 (12/6/1) FC 6 x 19 (9/9/1) FC
	6 x 37	14 to 18 outer wires in a strand. Three layers of wires over a king wire.	20 to 72	6 x 37 (18/12/6/1) FC

*1 N/mm² = 1 MPa.

except in the case of 3 mm to 7 mm diameter 6 x 12 and 6 x 19 constructions which shall be 1770 N/mm² tensile grade.

5.2 Rope main core

The main core of the rope shall be of fibre or steel as specified in table 1. Where a steel core is used it shall be a wire strand (WSC) of the same construction as the outer strands. Fibre cores (FC) shall comply with 3.2 of BS 302 : Part 1 : 1987.

6 Direction of lay

Ropes shall be right-hand ordinary lay.

7 Lubrication

Fibre main cores shall be treated and the wires of the rope shall be coated with a lubricant complying with 3.3 of BS 302 : Part 1 : 1987.

8 Minimum breaking load

The minimum breaking loads shall be as given in tables 2 to 6.

NOTE. For guidance, these tables also give approximate masses of ropes, calculated as in C.2 of BS 302 : Part 1 : 1987.

Table 2. Construction groups with steel core



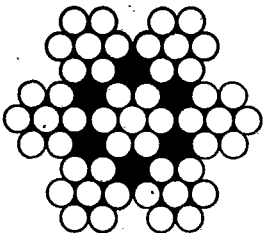
Table 2. Construction groups with steel core					
					
6 x 7 (6/1) WSC (7 x 7)		6 x 19 (12/6/1) WSC (7 x 19)			
Nominal diameter	Minimum breaking force		Minimum breaking load		Approximate mass
	1420 N/mm ² tensile grade	1570 N/mm ² tensile grade	1420 N/mm ² tensile grade	1570 N/mm ² tensile grade	
mm	kN	kN	t	t	kg/100 m
7 x 7 (6/1) group					
12	73.4	81.2	7.48	8.28	54.9
14	99.9	110	10.2	11.2	74.7
16	131	144	13.4	14.7	97.5
18	165	183	16.8	18.7	123
20	204	225	20.8	22.9	152
22	247	273	25.2	27.8	184
24	294	325	30.0	33.1	219
26	345	381	35.2	38.8	258
28	400	442	40.8	45.1	299
7 x 19 group					
32	483	534	49.2	54.4	390
36	611	676	62.3	68.9	494
40	754	834	76.9	85.0	610
44	913	1009	93.1	103	738
48	1086	1201	111	122	878


Table 3. 6 x 12 construction group with fibre cores

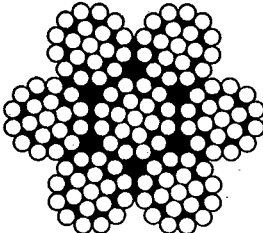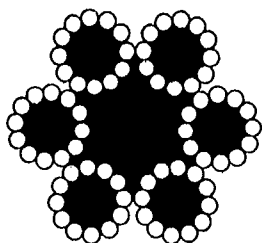


6 x 12 (12/Fibre) FC

Nominal diameter	Minimum breaking force			Minimum breaking load			Approximate mass
	1420 N/mm ² tensile grade	1570 N/mm ² tensile grade	1770 N/mm ² tensile grade	1420 N/mm ² tensile grade	1570 N/mm ² tensile grade	1770 N/mm ² tensile grade	
mm	kN	kN	kN	t	t	t	kg/100 m
3	—	—	3.33	—	—	0.34	2.26
4	—	—	5.92	—	—	0.60	4.02
5	—	—	9.25	—	—	0.94	6.28
6	—	—	13.3	—	—	1.36	9.04
7	—	—	18.1	—	—	1.85	12.3
8	19.0	21.0	—	1.94	2.14	—	16.1
9	24.0	26.6	—	2.45	2.71	—	20.3
10	29.7	32.8	—	3.03	3.34	—	25.1
12	42.7	47.3	—	4.35	4.82	—	36.1
14	58.2	64.3	—	5.93	6.55	—	49.2
16	76.0	84.0	—	7.75	8.56	—	64.3

Table 4. 6 x 24 construction group with fibre cores

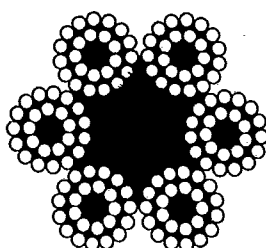


6 x 24 (15/9/Fibre) FC

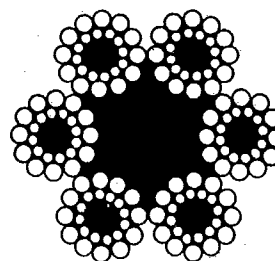


6 x 24 (12/12/F) FC

Nominal diameter	Minimum breaking force		Minimum breaking load		Approximate mass
	1420 N/mm ² tensile grade	1570 N/mm ² tensile grade	1420 N/mm ² tensile grade	1570 N/mm ² tensile grade	
mm	kN	kN	t	t	kg/100 m
8	25.4	28.1	2.59	2.86	19.7
9	32.2	35.6	3.28	3.63	24.9
10	39.8	44.0	4.06	4.49	30.8
11	48.1	53.2	4.90	5.42	37.3
12	57.3	63.3	5.84	6.45	44.4
13	67.2	74.3	6.85	7.57	52.1
14	77.9	86.2	7.94	8.79	60.4
16	102	113	10.4	11.5	78.8
18	129	142	13.1	14.5	99.8
19	144	159	14.7	16.2	111
20	159	176	16.2	17.9	123
22	192	213	19.6	21.7	149
24	229	253	23.3	25.8	177
26	269	297	27.4	30.3	208
28	312	345	31.8	35.2	241
32	407	450	41.5	45.9	315
35	487	539	49.6	54.9	377
36	515	570	52.5	58.1	399
38	574	635	58.5	64.7	445
40	636	703	64.8	71.7	493

Table 5. 6 x 19 construction group with fibre main core

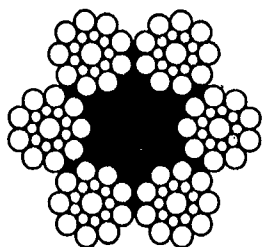


6 x 19 (9/9/1) FC

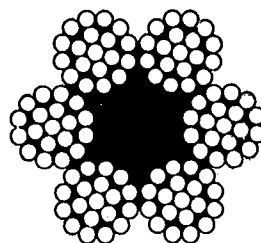

6 x 19 (12/6/1) FC

Nominal diameter	Minimum breaking force		Minimum breaking load		Approximate mass
	1420 N/mm ² tensile grade	1770 N/mm ² tensile grade	1420 N/mm ² tensile grade	1770 N/mm ² tensile grade	
mm	kN	kN	t	t	kg/100 m
3	—	4.89	—	0.50	3.1
4	—	8.69	—	0.89	5.5
5	—	13.6	—	1.39	8.6
6	—	19.6	—	2.0	12.5
7	—	26.6	—	2.71	17.0
8	27.9	—	2.84	—	22.1
10	43.6	—	4.44	—	34.6
12	62.8	—	6.40	—	49.8
14	85.4	—	8.71	—	67.8
16	112	—	11.4	—	88.6
18	141	—	14.4	—	112
20	174	—	17.7	—	138
22	211	—	21.5	—	167
24	251	—	25.6	—	199

Table 6. 6 x 37 construction group with fibre main core

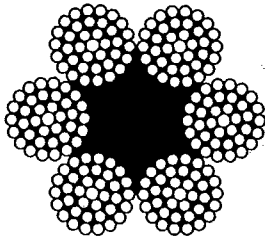

6 x 37 (18/12/6/1) FC

Nominal diameter	Minimum breaking force		Minimum breaking load		Approximate mass
	1420 N/mm ² tensile grade	1570 N/mm ² tensile grade	1420 N/mm ² tensile grade	1570 N/mm ² tensile grade	
mm	kN	kN	t	t	kg/100 m
20	168	185	17.1	18.9	138
22	203	224	20.7	22.8	167
24	241	267	24.6	27.2	199
26	283	313	28.8	31.9	234
28	328	363	33.4	37.0	271
32	429	474	43.7	48.3	354
36	543	600	55.4	61.2	448
40	670	741	68.3	75.5	554
44	811	897	82.7	91.4	670
48	965	1067	98.4	109	797
52	1133	1252	115	128	936
56	1314	1452	134	148	1085
60	1508	1667	154	170	1246
64	1716	1897	175	193	1417
68	1937	2142	197	218	1600
72	2172	2401	221	245	1794

Publications referred to

- BS 2763 Specification for round carbon steel wire for wire ropes
- BS 5750* Quality systems
Part 2 Specification for manufacture and installation
- BS 6570* Code of practice for the selection, care and maintenance of steel wire ropes
- ISO 2408* Steel wire ropes for general purposes — Characteristics
- ISO 4344* Steel wire ropes for lifts

*Referred to in the foreword only.

BS 302 : Part 3 : 1987

This British Standard, having been prepared under the direction of the Mechanical Handling Standards Committee, was published under the authority of the Board of BSI and comes into effect on 30 June 1987.

© British Standards Institution, 1987

First published, as BS 302, September 1927

First revision, as BS 302 and 621, December 1957

Second revision, as BS 302, May 1968

Third revision, as BS 302 : Part 3, June 1987.

ISBN 0 580 15642 7

The following BSI references relate to the work on this standard:
Committee reference MHE/2 Draft for comment 85/70787 DC

British Standards Institution. Incorporated by Royal Charter, BSI is the independent national body for the preparation of British Standards. It is the UK member of the International Organization for Standardization and UK sponsor of the British National Committee of the International Electrotechnical Commission.

In addition to the preparation and promulgation of standards, BSI offers specialist services including the provision of information through the BSI Library and Standardline Database; Technical Help to Exporters; and other services. Advice can be obtained from the Enquiry Section, BSI, Milton Keynes MK14 6LE, telephone 0908 221166, telex 825777.

Copyright. Users of British Standards are reminded that copyright subsists in all BSI publications. No part of this publication may be

reproduced in any form without the prior permission in writing of BSI. This does not preclude the free use, in the course of implementing the standard, of necessary details such as symbols and size, type or grade designations. Enquiries should be addressed to the Publications Manager, BSI, Linford Wood, Milton Keynes MK14 6LE. The number for telephone enquiries is 0908 220022 and for telex 825777.

Contract requirements. A British Standard does not purport to include all the necessary provisions of a contract. Users of British Standards are responsible for their correct application.

Revision of British Standards. British Standards are revised, when necessary, by the issue either of amendments or of revised editions. It is important that users of British Standards should ascertain that they are in possession of the latest amendments or editions.

Automatic updating service. BSI provides an economic, individual and automatic standards updating service called **PLUS**. Details are available from BSI Enquiry Section at Milton Keynes, telephone 0908 221166, telex 825777.

Information on all BSI publications is in the *BSI Catalogue*, supplemented each month by *BSI News* which is available to subscribing members of BSI and gives details of new publications, revisions, amendments and withdrawn standards. Any person who, when making use of a British Standard, encounters an inaccuracy or ambiguity, is requested to notify BSI without delay in order that the matter may be investigated and appropriate action taken.

Committees responsible for this British Standard

The preparation of this British Standard was entrusted by the Mechanical Handling Standards Committee (MHE/-) to Technical Committee MHE/2, upon which the following bodies were represented:

Associated Offices Technical Committee

Association of Supervisory and Executive Engineers

British Coal

British Ports Association and the National Association of Ports Employers

British Railways Board

British Steel Industry (Wire Section)

Bureau Veritas

Chain Testers Association of Great Britain

Department of the Environment (Property Services Agency)

Federation of Manufacturers of Construction Equipment and Cranes

Federation of Wire Rope Manufacturers of Great Britain

Health and Safety Executive

Institution of Mechanical Engineers

Institution of Mining Engineers

Institution of Mining and Metallurgy

Ministry of Defence

National Association of Lift Makers

Zinc Development Association

Amendments issued since publication

Amd. No.	Date of issue	Text affected

British Standards Institution · 2 Park Street London W1A 2BS · Telephone 01-629 9000 · Telex 266933